

ISSN 2518-170X (Online),  
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ  
Satbayev University

# Х А Б А Р Л А Р Ы

---

---

## ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК  
РЕСПУБЛИКИ КАЗАХСТАН  
Satbayev University

## NEWS

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF KAZAKHSTAN  
Satbayev University

**SERIES  
OF GEOLOGY AND TECHNICAL SCIENCES**

**4 (442)**

**JULY – AUGUST 2020**

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

---

*NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.*

*Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.*

*НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.*

Б а с р е д а к т о р ы  
э. ғ. д., профессор, ҚР ҰҒА академигі

**И.К. Бейсембетов**

Бас редакторының орынбасары  
**Жолтаев Г.Ж.** проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

**Абаканов Т.Д.** проф. (Қазақстан)  
**Абишева З.С.** проф., академик (Қазақстан)  
**Абсадықов Б.Н.** проф., корр.-мүшесі (Қазақстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Әзірбайжан)  
**Бакиров А.Б.** проф., (Қырғызстан)  
**Буктуков Н.С.** проф., академик (Қазақстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Тәжікстан)  
**Грэвис Р.М.** проф. (АҚШ)  
**Жарменов А.А.** проф., академик (Қазақстан)  
**Конторович А.Э.** проф., академик (Ресей)  
**Курскеев А.К.** проф., академик (Қазақстан)  
**Курчавов А.М.** проф., (Ресей)  
**Медеу А.Р.** проф., академик (Қазақстан)  
**Мұхамеджанов М.А.** проф., корр.-мүшесі (Қазақстан)  
**Оздоев С.М.** проф., академик (Қазақстан)  
**Постолатий В.** проф., академик (Молдова)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (АҚШ)  
**Штейнер М.** проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы».

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан Республикасының Ақпарат және қоғамдық даму министрлігінің Ақпарат комитетінде 29.07.2020 ж. берілген № **KZ39VRY00025420** мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,  
<http://www.geolog-technical.kz/index.php/en/>

---

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2020

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыр көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «NurNaz GRACE», Алматы қ., Рысқұлов көш., 103.

Г л а в н ы й р е д а к т о р  
д. э. н., профессор, академик НАН РК

**И. К. Бейсембетов**

Заместитель главного редактора  
**Жолтаев Г.Ж.** проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

**Абаканов Т.Д.** проф. (Казахстан)  
**Абишева З.С.** проф., академик (Казахстан)  
**Абсадыков Б.Н.** проф., чл.-корр. (Казахстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Азербайджан)  
**Бакиров А.Б.** проф., (Кыргызстан)  
**Буктуков Н.С.** проф., академик (Казахстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Таджикистан)  
**Грэвис Р.М.** проф. (США)  
**Жарменов А.А.** проф., академик (Казахстан)  
**Конторович А.Э.** проф., академик (Россия)  
**Курскеев А.К.** проф., академик (Казахстан)  
**Курчавов А.М.** проф., (Россия)  
**Медеу А.Р.** проф., академик (Казахстан)  
**Мухамеджанов М.А.** проф., чл.-корр. (Казахстан)  
**Оздоев С.М.** проф., академик (Казахстан)  
**Постолатий В.** проф., академик (Молдова)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (США)  
**Штейнер М.** проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации Министерства информации и общественного развития Республики Казахстан № **KZ39VPY00025420**, выданное 29.07.2020 г.

Периодичность: 6 раз в год.

Тираж: 300 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,  
<http://www.geolog-technical.kz/index.php/en/>

---

© Национальная академия наук Республики Казахстан, 2020

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: «NurNaz GRACE», г. Алматы, ул. Рыскулова, 103.

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

**I. K. Beisembetov**

Deputy editor in chief

**Zholtayev G.Zh.** prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

**Abakanov T.D.** prof. (Kazakhstan)  
**Abisheva Z.S.** prof., academician (Kazakhstan)  
**Absadykov B.N.** prof., corr. member. (Kazakhstan)  
**Agabekov V.Ye.** academician (Belarus)  
**Aliyev T.** prof., academician (Azerbaijan)  
**Bakirov A.B.** prof., (Kyrgyzstan)  
**Buktukov N.S.** prof., academician (Kazakhstan)  
**Bulat A.F.** prof., academician (Ukraine)  
**Ganiyev I.N.** prof., academician (Tadjikistan)  
**Gravis R.M.** prof. (USA)  
**Zharmenov A.A.** prof., academician (Kazakhstan)  
**Kontorovich A.Ye.** prof., academician (Russia)  
**Kurskeyev A.K.** prof., academician (Kazakhstan)  
**Kurchavov A.M.** prof., (Russia)  
**Medeu A.R.** prof., academician (Kazakhstan)  
**Muhamedzhanov M.A.** prof., corr. member. (Kazakhstan)  
**Ozdoyev S.M.** prof., academician (Kazakhstan)  
**Postolatii V.** prof., academician (Moldova)  
**Stepanets V.G.** prof., (Germany)  
**Humphery G.D.** prof. (USA)  
**Steiner M.** prof. (Germany)

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.**

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty).

The certificate of registration of a periodical printed publication in the Committee of information of the Ministry of Information and Social Development of the Republic of Kazakhstan **No. KZ39VPY00025420**, issued 29.07.2020.

Periodicity: 6 times a year.

Circulation: 300 copies.

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,

<http://www.geolog-technical.kz/index.php/en/>

---

© National Academy of Sciences of the Republic of Kazakhstan, 2020

Editorial address: Institute of Geological Sciences named after K.I. Satpayev

69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: «NurNaz GRACE», 103, Ryskulov str, Almaty.

**NEWS**

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

**SERIES OF GEOLOGY AND TECHNICAL SCIENCES**

ISSN 2224-5278

Volume 4, Number 442 (2020), 120 – 126

<https://doi.org/10.32014/2020.2518-170X.92>

UDC 625.7/.8:691.16

**M. Zh. Zhurinov<sup>1</sup>, B. B. Teltayev<sup>2</sup>, A. A. Kalybai<sup>2</sup>, C. O. Rossi<sup>3</sup>, Ye. D. Amirbayev<sup>2</sup>**

<sup>1</sup>JSC “D. V. Sokolskiy Institute of Fuel, Catalysis and Electrochemistry”, Almaty, Kazakhstan;

<sup>2</sup>JSC “Kazakhstan Highway Research Institute”, Almaty, Kazakhstan;

<sup>3</sup>University of Calabria, Rende, Italy.

E-mail: nanrk.mzh@mail.ru, ao\_kazdornii@mail.ru, cesare.oliviero@unical.it

**COMPARATIVE ANALYSIS OF STANDARD INDICATORS  
FOR NANOCARBON ASPHALT CONCRETE  
AND OTHER ASPHALT CONCRETES**

**Abstract.** A comparative analysis of the standard indicators for a nanoasphalt concrete of the type B prepared with the use of a nanocarbon powder and the asphalt concretes of the type B and stone mastic asphalt concretes (SMA20) with modifiers and without them has been performed in the work. The bitumens of the grades BND 70/100, BND 100/130 and BND 130/200 have been used for preparing of the asphalt concretes. The bitumens of the grades BND 70/100 and BND 100/130 have been produced by the Pavlodar petrochemical plant, and the bitumen of the grade BND 130/200 has been manufactured by compounding of the bitumen of the grade BND 100/130 and the petroleum tar of the same plant in Kazakhstan Highway Research Institute. A nanopowder (150-200 nm) has been manufactured from a coal rock of the deposit “Saryadyr” of the “Corpoation “ON-Olza” LLP (Akmola region) by three-stage size reduction sequentially in a mechanical dispergator (up to 2-3 mm), an aerodynamic mill (up to 20 mcm) and a reactor with a rotating electromagnetic field (150-200 nm).

To compare the standard indicators of 13 types of asphalt concretes have been prepared. The standard indicators of the asphalt concretes have been determined in a laboratory under the standard ST RK 1218-2003. The comparative analysis has been performed under the following 6 main standard indicators: a compression strength at the temperature of 50 °C; a compression strength at the temperature of 20 °C; a compression strength at the temperature of 0 °C; the shear resistance (at friction at the temperature of 50 °C); the crack resistance at the temperature of 0 °C; the water saturation.

It is found out that the nanoasphalt concrete under the considered standard indicators can substitute practically all the main types of the asphalt concretes used in a road construction in many countries of the world and in Kazakhstan. It has essentially high resistance to the shear, low temperature and fatigue failures, cyclic freezing and thawing.

**Keywords:** bitumens, carbon nanopowder, polymers, crumb rubber, asphalt concretes, stone mastic asphalt concretes, standard indicators.

**1. Introduction.** An asphalt concrete is one of the main road materials in the world. It is used, as a rule, for construction of the upper road surfacing layers – a pavement of highways. Therefore, it is exactly the pavement from the asphalt concrete which sustains the strongest weather-climatic and mechanical impacts during its full service life. The road asphalt concrete should have a complex of the required properties to become sufficiently resistant to the above impacts. As the multiyear experience shows the composition, the technology of preparing and construction of the asphalt concretes are constantly improved to have all the required properties. At present all over the world it is considered that it is possible to achieve the considerable increase of the operational characteristics of the road asphalt concretes by the modification of the bitumens with different polymers.

The works [1-4] show the possibility of the essential increase for the low temperature characteristics of the road bitumens by their modification with a nanocarbon powder. Based on the electromagnetic theory [5,6] and the quantum physics [7] a physic-chemical phenomenon has been explained for a group

chemical composition variation of the bitumen which stipulated the essential variation of the low temperature characteristics of the bitumen. The work [8] demonstrates the increased characteristics of ananoasphaltconcrete of the type B prepared with the use of the bitumen with the nanocarbon powder we obtained before. This article is a continuation of our above works, and it gives the results of the comparative analysis for the standard indicators of the nanoasphalt concrete of the type B and 12 other main types of asphalt concrete: 2 asphalt concretes of the type B, 5 asphalt concretes of the type B with the polymers and a crumb rubber, 5 types of stone mastic asphalt concretes (SMA 20) with polymers and without them.

## 2. Materials and methods.

**2.1. Bitumens.** In this work the road bitumens of three grades (BND 70/100, BND 100/130 and BND 130/200) satisfying the requirements of the standard ST RK 1373-2013 have been used for preparing of the asphalt concretes of 13 different types including thenanoasphalt concrete of the type B. In this work the polymers Elvaloy 4170, Calprene 501, Butonal NS 198, SBS L30-01 A and a crumb rubber have been used as the modifiers. The bitumens modified with the polymers satisfy the requirements of the standard ST RK 2534-2014. The detailed information about preparing of the bitumens modified with the polymers one can obtain in the work [9].

The nanopowder (150-200 nm) has been manufactured from a coal rock of the deposit “Saryadyr” (“Corpoation “ON-Olza” LLP, Akmola region). First for the purpose of provision a homogeneous distribution of the nanopowder particles in the bitumen the nanocarbon powder has been dispersed in a kerosene under the impact of an ultrasound with the frequency of 20 kHz for 5 minutes at a room temperature. Then the dispersed solution (kerosene+nanopowder) has been added to the bitumen at the temperature of 160 °C and constant mixing for 30 minutes.

**2.2. Asphalt concretes.** For the purpose of the determination of the standard indicators the next 13 types of asphalt concretes have been prepared and tested: a nanoasphalt concrete of the type B, 2 asphalt concretes of the type B, 5 asphalt concretes of the type B with polymers and a crumb rubber, 5 type of the stone mastic asphalt concretes (SMA 20) with the polymers and without them. The data about the prepared and tested asphalt concretes are given in the Table 1. The asphalt concrete mixes have been prepared in accordance with the requirements of the following relevant standards:

Data about the tested types of asphalt concretes

Serial number	Type of asphalt concrete	Grade of bitumen	Modifier	Content of modifier, %	Contracted notation
1	Dense fine-grained, type B	BND 70/100	–	–	B-70-100
2	Dense fine-grained, type B	BND 70/100	nanocarbon	2.0	B-70-100+nano
3	Dense fine-grained, type B	BND 100/130	–	–	B-100-130
4	Dense fine-grained, type B	BND 100/130	polymer Elvaloy 4170	1.4	B-100-130+Elvaloy
5	Dense fine-grained, type B	BND 100/130	polymer Calprene 501	4.0	B-100-130+Calprene
6	Dense fine-grained, type B	BND 100/130	polymer Butonal NS 198	3.0	B-100-130+Butonal
7	Dense fine-grained, type B	BND 100/130	Crumb rubber	10	B-100-130+CR10
8	Dense fine-grained, type B	BND 100/130	Crumb rubber	15	B-100-130+CR15
9	Stone mastic asphalt concrete-20	BND 100/130	–	–	SMA-100-130
10	Stone mastic asphalt concrete-20	BND 130/200	polymer Elvaloy 4170	1.7	SMA-130-200+Elvaloy
11	Stone mastic asphalt concrete-20	BND 130/200	polymer Calprene 501	6.0	SMA-130-200+Calprene
12	Stone mastic asphalt concrete-20	BND 130/200	polymer Butonal NS 198	3.5	SMA-130-200+Butonal
13	Stone mastic asphalt concrete-20	BND 130/200	polymer SBLS30-01 A	5.0	SMA-130-200+SBS

The asphalt concretes and thenanoasphalt concrete of the type B – ST RK 1225-2019; the polymer asphalt concretes of the type B – ST RK 1223-2019; the asphalt concretes of the type B with the crumb rubber – ST RK 2028-2010; the stone mastic asphalt concrete (SMA 20) – under GOST 31015-2002; the stone mastic asphalt concretes (SMA 20) with the polymers – ST RK 2373-2019.

### 3. Results and discussion

**3.1. Compression strength at the temperature of 50 °C.** It is found out in our work [8] that the strength of the asphalt concrete of the type B with nanocarbon bitumen (content of the carbon nanopowder is 2%) at compression at the temperature of 50 °C is higher for 29% than the strength of the conventional asphalt concrete of the type B. Now we can see (figure 1) that the strength of the nanoasphalt concrete of the type B at 50 °C is higher than the average strength of the stone mastic asphalt concretes nearly for 60% and not lower than the minimum allowed strength of the polymer asphalt concretes of the type B.

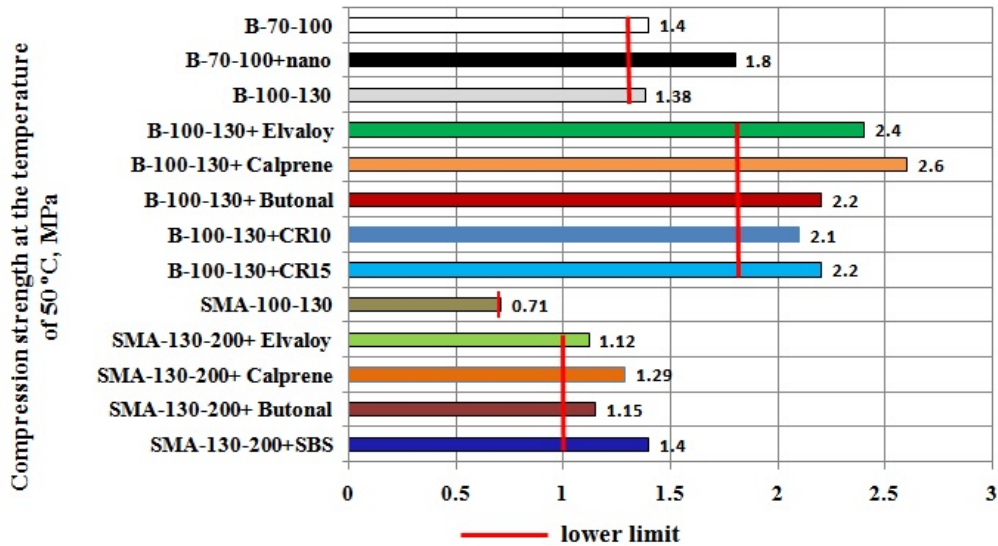


Figure 1 – Compression strength of the asphalt concretes at the temperature of 50°C

**3.2. Compression strength at the temperature of 20°C.** It is clearly seen (figure 2) that the values of this indicator for the compared asphalt concretes are varied within narrow limits (3.2-4.1 MPa), i.e. they have the similar values. Meanwhile, the nanoasphalt concrete of the type B has the strength (3.5 MPa) essentially higher than the minimum allowed values for all the compared asphalt concretes. The minimum allowed value of the compression strength at the temperature of 20°C for the asphalt concretes of the type B and the stone mastic asphalt concrete without a polymer is equal to 2.5 MPa, and it is equal to 2.8 MPa for the stone mastic asphalt concretes with the polymers. For example, the nanoasphalt concrete has the strength at the temperature of 20°C higher than the minimum allowed value for the asphalt concretes of type B without polymers and for the stone mastic polymer asphalt concretes for 40% and 25% respectively.

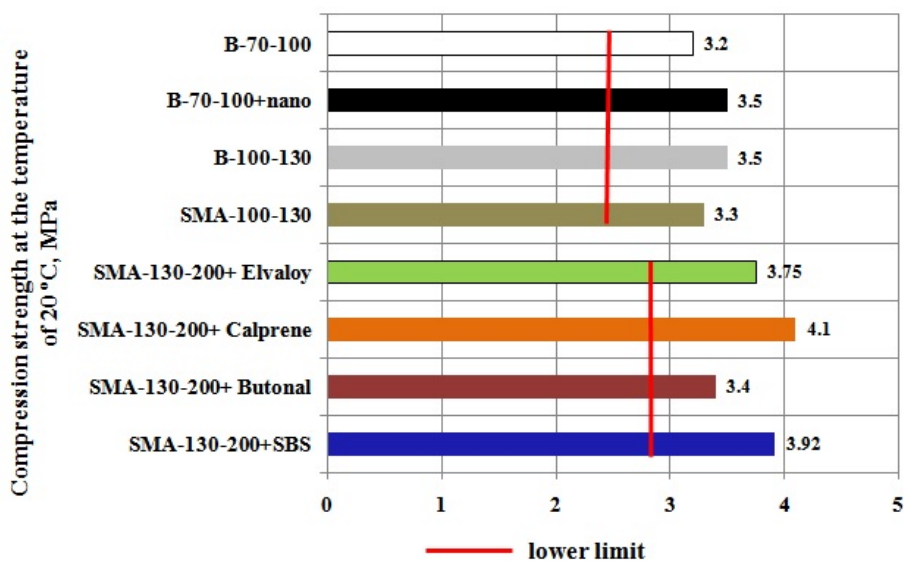


Figure 2 – Compression strength of the asphalt concretes at the temperature of 20°C



**3.3. Compression strength at the temperature of 0 °C.** It is found out in our work [8] that the strength at 0°C for the nanoasphalt concrete of the type B is nearly 2 times (44%) lower than for the conventional asphalt concrete of the type B. Now we can see (figure 3) that the nanoasphalt concrete reigns supreme under this indicator – its strength at 0°C is nearly 2 times (more exactly 1.91 times) lower than the average strength of other compared asphalt concretes.

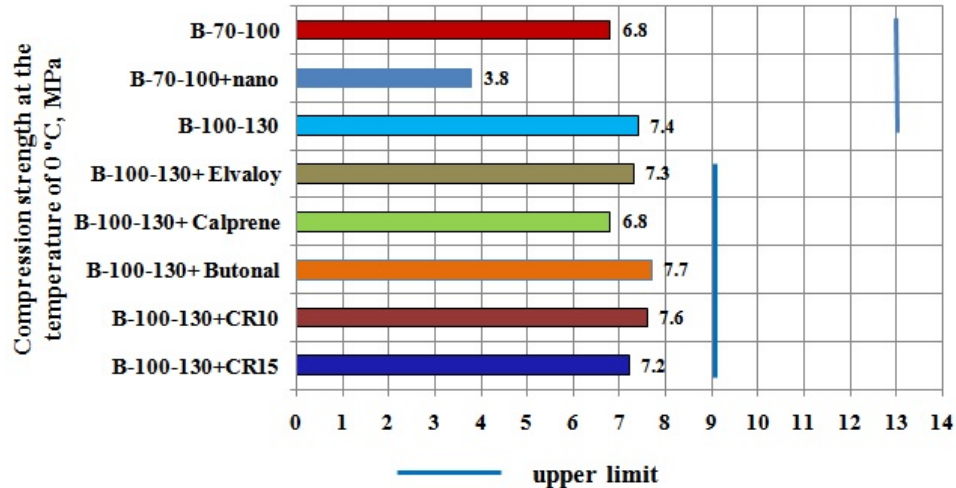


Figure 3 – Compression strength of the asphalt concretes at the temperature of 0°C

**3.4. Shear resistance.** It is found out in our work [8] that the nanoasphalt concrete of the type B has the shear resistance for 43% higher than for the conventional asphalt concrete of the type B. And now it is clearly seen (figure 4) that under this indicator the nanoasphalt concrete is one of the best among the compared ones: its shear resistance is more for 48%, 25% and 2.04 times compared with the conventional asphalt concretes of the type B, the asphalt concretes of the type B with the polymers and the stone mastic asphalt concretes with the polymers and without them.

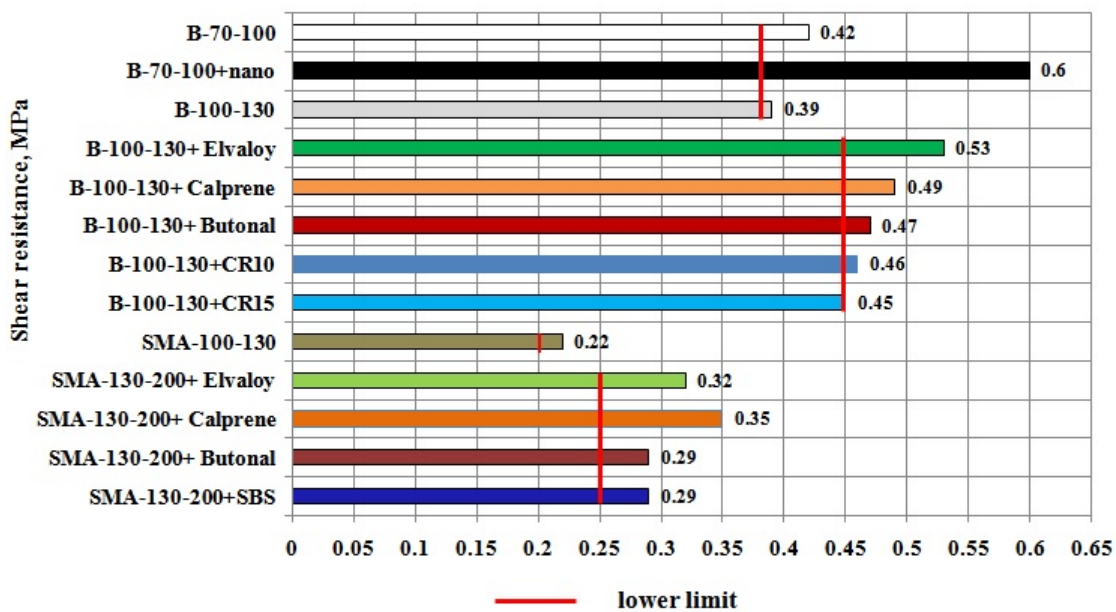


Figure 4 – Shear resistance of the asphalt concretes (at friction at the temperature of 50°C)

**3.5. Crack resistance at the temperature of 0°C.** It is seen from the figure 5 that the nanoasphalt concrete of the type B has the crack resistance considerably lower than the maximum allowed values for all the considered types of the asphalt concretes. This fact indicates that the nanoasphalt concrete according to the considered standard indicator can substitute practically all the main types of the asphalt concretes used in a road construction in many countries of the world including Kazakhstan.

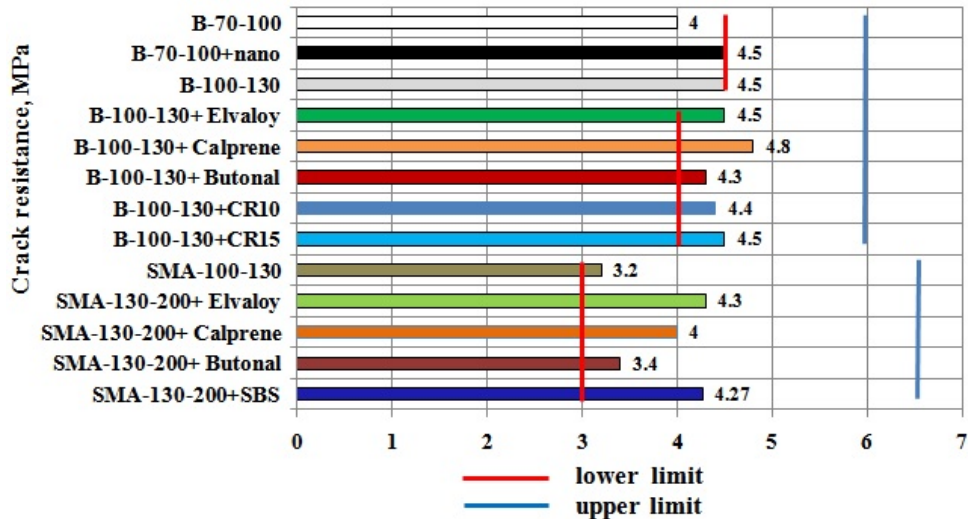


Figure 5. Crack resistance of the asphalt concretes at the temperature of 0°C

**3.6. Water saturation.** It has been found out in our work [8] that the water saturation for the nanoasphalt concrete of the type B is for 18% less than for the conventional asphalt concrete of the type B. And now it is seen (figure 6) that except for the asphalt concrete of the type B with the polymer Calprene the nanoasphalt concrete of the type Bis among those types of the asphalt concrete which have the least values of the water saturation (2.5-2.8%). It is also should be mentioned that the water saturation of the nanoasphalt concrete is lower than the maximum allowed values for all the considered types of the asphalt concrete.

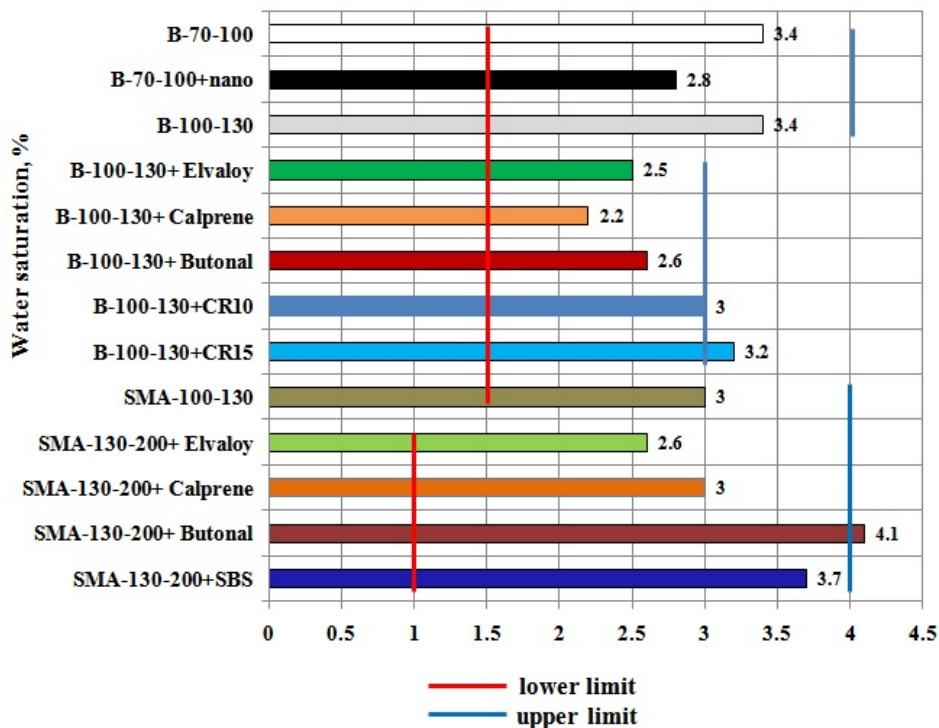


Figure 6 – Water saturation of the asphalt concretes

**Conclusion.** 1. The nanoasphalt concrete according to the considered standard indicators can substitute practically all the main types of the asphalt concretes used in a road construction in many countries of the world and in Kazakhstan.

2. The nanoasphalt concrete has the compression strength at the temperature of 0° Con average nearly 2 times higher than other types of the asphalt concretes, i.e. it has essentially high low temperature and fatigue strengths.

3. The nanoasphalt concrete proved to be the most shear resistant among the considered types of the asphalt concretes: its shear resistance is more for 25-204 % than for other asphalt concretes.

4. The nanoasphalt concrete is among the group of the asphalt concretes with the least water saturation values, i.e. after appropriate additional tests it may prove to be one of the most frost resistant types of the asphalt concretes.

**М. Ж. Жұрынов<sup>1</sup>, Б. Б. Телтаев<sup>2</sup>, А. А. Қалыбай<sup>2</sup>, С. О. Росси<sup>3</sup>, Е. Д. Әмірбаев<sup>2</sup>**

<sup>1</sup>«Д. В. Сокольский атындағы жанармай, катализ және электрохимия институты» АҚ, Алматы, Қазақстан;

<sup>2</sup>«Қазақстан жол ғылыми-зерттеу институты» АҚ, Алматы, Қазақстан;

<sup>3</sup>Калабрия университеті, Ренде, Италия

### **НАНОКӨМІРТЕК АСФАЛЬТБЕТОН МЕН БАСҚА АСФАЛЬТБЕТОНДАРДЫҢ СТАНДАРТТЫҚ КӨРСЕТКІШТЕРІН САЛЫСТЫРМАЛЫ ТАЛДАУ**

**Аннотация.** Жұмыста нанокөміртекті ұнтақты негізінде дайындалған Б типті наноасфальтбетон, модификатормен және онсыз Б типті асфальтбетон және шағыл тас-мастикалық асфальтбетондардың стандарттық көрсеткіштерін салыстырмалы талдау жасалған. Асфальтбетондарды дайындауға МЖБ 70/100, МЖБ 100/130 және МЖБ 130/200 маркалы битумдар пайдаланылды. МЖБ 70/100 және МЖБ 100/130 маркалы битумдар Павлодар мұнай-химия зауытында, ал МЖБ 130/200 маркалы битумы Қазақстан жол ғылыми-зерттеу институтында МЖБ 100/130 маркалы битум мен сол зауыттың гудроны араластыру негізінде алынды. Наноұнтақ (150-200 нм) «ОН-Олжа» ЖШС-нің (Ақмола облысы) «Сарадыр» кенорнының көмір жынысын механикалық диспергаторда (2-3 мм-ге дейін), аэродинамикалық диірменде (20 мкм-ге дейін) және айналымы электр-магниттік өрісті реакторда ұшатылы тізбектей ұнтақтау жолымен алынды.

Стандарттық көрсеткіштерін салыстыру үшін асфальтбетонның 13 түрі дайындалып, сынақтан өткізілді. Зертханада ҚР СТ 1218-2003 стандарты бойынша асфальтбетондардың стандарттық көрсеткіштері анықталды. Салыстырмалы талдау келесі 6 негізгі стандарттық көрсеткіштер бойынша жасалды: 50°С температурадағы сығу беріктігі; 20°С температурадағы сығу беріктігі; 0°С температурадағы сығу беріктігі; ығысуға тұрақтылық (50°С температурадағы ілігісу бойынша); 0°С температурадағы жарылуға тұрақтылық; суға қанығу.

Қарастырылған стандарттық көрсеткіштер бойынша наноасфальтбетонның әлемнің көптеген елдерінде және Қазақстанда жол құрылысында қолданылатын асфальтбетондардың барлық негізгі түрлерін алмастыра алатындығы анықталды. Оның ығысуға, төменгі температуралық және шаршау бұзылысына, циклдік тоңу мен еруге тұрақтылығы айтарлықтай жоғары.

**Түйін сөздер:** битумдар, көміртекті наноұнтақты, полимерлер, резеңке ұнтақты, асфальтбетондар, шағыл тас-мастикалық асфальтбетондар, стандарттық көрсеткіштер.

**М. Ж. Журинов<sup>1</sup>, Б. Б. Телтаев<sup>2</sup>, А. А. Қалыбай<sup>2</sup>, С. О. Росси<sup>3</sup>, Е. Д. Амирбаев<sup>2</sup>**

<sup>1</sup>«Институт топлива, катализа и электрохимии им. Д. В. Сокольского», Алматы, Казахстан;

<sup>2</sup>«Казахстанский дорожный научно-исследовательский институт», Алматы, Казахстан;

<sup>3</sup>Университет Калабрии, Ренде, Италия

### **СРАВНИТЕЛЬНЫЙ АНАЛИЗ СТАНДАРТНЫХ ПОКАЗАТЕЛЕЙ НАНОУГЛЕРОДНОГО АСФАЛЬТОБЕТОНА И ДРУГИХ АСФАЛЬТОБЕТОНОВ**

**Аннотация.** В настоящей работе выполнен сравнительный анализ стандартных показателей наноасфальтобетона типа Б, приготовленного с использованием наноуглеродного порошка и асфальтобетонов типа Б и щебеночно-мастичных асфальтобетонов (ЩМАС-20) с модификаторами и без них. Для приготовления асфальтобетонов использовались битумы марок БНД 70/100, БНД 100/130 и БНД 130/200. Битумы марок БНД 70/100 и БНД 100/130 были произведены Павлодарским нефтехимическим заводом, а битум марки БНД 130/200 был получен путем компаундирования битума марки БНД 100/130 и гудрона из того же завода в Казахском дорожном научно-исследовательском институте. Нанопорошок (150-200 нм) получен из

угольной породы месторождения «Сарыадыр» ТОО «Корпорация «ОН-Олга» (Акмолинская область) путем трехстадийного измельчения последовательно в механическом диспергаторе (до 2-3 мм), аэродинамической мельнице (до 20 мкм) и реакторе с вращающимся электромагнитным полем (150-200 нм).

Для сравнения стандартных показателей были приготовлены и испытаны 13 видов асфальтобетонов. В лаборатории по стандарту СТ РК 1218-2003 были определены стандартные показатели асфальтобетонов. Сравнительный анализ был выполнен по следующим 6 основным стандартным показателям: прочность при сжатии при температуре 50 °С; прочность при сжатии при температуре 20 °С; прочность при сжатии при температуре 0 °С; сдвигоустойчивость (по сцеплению при температуре 50 °С); трещиностойкость при температуре 0 °С; водонасыщение.

Установлено, что наноасфальтобетон по рассмотренным стандартным показателям может заменить практически все основные виды асфальтобетонов, применяемых в дорожном строительстве во многих странах мира и в Казахстане. Он имеет существенно высокую устойчивость к сдвигу, низкотемпературному и усталостному разрушению, циклическому замораживанию и оттаиванию.

**Ключевые слова:** битумы, углеродный нанопорошок, полимеры, резиновая крошка, асфальтобетоны, щебеночно-мастичные асфальтобетоны, стандартные показатели.

#### **Information about authors:**

Zhurinov M.Zh., Doctor of Chemical Sciences, Professor, Academician, President of NAS RK, JSC “D. V. Sokolskiy Institute of Fuel, Catalysis and Electrochemistry”, Almaty, Kazakhstan, nanrk.mzh@mail.ru; <https://orcid.org/0000-0001-5314-1219>

Teltayev B.B., Doctor of Technical Sciences, Professor, Corresponding member of NAS RK, President of JSC “Kazakhstan Highway Research Institute”, Almaty, Kazakhstan, bagdatbt@yahoo.com; <https://orcid.org/0000-0002-8463-9965>

Kalybay A.A., Doctor of Physical and Mathematical Sciences, Scientific Consultant of JSC “Kazakhstan Highway Research Institute”, Almaty city, Republic of Kazakhstan, Almaty, Kazakhstan; [ao\\_kazdornii@mail.ru](mailto:ao_kazdornii@mail.ru); <https://orcid.org/0000-0002-7646-8991>

Rossi C.O., Professor of Physical Chemistry, President of the spin-off “Chemical” at University of Calabria, Department of Chemistry and Chemical Technologies of University of Calabria, Rende, Italy; [cesare.oliviero@unical.it](mailto:cesare.oliviero@unical.it); <https://orcid.org/0000-0003-4406-7824>

Amirbayev Ye.D., Chief of Road Construction Materials Division of JSC “Kazakhstan Highway Research Institute”, Almaty, Kazakhstan; <https://orcid.org/0000-0001-8508-8803>

#### **REFERENCES**

- [1] Teltayev B.B., Kalybai A.A., Rossi C.O., Amirbayev E.D., Sivokhina E.S. Increasing of low temperature stability of bitumen with the use of nanocarbon powder. Proceedings of X International Symposium “The Physics and Chemistry of Carbon and Nanocarbon Materials”. September 12-14, 2018. Almaty (in Eng.).
- [2] Teltayev B.B., Kalybai A.A., Izmailova G.G., Rossi C.O., Amirbayev E.D., Sivokhina E.S. Nanostructured bitumen with nanocarbon // Eurasian Chemico-Technological Journal. 2019. 21. P. 303-310 (in Eng.).
- [3] Zhurinov M.Zh., Teltayev B.B., Kalybai A.A. Characteristics of road bitumen modified with nanocarbon nanopowder // News of the National Academy of Sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2019. 5 (437). P. 223-228 (in Eng.).
- [4] Zhurinov M.Zh., Teltayev B.B., Kalybai A.A. Effect of road bitumen modification with nanocarbon powder // Reports of the National Academy of Sciences of the Republic of Kazakhstan. 2020. 1 (329). P. 134-138 (in Eng.).
- [5] Kalybai A.A., Teltayev B.B., Abzhali A.K. Nanoenergetic materials and low carbon energetic on common resource and technological basis. Proceedings of X International Symposium “The Physics and Carbon and Nanoenergetic Materials”. September 12-14, 2018. Almaty (in Eng.).
- [6] Kalybai A.A., Teltayev B.B., Abzhali A.K. Nanoenergetic materials and low carbon energetic: regularities, technology and raw materials // News of the National Academy of Sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2019. 3 (435). P. 189-202 (in Eng.).
- [7] Zhurinov M.Zh., Kalybai A.A., Teltayev B.B. Characteristics and properties of physical and quantum fields of nanocarbon and their applications // News of the National Academy of Sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2019. 5 (437). P. 229-236 (in Eng.).
- [8] Zhurinov M.Zh., Teltayev B.B., Kalybai A.A., Amirbayev E.D. Asphalt concrete with nanocarbon bitumen // News of the National Academy of Sciences of the Republic of Kazakhstan. Series of Geology and Technical Sciences. 2020. 3 (441). P. 186-191 (in Eng.).
- [9] Teltayev B.B., Rossi C.O., Izmailova G.G., Amirbayev E.D. Effect of freeze-thaw cycles on mechanical characteristics of bitumens and stone mastic asphalts // Applied Sciences. 2019. 9. P. 1-18 (in Eng.).

**Publication Ethics and Publication Malpractice  
in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

[www:nauka-nanrk.kz](http://www.nauka-nanrk.kz)

**ISSN 2518-170X (Online), ISSN 2224-5278 (Print)**

<http://www.geolog-technical.kz/index.php/en/>

Редакторы *М. С. Ахметова, Д. С. Аленов, А. Ахметова*  
Верстка *Д. А. Абдрахимовой*

Подписано в печать 14.08.2020.  
Формат 70x881/8. Бумага офсетная. Печать – ризограф.  
11,1 п.л. Тираж 300. Заказ 4.