

ISSN 2518-170X (Online)
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫ

Satbayev University

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ
НАУК РЕСПУБЛИКИ
КАЗАХСТАН
Satbayev University

N E W S

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF
KAZAKHSTAN
Satbayev University

SERIES

OF GEOLOGY AND TECHNICAL SCIENCES

2 (458)

MARCH – APRIL 2023

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы «ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы» ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.

Бас редактор

ЖҰРЫНОВ Мұрат Жұрынұлы, химия ғылымдарының докторы, профессор, ҚР ҰҒА академигі, Қазақстан Республикасы Ұлттық Ғылым академиясының президенті, АҚ «Д.В. Сокольский атындағы отын, катализ және электрохимия институтының» бас директоры (Алматы, Қазақстан) **Н = 4**

Редакциялық алқа:

АБСАДЫКОВ Бахыт Нарикбайұлы, техника ғылымдарының докторы, профессор, ҚР ҰҒА жауапты хатшысы, А.Б. Бектұров атындағы химия ғылымдары институты (Алматы, Қазақстан) **Н = 5**

ӘБСАМЕТОВ Мәліс Құдысұлы (бас редактордың орынбасары), геология-минералогия ғылымдарының докторы, профессор, ҚР ҰҒА академигі, «У.М. Ахмедсафина атындағы гидрогеология және геоэкология институтының» директоры (Алматы, Қазақстан) **Н = 2**

ЖОЛТАЕВ Герой Жолтайұлы (бас редактордың орынбасары), геология-минералогия ғылымдарының докторы, профессор, Қ.И. Сатпаев атындағы геология ғылымдары институтының директоры (Алматы, Қазақстан) **Н=2**

СНОУ Дэниел, Ph.D, қауымдастырылған профессор, Небраска университетінің Су ғылымдары зертханасының директоры (Небраска штаты, АҚШ) **Н = 32**

ЗЕЛЬТМАН Реймар, Ph.D, табиғи тарих мұражайының Жер туралы ғылымдар бөлімінде петрология және пайдалы қазбалар кен орындары саласындағы зерттеулердің жетекшісі (Лондон, Англия) **Н = 37**

ПАНФИЛОВ Михаил Борисович, техника ғылымдарының докторы, Нанси университетінің профессоры (Нанси, Франция) **Н=15**

ШЕН Пин, Ph.D, Қытай геологиялық қоғамының тау геологиясы комитеті директорының орынбасары, Американдық экономикалық геологтар қауымдастығының мүшесі (Пекин, Қытай) **Н = 25**

ФИШЕР Аксель, Ph.D, Дрезден техникалық университетінің қауымдастырылған профессоры (Дрезден, Берлин) **Н = 6**

КОНТОРОВИЧ Алексей Эмильевич, геология-минералогия ғылымдарының докторы, профессор, РФА академигі, А.А. Трофимука атындағы мұнай-газ геологиясы және геофизика институты (Новосибирск, Ресей) **Н = 19**

АГАБЕКОВ Владимир Енокович, химия ғылымдарының докторы, Беларусь ҰҒА академигі, Жаңа материалдар химиясы институтының құрметті директоры (Минск, Беларусь) **Н = 13**

КАТАЛИН Стефан, Ph.D, Дрезден техникалық университетінің қауымдастырылған профессоры (Дрезден, Берлин) **Н = 20**

СЕЙТМҰРАТОВА Элеонора Юсуповна, геология-минералогия ғылымдарының докторы, профессор, ҚР ҰҒА корреспондент-мүшесі, Қ.И. Сатпаев атындағы Геология ғылымдары институты зертханасының меңгерушісі (Алматы, Қазақстан) **Н=11**

САҒЫНТАЕВ Жанай, Ph.D, қауымдастырылған профессор, Назарбаев университеті (Нұр-Сұлтан, Қазақстан) **Н = 11**

ФРАТТИНИ Паоло, Ph.D, Бикокк Милан университеті қауымдастырылған профессоры (Милан, Италия) **Н = 28**

«ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Меншіктеуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан Республикасының Ақпарат және қоғамдық даму министрлігінің Ақпарат комитетінде 29.07.2020 ж. берілген № **KZ39VPY00025420** мерзімдік басылым тіркеуіне қойылу туралы куәлік. Тақырыптық бағыты: *геология, мұнай және газды өңдеудің химиялық технологиялары, мұнай химиясы, металдарды алу және олардың қосындыларының технологиясы.*

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекен-жайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., тел.: 272-13-19 <http://www.geolog-technical.kz/index.php/en/>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2023

Типографияның мекен-жайы: «Аруна» ЖК, Алматы қ., Мұратбаев көш., 75.

Главный редактор

ЖУРИНОВ Мурат Журинович, доктор химических наук, профессор, академик НАН РК, президент Национальной академии наук Республики Казахстан, генеральный директор АО «Институт топлива, катализа и электрохимии им. Д.В. Сокольского» (Алматы, Казахстан) **Н = 4**

Редакционная коллегия:

АБСАДЫКОВ Бахыт Нарикбаевич, доктор технических наук, профессор, ответственный секретарь НАН РК, Институт химических наук им. А.Б. Бектурова (Алматы, Казахстан) **Н = 5**

АБСАМЕТОВ Малис Кудысович, (заместитель главного редактора), доктор геолого-минералогических наук, профессор, академик НАН РК, директор Института гидрогеологии и геоэкологии им. У.М. Ахмедсафина (Алматы, Казахстан) **Н = 2**

ЖОЛТАЕВ Герой Жолтаевич, (заместитель главного редактора), доктор геолого-минералогических наук, профессор, директор Института геологических наук им. К.И. Сатпаева (Алматы, Казахстан) **Н=2**

СНОУ Дэниел, Ph.D, ассоциированный профессор, директор Лаборатории водных наук университета Небраски (штат Небраска, США) **Н = 32**

ЗЕЛЬТМАН Реймар, Ph.D, руководитель исследований в области петрологии и месторождений полезных ископаемых в Отделе наук о Земле Музея естественной истории (Лондон, Англия) **Н = 37**

ПАНФИЛОВ Михаил Борисович, доктор технических наук, профессор Университета Нанси (Нанси, Франция) **Н=15**

ШЕН Пин, Ph.D, заместитель директора Комитета по горной геологии Китайского геологического общества, член Американской ассоциации экономических геологов (Пекин, Китай) **Н = 25**

ФИШЕР Аксель, ассоциированный профессор, Ph.D, технический университет Дрезден (Дрезден, Берлин) **Н = 6**

КОНТОРОВИЧ Алексей Эмильевич, доктор геолого-минералогических наук, профессор, академик РАН, Институт нефтегазовой геологии и геофизики им. А.А. Трофимука СО РАН (Новосибирск, Россия) **Н = 19**

АГАБЕКОВ Владимир Енокович, доктор химических наук, академик НАН Беларуси, почетный директор Института химии новых материалов (Минск, Беларусь) **Н = 13**

КАТАЛИН Стефан, Ph.D, ассоциированный профессор, Технический университет (Дрезден, Берлин) **Н = 20**

СЕЙТМУРАТОВА Элеонора Юсуповна, доктор геолого-минералогических наук, профессор, член-корреспондент НАН РК, заведующая лабораторией Института геологических наук им. К.И. Сатпаева (Алматы, Казахстан) **Н=11**

САГИНТАЕВ Жанай, Ph.D, ассоциированный профессор, Назарбаев университет (Нурсултан, Казахстан) **Н = 11**

ФРАТТИНИ Паоло, Ph.D, ассоциированный профессор, Миланский университет Бикокк (Милан, Италия) **Н = 28**

«Известия НАН РК. Серия геологии и технических наук».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан» (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации Министерства информации и общественного развития Республики Казахстан № KZ39VPY00025420, выданное 29.07.2020 г.

Тематическая направленность: *геология, химические технологии переработки нефти и газа, нефтехимия, технологии извлечения металлов и их соединений.*

Периодичность: 6 раз в год.

Тираж: 300 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, оф. 219, тел.: 272-13-19

<http://www.geolog-technical.kz/index.php/en/>

© Национальная академия наук Республики Казахстан, 2023

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75.

Editorial chief

ZHURINOV Murat Zhurinovich, doctor of chemistry, professor, academician of NAS RK, president of the National Academy of Sciences of the Republic of Kazakhstan, general director of JSC “Institute of fuel, catalysis and electrochemistry named after D.V. Sokolsky» (Almaty, Kazakhstan) **H = 4**

Editorial board:

ABSADYKOV Bakhyt Narikbaevich, doctor of technical sciences, professor, executive secretary of NAS RK, Bekturov Institute of chemical sciences (Almaty, Kazakhstan) **H = 5**

ABSAMETOV Malis Kudysovich, (deputy editor-in-chief), doctor of geological and mineralogical sciences, professor, academician of NAS RK, director of the Akhmedsafin Institute of hydrogeology and hydrophysics (Almaty, Kazakhstan) **H=2**

ZHOLTAEV Geroy Zholtaevich, (deputy editor-in-chief), doctor of geological and mineralogical sciences, professor, director of the institute of geological sciences named after K.I. Satpayev (Almaty, Kazakhstan) **H=2**

SNOW Daniel, Ph.D, associate professor, director of the laboratory of water sciences, Nebraska University (Nebraska, USA) **H = 32**

ZELTMAN Reyman, Ph.D, head of research department in petrology and mineral deposits in the Earth sciences section of the museum of natural history (London, England) **H = 37**

PANFILOV Mikhail Borisovich, doctor of technical sciences, professor at the Nancy University (Nancy, France) **H=15**

SHEN Ping, Ph.D, deputy director of the Committee for Mining geology of the China geological Society, Fellow of the American association of economic geologists (Beijing, China) **H = 25**

FISCHER Axel, Ph.D, associate professor, Dresden University of technology (Dresden, Germany) **H = 6**

KONTOROVICH Aleksey Emilievich, doctor of geological and mineralogical sciences, professor, academician of RAS, Trofimuk Institute of petroleum geology and geophysics SB RAS (Novosibirsk, Russia) **H = 19**

AGABEKOV Vladimir Enokovich, doctor of chemistry, academician of NAS of Belarus, honorary director of the Institute of chemistry of new materials (Minsk, Belarus) **H = 13**

KATALIN Stephan, Ph.D, associate professor, Technical university (Dresden, Berlin) **H = 20**

SEITMURATOVA Eleonora Yusupovna, doctor of geological and mineralogical sciences, professor, corresponding member of NAS RK, head of the laboratory of the Institute of geological sciences named after K.I. Satpayev (Almaty, Kazakhstan) **H=11**

SAGINTAYEV Zhanay, Ph.D, associate professor, Nazarbayev University (Nursultan, Kazakhstan) **H = 11**

FRATTINI Paolo, Ph.D, associate professor, university of Milano-Bicocca (Milan, Italy) **H = 28**

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Owner: RPA «National Academy of Sciences of the Republic of Kazakhstan» (Almaty).

The certificate of registration of a periodical printed publication in the Committee of information of the Ministry of Information and Social Development of the Republic of Kazakhstan **No. KZ39VPY00025420**, issued 29.07.2020.

Thematic scope: *geology, chemical technologies for oil and gas processing, petrochemistry, technologies for extracting metals and their connections.*

Periodicity: 6 times a year.

Circulation: 300 copies.

Editorial address: 28, Shevchenko str., of. 219, Almaty, 050010, tel. 272-13-19

<http://www.geolog-technical.kz/index.php/en/>

© National Academy of Sciences of the Republic of Kazakhstan, 2023

Address of printing house: ST «Aruna», 75, Muratbayev str, Almaty.

NEWS of the National Academy of Sciences of the Republic of Kazakhstan
SERIES OF GEOLOGY AND TECHNICAL SCIENCES
ISSN 2224-5278
Volume 2, Number 458 (2023), 188–196
<https://doi.org/10.32014/2023.2518-170X.294>
UDC 669.333.7: 669.243.72

© V.M. Shevko¹, A.M. Nurpeisova^{1*}, D.K. Aitkylov², A.A. Joldassov³, 2023

¹M. Auezov South Kazakhstan university, Shymkent, Kazakhstan;

²National Center on Complex Processing of Mineral Raw Materials of the Republic of Kazakhstan, Almaty, Kazakhstan;

³Satbayev University, Almaty, Kazakhstan.

E-mail: aigerim_nurpeis@mail.ru

THERMODYNAMIC PREDICTION AND EXPERIMENTAL PRODUCTION OF SILICON ALLOYS FROM TAILINGS LEACHING OF OXIDIZED COPPER ORE ALMALY

Nurpeisova Aigerim Muratbaevna — Master of Technical Sciences, doctoral student of the department of Metallurgy of M. Auezov University of South Kazakhstan. Shymkent, Kazakhstan

E-mail: aigerim_nurpeis@mail.ru, <https://orcid.org/0000-0001-8494-7872>;

Shevko Viktor Mikhailovich — Doctor of Technical Sciences. Professor. Head of the Department of Metallurgy of M. Auezov South Kazakhstan University. Shymkent, Kazakhstan

E-mail: shevkovm@mail.ru, <https://orcid.org/0000-0002-9814-6248>;

Aitkulov Dosmurat Kyzylbievich — Doctor of Technical Sciences. Professor. Director of the National Research Center for Integrated Processing of Mineral Raw Materials of the Republic of Kazakhstan, Almaty, Kazakhstan

E-mail: aitkulov_dk@mail.ru, <https://orcid.org/0000-0003-2571-6710>;

Joldassov Aidos Abdisalimovich — Master of technical science, Satbayev University, Almaty, Kazakhstan

E-mail: jaydos@mail.ru, <https://orcid.org/0000-0002-4740-2352>.

Abstract. The article presents the results of studies on the production of silicon-containing ferroalloys from the tailings of sulfuric acid leaching of oxidized copper ore from the Almalay deposit. The studies were carried out by the method of thermodynamic modeling using the HSC — 6.0 rotatable second-order planning complex (Box – Hunter plan) and electric charge melting in an arc single-electrode furnace. The influence of temperature, carbon, and charge composition on the production of siliceous alloys was determined. It was found that under equilibrium conditions from the tailings in the temperature range 1903–in the presence of 52–66 % carbon and 24 % iron, it is possible to form ferrosilicoaluminium grade FeSi45A10 at 1753–1875°C and 34–66% carbon ferrosilium grade FeSi45, and in the temperature range 1796–1950°C, 34–66 % carbon Fe-Si-Al ligature containing 2,0–7,5 Al and 45,9–47,5 % Si. During electric melting of charges containing 52–54 % tailings, 25–28 % coke and 20–21% steel chips of ferrosilium grade FeSi45 (41,3 % Si and 1,3 % Al) and ferrosilicoaluminium grade FeSi45A10 (43,4 % Si and 7,4 % Al) with extractions to the alloy up to 79,8 % Si and 50,8 % Al.

Keywords: oxidized copper ore, leaching tailings, thermodynamic prediction, electric melting, ferrosilicon, ferrosilicoaluminium, Fe-Si-Al ligature

© В.М. Шевко¹, А.М. Нурпеисова^{1*}, Д.К. Айткулов², А.А. Жолдасов³, 2023

¹М. Әуезов атындағы Оңтүстік Қазақстан университеті, Шымкент, Қазақстан;

²Қазақстан Республикасының минералдық шикізатты кешенді қайта өңдеу жөніндегі ұлттық орталығы, Алматы, Қазақстан;

³Сәтбаев университеті, Алматы, Қазақстан.

E-mail: aigerim_nurpeis@mail.ru

АЛМАЛЫ ТОТЫҚҚАН МЫС КЕНІН ШАЙМАЛАУ ҚАЛДЫҚТАРЫНАН КРЕМНИЙЛІ ҚОРЫТПАЛАРДЫ ТӘЖІРИБЕЛІ АЛУ ЖӘНЕ ТЕРМОДИНАМИКАЛЫҚ БОЛЖАУ

Нурпейсова Айгерім Муратбаевна — Техника ғылымдарының магистрі, М. Әуезов атындағы Оңтүстік Қазақстан университетінің Metallургия кафедрасының докторанты. Шымкент, Қазақстан

E-mail: aigerim_nurpeis@mail.ru, <https://orcid.org/0000-0001-8494-7872>;

Шевко Виктор Михайлович — Техника ғылымдарының докторы, профессор, Оңтүстік Қазақстан университетінің Metallургия кафедрасының меңгерушісі. М. Әуезов. Шымкент, Қазақстан

E-mail: shevkovm@mail.ru, <https://orcid.org/0000-0002-9814-6248>;

Айткулов Досмурат Қызылбаевич — Техника ғылымдарының докторы, профессор, Қазақстан Республикасы Минералдық шикізатты кешенді қайта өңдеудің Ұлттық зерттеу орталығының директоры, Алматы, Қазақстан

E-mail: aitkulov_dk@mail.ru, <https://orcid.org/0000-0003-2571-6710>;

Жолдасов Айдос Абдисалимович — Техника ғылымдарының магистрі. Сәтбаев университеті, Алматы, Қазақстан

E-mail: jaydos@mail.ru, <https://orcid.org/0000-0002-4740-2352>.

Аннотация. Мақалада Алмалы кен орнының күкірт қышқылды сілтісіздендіру қалдықтарынан тотыққан мыс кенін алу жөніндегі зерттеулердің нәтижелері келтіріледі. Зерттеулер HSC – 6,0 екінші ретті рототабельді жоспарлау кешенін (бокс – Хантер жоспары) және доғалы бір электродты пештегі зарядты электрмен балқыту арқылы термодинамикалық модельдеу әдісімен жүргізілді. Кремний қорытпаларын алуға температураның, көміртектің, зарядтың құрамының әсері анықталды. Тепе-теңдік жағдайында 1903-1950⁰C температура диапазонындағы қалдықтардан 52–66 % көміртегі және 24 % темір болған кезде FC45A10 маркалы ферросиликоалюминий 1753–1875⁰C және 34–66 % FC45 маркалы көміртегі ферросилицийінің пайда болуы мүмкін екендігі, ал температура аймағында 1796-1950⁰C, 34–66 % Fe-Si-Al көміртегі құрамы бар лигатура 2.0–7.5 Al және 45.9–47.5 % Si болатыны анықталды. Құрамында 52–54 % қалдықтар, 25–28 % кокс және 20–21 % болат жаңқалары FC45 (41,3 % Si және 1,3% Al) маркалы ферросилиций және FC45A10 (43,4 % Si және 7,4 % Al) маркалы ферросиликоалюминий бар шикіқұрамды электрмен балқыту кезінде қорытпаға 79,8 % Si және 50,8 % Al дейін бөлінеді.

Түйін сөздер: тотыққан кен, термодинамикалық моделдеу, электрлі балқыту, ферросилиций, ферросиликоалюминий

© В.М. Шевко¹, А.М. Нурпейсова^{1*}, Д.К. Айтқұлов², А.А. Жолдасов³, 2023

¹Южно-Казахстанский университет имени М. Ауэзова, Шымкент, Казахстан;

²Национальный центр по комплексной переработке минерального сырья Республики Казахстан, Алматы, Казахстан;

³Сатбаев университеті, Алматы, Казахстан.

E-mail: aigerim_nurpeis@mail.ru

ТЕРМОДИНАМИЧЕСКОЕ ПРОГНОЗИРОВАНИЕ И ЭКСПЕРИМЕНТАЛЬНОЕ ПОЛУЧЕНИЕ КРЕМНИЕВЫХ СПЛАВОВ ИЗ ХВОСТОВ ВЫЩЕЛАЧИВАНИЯ ОКИСЛЕННОЙ МЕДНОЙ РУДЫ АЛМАЛЫ

Нурпейсова Айгерім Муратбаевна — магистр технических наук, докторант кафедры металлургии Южно-Казахстанского университета имени М. Ауэзова. Шымкент, Казахстан

E-mail address: aigerim_nurpeis@mail.ru, <https://orcid.org/0000-0001-8494-7872>;

Шевко Виктор Михайлович — доктор технических наук, профессор, заведующий кафедрой металлургии Южно-Казахстанского университета им. М. Ауэзова. Шымкент, Казахстан

E-mail address: shevkovm@mail.ru, <https://orcid.org/0000-0002-9814-6248>;

Айтқұлов Досмұрат Қызылбаевич — доктор технических наук, профессор, директор Национального исследовательского центра комплексной переработки минерального сырья Республики Казахстан, Алматы, Казахстан

E-mail address: aitkulov_dk@mail.ru, <https://orcid.org/0000-0003-2571-6710>;

Жолдасов Айдос Абдисалимович — Магистр технических наук, университет Сатбаева, Алматы, Казахстан

Email address: jaydos@mail.ru, <https://orcid.org/0000-0002-4740-2352>.

Аннотация. В статье приводятся результаты исследований по получению кремнийсодержащих ферросплавов из хвостов серноокислотного выщелачивания окисленной медной руды месторождения Алмалы. Исследования проводились методом термодинамического моделирования с использованием комплекса HSC — 6,0 рототабельного планирования второго порядка (план Бокса – Хантера) и электроплавкой шихта в дуговой одноэлектродной печи. Определялось влияние температуры, углерода, состава шихты на получение кремнистых сплавов. Было найдено, что в равновесных условиях из хвостов в температурном интервале 1903–1950⁰C в присутствии 52–66 % углерода и 24 % железа возможно образование ферросиликоалюминия марки FC45A10 при 1753–1875⁰C и 34–66 % углерода ферросилиций марки FC45, а в температурном области 1796–1950⁰C, 34–66 % углерода Fe-Si-Al лигатура с содержанием 2,0–7,5 Al и 45,9–47,5 % Si. При электроплавке шихт, содержащих 52–54 % хвостов, 25–28 % кокса и 20–21 % стальной стружки, получен ферросилиций марки FC45 (41,3 % Si и 1,3% Al) и ферросиликоалюминий марки FC45A10 (43,4 % Si и 7,4 % Al) при извлечении в сплав до 79,8 % Si и 50,8 % Al.

Ключевые слова: окисленная медная руда, хвосты выщелачивания, термодинамическое прогнозирование, электроплавка, ферросилиций, ферросиликоалюминий, Fe-Si-Al лигатура

Introduction

According to the National Center for Integrated Processing of Mineral Raw Materials at the end of the last century, over the past 20–25 years, the share of hard-to-enrich ores has increased by ≈ 3 times, accounting for 45 % of the total mass of enriched mineral raw materials (Poly'vyany'j al 1995: 18). This category includes oxidized and mixed copper ores, whose reserves in Kazakhstan amount to at least 1 billion tons (Zharmenov et al., 2019: 630). For the processing of such a category of ores, their preliminary sulfidation with various substances is proposed (Mitrofanov et al., 1984: 216; Bekturganov et al., 1989: 211; Shevko et al., 2014: 287; Zharmenov et al., 2015: 1; Ory'ngozhin et al., 2020: 4) and then (after sulfidation) use for flotation enrichment. A combined chloride-electrothermal method of processing oxidized and mixed ores to produce ferrosilicon and cathode copper is described in the literature (Kushakova et al., 2010: 31; Robinson et al., 2003: 24). In hydrometallurgy technology, leaching processes are characterized by a significant variety of raw materials (Zharmenov et al., 2015: 1; Ory'ngozhin et al., 2020: 4; Kushakova et al., 2010: 31). Heap leaching, in particular, is used to extract copper from oxidized and mixed ores (Kushakova et al., 2010: 31; Robinson et al., 2003: 24). However, the most widespread technology for this category of ores is "Heap leaching –SX-EW" (Robinson et al., 2003: 24; ProcessSX/EW//MiningMag 1994: 256; Jenkins et al., Cobre'99 conference, Jenkins 1964: 1094). According to the data of the International Copper Study Group (International Copper Study Group ICSG), the share of commercial copper obtained by this method in 2016 amounted to 16 % of the total world production (Zharmenov et al., 2019: 630). In Kazakhstan, the "Heap leaching –SX-EW" technology has been implemented since 2008 at the Konurad, Almaly, Aktogay, Ayak-Kojan and a number of other fields (Zharmenov et al., 2019: 630), Kushakova et al., 2013: 343). In 2019, this technology produced ≈ 50 thousand tons of copper in Kazakhstan (≈ 12 % of the total amount of copper produced) (Zharmenov et al., 2019: 630). Despite the rather high extraction of copper from the ore into a copper solution (80–82 %), this method involves the extraction of only copper from the ore. At the same time, the non-metallic component (98–98.5 % of the ore mass) is not used. Therefore, the degree of integrated use of the raw materials of the "Heap leaching –SX-EW" technology is low.


This paper presents the results of studies on the production of ferroalloys from the leaching tailings (TL) of oxidized ores of the Almaly deposit, which contained mass. %: 73,4 % SiO_2 , 16,3 % Al_2O_3 , 3,1 % K_2O , 2,4 % CaO , 1,1 % MgO , 21 % Fe_2O_3 , 0,07 % Cu . Coke mass content, %: 86,4 % C , 4,3 % SiO_2 , 1,3 % CaO , 0,5 % MgO , 1,9 % Al_2O_3 , 2,0 % Fe_2O_3 , 0,7 % S , 1,0 % H_2O , 1,2 % other, and steel chips 98,7 % Fe , 0,2 % C , 1,1 % other (Si, Mn, Al)

Materials and basic methods

The research was carried out by the method of thermodynamic modeling using the HSC — 6.0 software package based on the Gibbs minimum energy principle (Roin, 2022). Based on the algorithm developed at M. Auezov SKU, we calculated the equilibrium degree of the distribution of elements and the concentration of elements in the alloy (Shevko et al., 2019: 1501). The method of thermodynamic modeling was combined with rotatable planning of the second plan (the Box-Hunter plan) (Axnazarova et al., 1985: 327) with the derivation of regression equations (Inkov et al., 2003) by constructing volumetric and planar images of the behavior of Si, Al and metals in an alloy (Ochkov al., 2009: 512).

Electric melting of TL was carried out on the installation shown in Figure 1. The installation consisted of a single-electrode single-phase electric furnace, a furnace transformer TDJF-1002 with adjustable power, a short network and current and voltage monitoring devices.

III

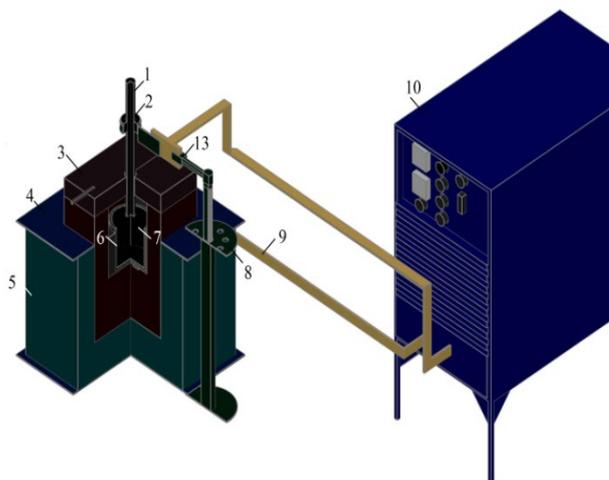

I-Installation sketch, II-photo of an electric furnace

1 - the electrode; 2- clip; 3-cap; 4 - lining; 5 - furnace casing; 6 - coke; 7 - crucible; 8-the mechanism of moving the electrode, 9 - the tire; 10- transformer


Figure 1- installation for electric melting of copper oxide ore leaching tails

The lining of the electric furnace is chromomagnesite, the base is carbon graphite. Graphite electrode with a diameter of –7 cm. The melting was carried out in a graphite crucible (with an internal diameter of 9 cm and a height of 2 cm). The crucible was installed on a graphite plate. The space between the crucible and the lining was filled with graphite carbon-graphite dust. The lid of the furnace, made of refractory material, was sliding. The vertical movement of the electrode was carried out by a mechanical screw mechanism. The maximum movement of the electrode was 50 cm. The short network-the section from the furnace to the transformer, was made of aluminum tires (1.5x4.5cm). The lower tire was connected to the carbon-graphite block using three copper studs.the upper busbar was connected to the graphite electrode using a flexible copper cable. Rated power of the furnace transformer to 56. The voltage and current on the low side were controlled by a voltmeter and an ammeter of the brands respectively TENGGEN 42L6 GB/T7676–1998, CHNT 4226 (China) (accuracy class 1.5) Before melting, the leaching tails were granulated with 2–3 % bentonite clay, dried at 150–160 °C, and then fired at 600–700 °C. The fired pellets had a diameter of 1–1.5 cm. Coke was also crushed to a fraction of 1–1.5 cm. The size of the steel chips did not exceed 1 cm. The furnace was heated for 3–3.5 hours by an arc at a current of 400–500A and a voltage of 40–50 V. Then the first batch of charge was loaded (600–700 g). It was melted for 5–7 minutes. After that, 2 more portions of the charge were loaded with an interval of 6–8 minutes. The total duration of the melting was 35–45 minutes. During melting, the current strength was 500–600 A. the voltage is 20–30V. After melting, the crucible was cooled in the furnace for 3–4 hours, removed from the furnace, cooled for another 3–3.5 hours in the air. Then the crucible was broken. The contents of the crucible were sorted into alloy and residue.

The elemental composition of the alloy was determined by SEM analysis using a scanning electron microscope of the brand JSM-6490LV (Japan). The degree of extraction of silicon and aluminum in the alloy was determined by the ratio of the mass of the metal in the alloy to the mass of the metal in the charge.

Results

Figure 2 shows the effect of temperature on the equilibrium quantitative (kg) distribution of silicon and aluminum in the TL (100 kg) Fe (24 kg) – C (34–66 kg).

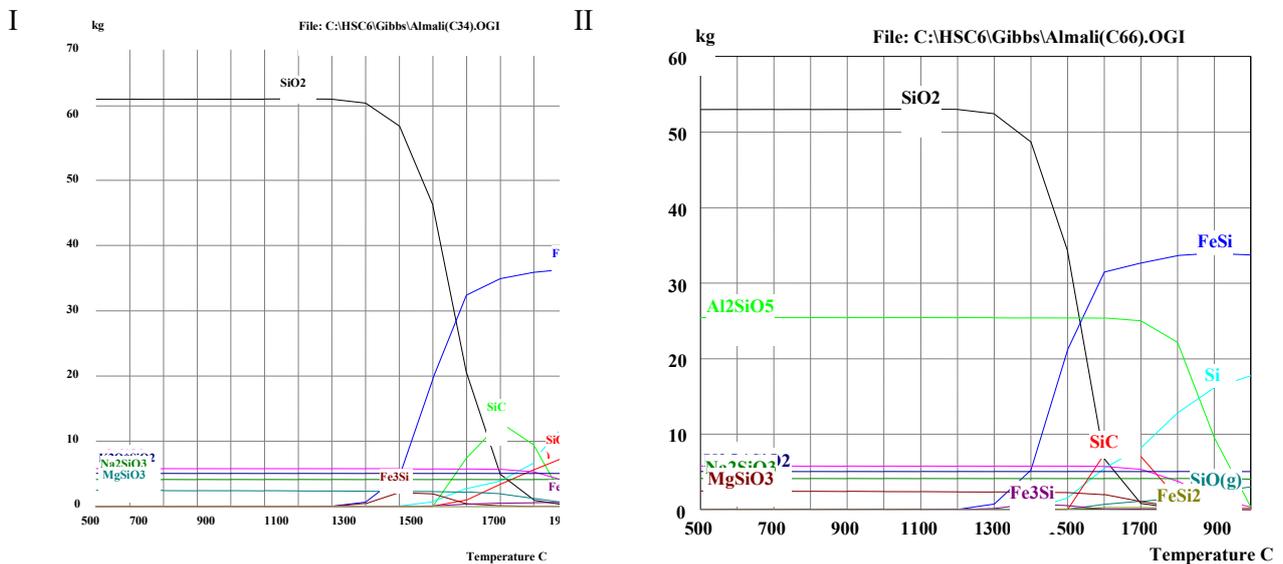

1 – 34 % C, 2 – 66 % C

Figure 2 - influence of temperature and carbon on the equilibrium (kg) quantitative distribution of silicon-containing substances

It can be seen that in the technological field 1200-2000 °C the main products of the interaction of SiO₂ tails with carbon are FeSi, Fe₃Si₂, Si, SiC and SiO_g. Increasing the amount of carbon does not lead to a significant change in the formation of FeSi (Table 1), but increases the formation of silicon and reduces the formation of SiC and SiO_g.

Table 1 – Influence of temperature and carbon on the quantitative (kg) distribution of silicon-containing substances

Substance	Carbon,%	Temperature°C
-----------	----------	---------------

		1300	1400	1500	1600	1700	1800	1900	2000
FeSi	34	0,67	4,62	19,61	32,43	34,94	35,90	36,38	36,06
	66	0,75	5,24	21,19	31,46	32,66	33,65	33,96	33,76
Si	34	0,01	0,08	0,74	2,75	3,90	6,66	12,55	12,38
	66	0,01	0,17	1,56	5,47	8,21	12,85	16,20	17,76
SiC	34	0,00	0,00	0,00	7,41	12,84	9,41	0,21	0,00
	66	0,00	0,00	0,00	7,34	7,05	1,49	0,00	0,00
SiOg	34	0,00	0,00	0,07	1,02	3,42	5,66	7,73	9,53
	66	0,00	0,00	0,08	0,71	1,12	1,61	2,37	3,05
Fe ₃ Si	34	0,47	2,15	1,95	0,43	0,13	0,01	0,00	0,00
	66	0,16	0,74	0,55	0,10	0,02	0,00	0,00	0,00

A noticeable formation of FeSi is noted at T > 1300°C, Si → 1400°C, SiO_g and SiC > 1500°C. Aluminum in the system under consideration begins to recover at a temperature of more than 1700°C. With an increase in carbon, the amount of aluminum formed increases markedly (Table 2)

Table 2 – Influence of temperature and carbon on the quantitative (kg.0) formation of aluminum

Carbon, %	Temperature °C			
	1700	1800	1900	2000
34	0,02	0,17	1,23	3,75
66	0,02	0,41	3,59	7,80

Further studies were carried out by the method of rotatable planning of the second order (the Box-Hunter plan). The temperature and the amount of carbon (Carbon, % of the weight of the enrichment tailings) were used as independent factors. Optimization parameters are the degree of extraction of silicon and aluminum into the alloy α_{Si(alloy)} and α_{Al(alloy)}, % concentration of silicon and aluminum in the alloy — C_{Si(alloy)} and C_{Al(alloy)}. Table 3 shows the plan and results of the study.

Table 3 – Plan of research and their results for obtaining ferroalloy from copper ore leaching tailings

№	Variables				Technological parameters			
	Coded view		Natural form		α _{Si(alloy)} , %	α _{Al(alloy)} , %	C _{Si(alloy)} , %	C _{Al(alloy)} , %
	X ₁	X ₂	T, °C	carbon, %				
1	+	+	1921	61,3	88,0	48,3	47,5	7,5
2	+	-	1921	38,7	74,8	26,2	46,3	4,3
3	-	+	1779	61,3	67,6	3,9	44,6	0,4
4	-	-	1779	38,7	56,1	2,0	40,8	0,3
5	1,414	0	1950	50	84,2	52,3	46,4	7,2
6	-1,414	0	1750	50	51,8	3,2	40,8	0,2
7	0	1,414	1850	66	79,1	22,4	48,0	4,5
8	0	-1,414	1850	34	64,8	5,5	43,9	1,3
9	0	0	1850	50	70,0	11,9	46,6	1,7
10	0	0	1850	50	69,7	12,1	47,8	1,6
11	0	0	1850	50	69,5	12,3	46,8	1,9
12	0	0	1850	50	71,1	12,1	47,5	1,8
13	0	0	1850	50	71,3	12,5	47,9	1,5

Based on Table 3, the following adequate regression equations are obtained:

$$\alpha_{Si(alloy)} = -694,91 - 0,7T - 1,458C + 1,5 \cdot 10^{-5} \cdot T^2 + 1,03 \cdot 10^{-2} C^2 + 4,98 \cdot 10^{-5} \cdot T \cdot C \quad (1)$$

$$\alpha_{Al(alloy)} = +5248,03 - 5,6 \cdot T - 11,69 \cdot C + 1,49 \cdot 10^{-4} \cdot T^2 + 5,1 \cdot 10^{-3} \cdot C^2 + 6,3 \cdot T \cdot C \quad (2)$$

$$C_{Si(alloy)} = -1358,05 + 1,43 \cdot T + 2,14 \cdot C - 3,6 \cdot 10^{-4} \cdot T^2 - 5,3 \cdot 10^{-3} \cdot C^2 - 8,1 \cdot 10^{-4} \cdot T \cdot C \quad (3)$$

$$C_{Al(alloy)} = 668,069 - 0,702 \cdot T - 2,1 \cdot C + 1,8 \cdot 10^{-4} \cdot T^2 + 4,35 \cdot 10^{-3} \cdot C^2 + 9,49 \cdot 10^{-4} \cdot T \cdot C \quad (4)$$

The adequacy of the equations was determined by the Fisher criterion (F), the values of which are shown in Table (4)

Table 4 – Values of the Fisher criterion

Fisher's Criterion	Equations			
	α _{Si(alloy)} = f(T, c)	α _{Al(alloy)} = f(T, c)	C _{Si(alloy)} = f(T, c)	C _{Al(alloy)} = f(T, c)
Calculated	6,476	4,856	1,054	6,029
Tabular	6,59	6,59	6,59	6,59

For all equations, the F_{crit} > F_{tabular} is the calculation criterion. Hence all the equations are adequate.


Discussion

Volumetric and planar images of the dependences of technological parameters on the temperature of the amount of carbon are shown in Figure 3. It can be seen that a high degree of silicon extraction into the alloy ($\geq 80\%$) is noted at $T > 1850\text{ }^\circ\text{C}$. More than 50% of aluminum is extracted into the alloy only at $1915\text{ }^\circ\text{C}$. The concentration of silicon in the alloy varies from 37% (at $1750\text{ }^\circ\text{C}$) to 48% ($T = 1850\text{--}1905\text{ }^\circ\text{C}$), aluminum from 5% (at $1865\text{ }^\circ\text{C}$) to 11% (at $1950\text{ }^\circ\text{C}$)

Figure 4 shows the combined information on the effect of temperature and carbon on the technological parameters of obtaining ferroalloy from the leaching tailings of oxidized copper ores.

When constructing the diagram, it was assumed that the minimum degree of transition of silicon to the alloy should be more than 65%, the concentration of Si in ferrosilicon – 41–47%, the concentration of aluminum in ferrosilicoaluminum – $\geq 7.5\%$, and silicon in it $\geq 47.5\%$. Figure 4 shows that in the temperature range of $1750\text{--}1950\text{ }^\circ\text{C}$ and 34–66% carbon, ferrosilicon grade FS45, ferrosilicoaluminum and Fe-Si-Al ligature can be formed from the leaching tails. Moreover, the maximum extraction of silicon into the alloy is 95.0% and aluminum 69.8% (point e). The maximum silicon content in the alloy – 48.6% is noted at $1878\text{ }^\circ\text{C}$ and 59.3% carbon (point M), and aluminum – 11.0%, – at $1950\text{ }^\circ\text{C}$ and 66% carbon (point e).

Tables 5 and 6 provide information on the technological parameters for the formation of ferroalloys of various types.

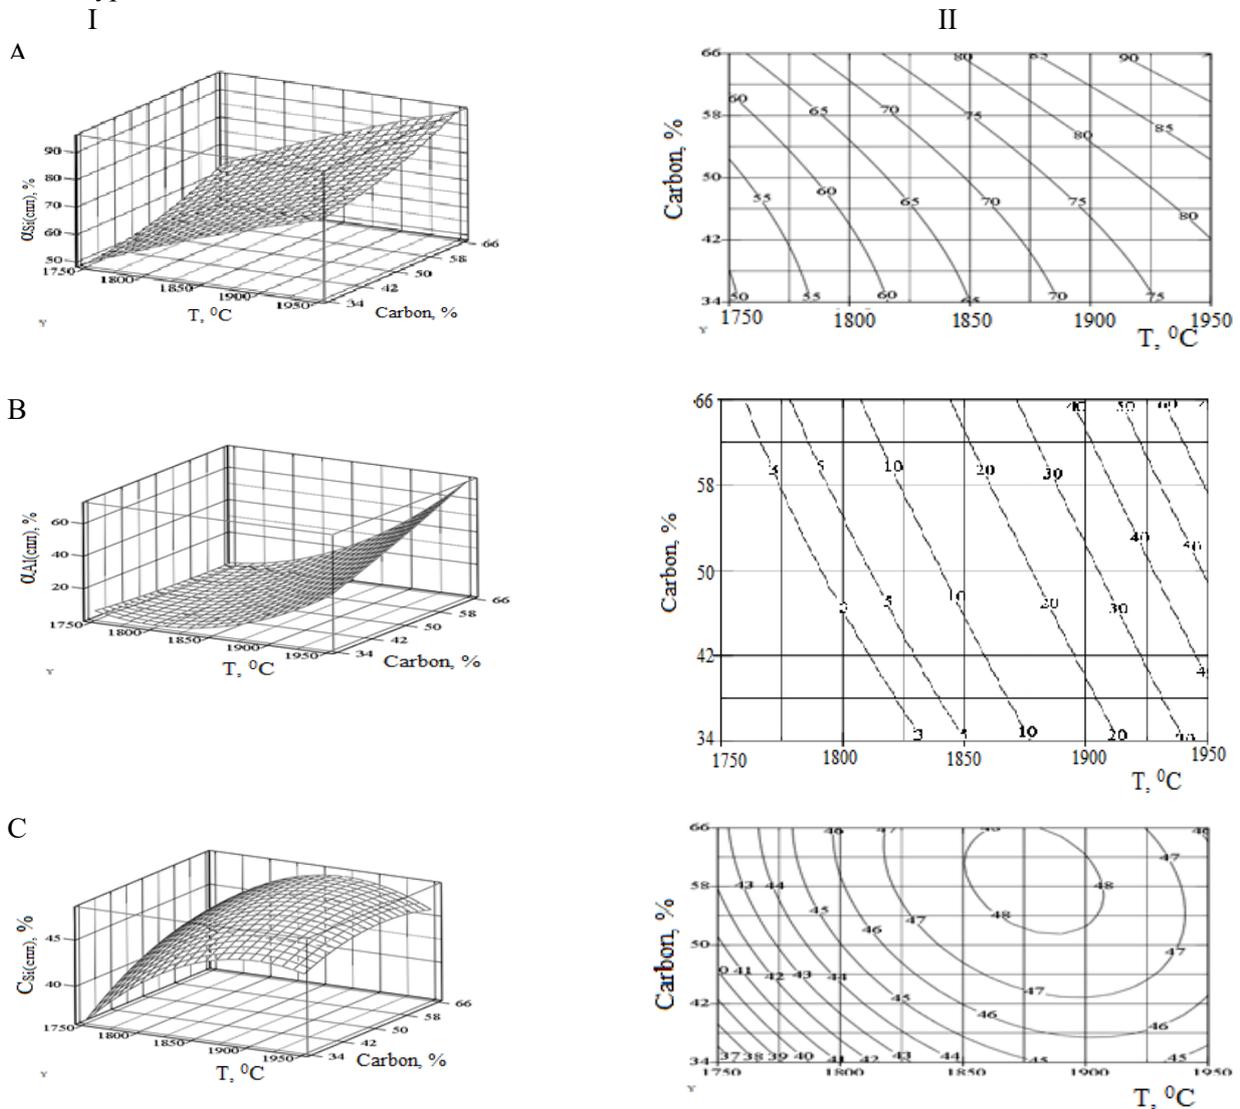

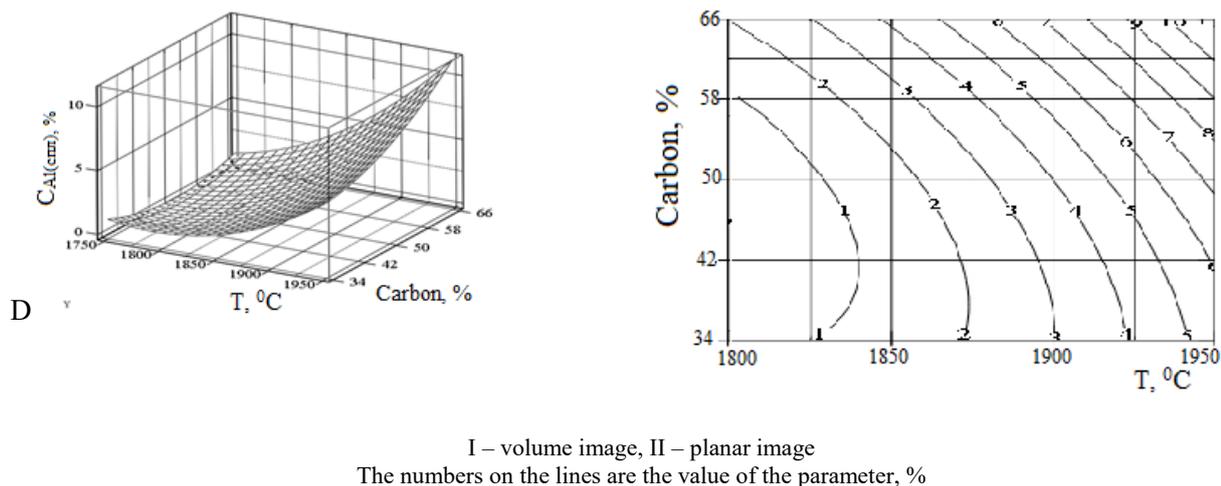


Figure 3 – graphical representation of the effect of temperature and amount of carbon on the degree of extraction of silicon in alloy (A), aluminum in alloy (B), silicon content in alloy (C), aluminum in alloy (D)

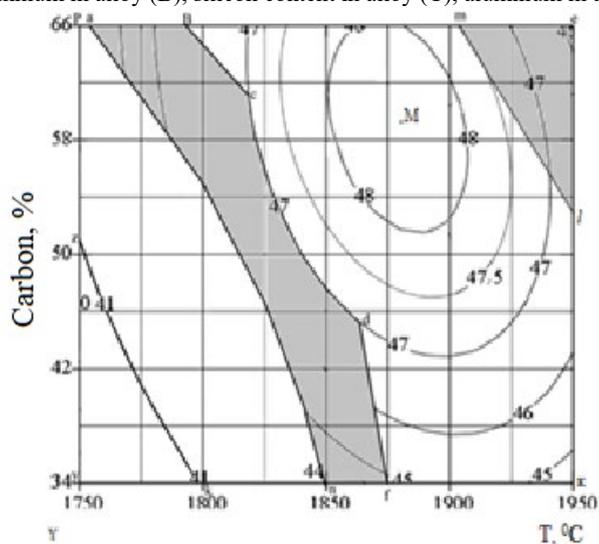


Figure 4-combined information on the influence of temperature and carbon on the technological parameters of obtaining ferroalloy from tailings

Lines ab - $\alpha_{Si(ally)}$ = 65 %, df and bc - $C_{Al(ally)}$ = 2 %, ml - $C_{Al(ally)}$ = 7,5 %, Cd - $e_{Si(ally)}$ = 47 %, zk - $C_{Si(ally)}$ = 41 %

Table 5 – Values of technological parameters in the boundary areas of Figure X.

Points in the drawing I	T, °C	carbon, %	$\alpha_{Si(ally)}$, %	$\alpha_{Al(ally)}$, %	$C_{Si(ally)}$, %	$C_{Al(ally)}$, %
a	1753	66,0	65,0	2,0	43,0	0,9
b	1796	68,0	68,2	1,3	45,9	2,0
c	1817,0	71,1	71,1	12,4	47,0	2,0
d	1860,3	71,3	71,3	13,5	47,0	1,8
f	1875	68,0	68,0	9,9	44,9	2,0
n	1850	60,0	65,0	5,0	44,0	1,5
m	1903	66,0	88,6	42,6	47,5	7,5
e	1950	66,0	95,0	69,8	45,9	11,0
l	1950	52,4	85,2	51,3	46,7	7,5
k	1800	34,0	57,4	2,1	41,0	0,1
z	1750	51,0	54,3	20,1	41,0	0,1
x	1950	34,0	77,4	34,3	45,2	5,3

Table 6 – Characteristics of ferroalloys in technological fields Figures T

The area in the figure 3	mel	bmlxfdc	abcdfn	kzpan	kzy
Characteristics of ferroalloys	Ferrosilicoaluminium grade FeSi45 A 1	Fe-Si-Al ligature with 2-2,75% Al content	Ferrosilicon FeSi45	Ferrosilicon Grade FeSi45 Extraction Si<65%)	Substandard ferrosilicon (Si<41%)

It follows from Tables 5 and 6 that to obtain ferrosilicoaluminium grade FS45A10, a temperature of 1903–1950 °C and 52,4–66,0 % carbon is required (while the extraction of Si and Al into the alloy is 85.2–

95.0 % and 42.6–69.8 %, respectively. In the *abcdfn* region (at 1753–1875⁰C and 34–66 % carbon), ferrosilicon of the FS45 brand is formed with the extraction of 60.0–71.3 % silicon into it. In the *kzpan* region, ferrosilicon of the FS45 grade is also formed (at 1750–1850⁰C and 34–54,3 % carbon). However, the degree of silicon extraction into the alloy is only 51–60 %. A large field in Figure 4 occupies the *bmlxfdc* region, in which a Fe-Si-Al ligature is formed with a content of 2–7.5 % Al and 44–48,6 % Si. Electric melting of the leaching tails was carried out with two charge compositions (Table 7).

Table 7 - Charge compositions for electric tailings melting

Charge №	Composition of the charge, %		
	Leachingtails	Coke	Steel shavings
1	54	25	21
2	52	28	20



I II
Figure 5-shows samples of the production of ferroalloys

I Alloy melting charge No. II Alloy melting charge No.

Figure 5 - photos of ferroalloys smelted from the leaching tailings of oxidized ore from the Almalı deposit

The ferroalloy obtained during the melting of the first charge contained 41,3 % Si, 1,3 % Al, 1,0 % C, 54,9 % Fe, 1,5 % (Σ Mn, Al, Ca, Ti, Cz). According to [GOST 1415–93. Ferrosilicij 2011], this alloy can be attributed to ferrosilicon grade FeSi45. Ferroalloy, the second melting contained 43,4 % Si, 7,4 % Al, 47,3 % Fe, 0,7 % Mn, 0,3 % Ti, 0,3 % Ca, 0,9 % C, 0,3 % others. According to (Ferrosilikoaluminiumij 2013), it belongs to ferrosilicoaluminium grade FeSi45A10.

The degree of silicon extraction into the alloy from the first charge was 75.8 % and from the second 79.8 %. Aluminum from the first charge turned into an alloy by 15.9 % and from the second 50.8 %.

Conclusion

Based on the results obtained for the production of ferroalloys from the tailings of sulfuric acid leaching of the oxidized copper ore of Almalı, the following conclusions can be drawn

1. Under equilibrium conditions, the formation of ferrosilicoaluminium grade FeSi45A10 is possible from tailings in the temperature range 1903–1950⁰C in the presence of 52–66 % carbon and 24 % iron. At 1753–1875⁰C and 34–66 % carbon, ferrosilicon grade FeSi45 is formed, and in the temperature range 1796–1950⁰C, 34–66 % carbon Fe-Si-Al ligature with a content of 2.0–7.5 Al and 45.9–47.5 % Si.

2. For electric melting of charges containing 52–54 % tailings, 25–28 % coke and 20–21 % steel chips. The resulting ferrosilicon has a grade of FeSi45 (41.3 % Si and 1.3 % Al), and ferrosilicoaluminium has a grade of FeSi45A10 (43.4 % Si and 7.4 % Al). 75,8–79,8 % Si and 70–50,8 % Al are extracted into the alloy.

REFERENCES

- A. Roin. HSC, 2022 – Chemistry Software, MetsoOutotec, Rozi 2021. www.mogroup.com/hsc. Accessed: 11.03. 2022.
- Axnazarova S.L., Kafarov V.V., 1985. *Metody optimizacii i kserimenta v ximicheskoj promy shlennosti: ucheb. posob.* 2-e izd. M.: Vysshaya shkola, 1985. 327 p. (Methodsofexperimentoptimizationinthechemicalindustry).
- Bekturganov N.S., Abishev D.N., 1989. *Kompleksnoe ispol'zovanie oksidnogo sy'r'ya tyazhely'x czvetny'x metallov.* – Alma – Ata; Nauka, 1989. – 211p. (Complex use of oxide raw materials of heavy non-ferrous metals).
- Copper heap leaching at San Manuel. Metallurgical test work/Jenkins J.G.//Mining Eng. (USA). – 1994. – 46. №9. – C.1094–1098.
- Electrolytic Copper – Leach, SX-EW World Operating Data. The Fourth international Copper/Jenkins J., Davenport W., Kennedy B., Robinson T.//Cobre'99 conference, Pointe Hilton Resort, Phoenix, Arizona, USA.
- GOST 1415–93. Ferrosilicij. *Texnicheskie trebovaniya i usloviya postavki.* M.: Standartinform, 2011. 19 p. (Ferrosilicon. Technical requirements and terms of delivery).

- Inkov A.M., Tapalov T., Umbetov U.U., XuVenCen V., Axmetova K.T., D'yakova E.T., 2003. Metody` optimizacii: e`lektronnyakniga. SKSU, 2003 (Optimization methods).
- Kushakova L.B., 2010. Vy`shhelachivanie otvalov Kounradskogo rudnika. Czvetny`emetally`. №8.2010. Pp.31–33. (Leaching of the dumps of the Kounrad mine).
- Kushakova L.B., Sizikova N.V., Kaznacheev M.A., Nazarenko A.Yu., Nexorosheva E.V., 2013. Izuchenie vozmozhnosti intensifikacii i tehnologii kuchnogovy`sh helachivaniyamedny`x i nikelovy`x rud mestorozhdeniya Kazaxstana s primeneniem processa kislotnogo okomkovaniya. Materialy` VII Mezhdunarodnoj konferencii. Ust`-Kamenogorsk, 2013. Pp.343–349. (To study the possibility of intensifying the technology of heap leaching of copper and nickel ores from Kazakhstan deposits using the acid pelletizing process).
- Mirovoe proizvodstvo medi zhidkostnoj e`kstrakcij: praktika i proekty`. World copper solvent extraction plants: practices and design/ Robinson T., Sandoval S., Cook P.//JOM:J.Miner., Metals and Mater. Soc. – 2003. – 55. №7. – Pp. 24–26.
- Mitrofanov S.I., Meshhaninova V.I., Kurochkina A.V. et al., 1984. Kombinirovanny`e processy` pererabotki rud czvetny`x metallov. –M., 1984.-216 p. (Combined processing processes of non-ferrous metal ores).
- Ochkov V.F., 2009. Mathcad 14 dlyastudentov, inzhenerovikonstruktorov. SPb: BXV-Peterburg, 2009. 512 p. (Mathcad 14 for students, engineers and designers).
- Ory`ngozhin E.S., Eremin N.A., Metaksa G.P., Alisheva Zh.N., 2020. Podzemnoe skvazhinnoe vy`shhelachivanie urana. Izvestiya NAN RK. Seriya geologiya i texniceskix nauk 2020 №4. (Underground borehole leaching of uranium).
- Poly`vyany`j I.R., Abishev D.N., 1995. Koncepciya razvitiya nauchno-texniceskogo potenciala czvetnoj metallurgii RK. Tezisy`j dokladov mezhdunarodny`j konferencij posveshhennoj 50-letnomu yubileyu IMiO. NUKPMSRK, Almaty`. 1995. Pp.18–24. (The concept of development of scientific and technical potential of non-ferrous metallurgy of the Republic of Kazakhstan.).
- Shevko V.M., Serzhanov G.M., Karataeva G.E., Amanov D.D., 2019. Raschet ravnovesnogo raspredeleniya e`lementov primenitel`no k programmnomu kompleksu HSC-5.1. Programma dlya E`VM. Svidetel`stvo na ob`ekt, oxranyaemy`j avtorskim pravom RK №1501 ot 29 yanvarya 2019 (Calculation of the equilibrium distribution of elements in relation to the HSC-5 software package.1. Computer program).
- Shevko V.M., Ajtkulov D.K., Ajtkulov B.D., 2014. Xloridno-e`lektrotermicheskaya pererabotka oksidny`ximed` soderzhashhix rud. Germaniya Lap Lambert Academic Publishing, 2014. – 287 p. (Chloride-electrothermal processing of oxide and copper-containing ores).
- Texnologiya proizvodstva medi. Process SX/EW//MiningMag. -1994. – 170. № 5. – Pp. 256–265.
- TU 0820-011-14513884-2013. Ferrosilikoaluminij. -Ekaterinburg: OOO «UIS», 2013. (Ferrosilicoaluminium).
- Zharmenov A.A., Baeshov A.B., Maxanbetov A.B., My`rzabekov B.E., Bedelova Zh.D., 2015. Sernokislotnoe vy`shhelachivanie marganez soderzhashhej rudy` mestorozhdeniya «Karamola».Izvestiya NAN RK. Seriya ximicheskaya. 2015. № 1. (Sulfuric acid leaching of manganese-containing ore from the Karamola deposit).
- Zharmenov A.A., Terlikbaeva A.Zh., Buktukov N.S., Shevko V.M., Abdibekov N.K., Ajtkulov D.K., Ananin A.I., Kushakova L.B., Shamganova L.S., 2019. Novy`e tehnologii doby`chi i pererabotki trudnoobogatimogo polimetallicheskogo sy`r`ya:(monografiya). – Almaty`, 2019. –630 p. (New technologies of extraction and processing of difficult-to-enrich polymetallic raw materials).

CONTENTS

A.E. Abetov, Sh.B. Yessirkepova, J. Curto Ma REMOTE SENSING AT THE STUDY OF THE THERMAL FIELD OF THE SOUTH USTYURT REGION TO FIND HYDROCARBON DEPOSITS.....	6
K.I. Akhmetov, G.M. Yessilkanov, A.Zh. Kassanova, A.V. Ubaskin, T.Zh. Abylkhassanov HYDROGEOCHEMICAL FEATURES OF THE WATER OF SALINE LAKES IN PAVLODAR REGION.....	17
S.V. Gladyshev, K.Sh. Akhmetova, L.M. Imangalieva, A.K. Kasymzhanova, N.K. Akhmadieva STUDY OF PURIFICATION OF COPPER ELECTROREFINING SOLUTION BY FLOW CENTRIFUGATION.....	26
D.A. Davronbekov, X.F. Alimdjanov, K.S. Chezhibayeva METHODS FOR REMOTE MONITORING OF BRIDGES UNDER THE INFLUENCE OF GROUNDWATER ON THEM.....	37
ZH.E. Daribayev, A.N. Kutzhanova, G.I. Issayev, I.G. Ikramov, D.U. Seksenova ASSESSMENT OF ENVIRONMENTAL DAMAGE OF NON-FERROUS METALLURGY WASTE TO THE ENVIRONMENT.....	48
K.R. Dzhabagieva, G.V. Degtyarev, A.M. Baytelieva, S.M. Laiyk, R.A. Pernebayeva FINITE ELEMENT STUDIES OF FLOW PROCESSES IN HYDROCYCLONES AND LOSS OF HEAD-ON FLOW MIXING.....	57
R.I. Yegemberdiev, I.N. Stolpovskikh, A.D. Kolga IMPROVEMENT OF THE SYSTEM OF EXPLOSIONS OF RING HOLES DURING THE DEVELOPMENT OF LOW-POWER ORE DEPOSITS.....	68
A.A. Yerzhan, P.V. Boikachev, S. Virko, Z.D. Manbetova, P.A. Dunayev A NEW METHOD OF MATCHING THE SYNTHESIS OF MATCHING DEVICES BASED ON MODIFIED APPROXIMATION IN TELECOMMUNICATION DEVICES.....	77
N.Zh. Zholamanov, S.M. Koibakov, S.T. Abildayev, G.A. Sarbassova, M.T. Omarbekova RECOMMENDATIONS FOR THE USE AND DESIGN OF FISH PROTECTION AND FISH PASSING STRUCTURES UNDER GEOLOGICAL CONDITIONS.....	85
L.Z. Issayeva, E. Slaby, S.K. Assubayeva, M.K. Kembayev, K.S. Togizov THE THREE-DIMENSIONAL MODEL OF THE AKBULAK RARE EARTH DEPOSIT (NORTHERN KAZAKHSTAN).....	96
A.A. Kabdushev, F.A. Agzamov, B.Zh. Manapbaev, D.N. Delikesheva, D.R. Korgasbekov STUDYING THE EFFECT OF REINFORCEMENT ON THE PROPERTIES OF PLUGGING MATERIALS WITH EXPANDING ADDITIVES.....	108
Y.M. Kalybekova, A.K. Zaurbek, N.N. Balgabayev, T.S. Ishangalyev, Y.K. Auelbek, A.V. Cravchuk IMPROVEMENT OF THE WATER DISTRIBUTION MANAGEMENT SCHEME ON IRRIGATION SYSTEMS USING HYDROLOGICAL INFORMATION.....	118
N.Zh. Karsakova, K.T. Sherov, B.N. Absadykov, M.R. Sikhimbayev, G.M. Tussupbekova THE ISSUES OF IMPROVING THE TECHNOLOGY FOR MACHINING THE LARGE DIAMETER HOLES OF THE LARGE-SCALE PARTS OF THE TECHNOLOGICAL EQUIPMENT.....	126
R.A. Kozbagarov, M.S. Zhiyenkozhaev, N.S. Kamzanov³, S.G. Tsygankov, A.S. Baikenzheeva DESIGN OF HYDRAULIC EXCAVATOR WORKING MEMBERS FOR DEVELOPMENT OF MUDSLIDES.....	134
E.I. Kuldeyeev, M.B. Nurpeissova, Z.A. Yestemesov, A.A. Ashimova, A.V. Barvinov OBTAINING AGLOPORITE FROM ASH OF EKIBASTUZ COAL SELECTED FROM ASH DUMP OF CRPP-3 OF ALMATY CITY.....	142

A.S. Madibekov, L.T. Ismukhanova, A.O. Zhadi, B.M. Sultanbekova, E.D. Zhaparkulova MICROPLASTICS IN THE AQUATIC ENVIRONMENT: OVERVIEW OF THE PROBLEM AND CURRENT RESEARCH AREAS.....	149
Y.G. Neshina, A.D. Mekhtiyev, V.V. Yugay, A.D. Alkina, P.Sh. Madi DEVELOPING A SENSOR FOR CONTROLLING THE PIT WALL DISPLACEMENT.....	160
M.B. Nurpeissova, Z.A. Yestemesov, A.A. Bek, V.S. Kim, G.K. Syndyrbekova MAIN CHARACTERISTICS OF FLY ASH FROM EKIBASTUZ SRPP-2.....	168
N.D. Spatayev, G.S. Sattarova, A.D. Nurgaliyeva, L. Kh. Balabas, F.K. Batessova ENSURING HEALTHY AND SAFE WORKING CONDITIONS IN BREAKAGE FACE WITH DIRECT-FLOW VENTILATION SCHEME.....	177
V.M. Shevko, A.M. Nurpeisova, D.K. Aitkylov, A.A. Joldassov THERMODYNAMIC PREDICTION AND EXPERIMENTAL PRODUCTION OF SILICON ALLOYS FROM TAILINGS LEACHING OF OXIDIZED COPPER ORE ALMALY.....	188

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>, that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE, and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайтах:

**[www:nauka-nanrk.kz](http://www.nauka-nanrk.kz)
<http://www.geolog-technical.kz/index.php/en/>
ISSN 2518-170X (Online),
ISSN 2224-5278 (Print)**

Заместитель директор отдела издания научных журналов НАН РК *Р. Жәліқызы*
Редакторы: *М.С. Ахметова, Д.С. Аленов*
Верстка на компьютере *Г.Д.Жадыранова*

Подписано в печать 14.04.2023.
Формат 70x90^{1/16}. Бумага офсетная. Печать – ризограф.
20,0 п.л. Тираж 300. Заказ 1.

Национальная академия наук РК
050010, Алматы, ул. Шевченко, 28, т. 272-13-19