

**ISSN 2518-170X (Online),
ISSN 2224-5278 (Print)**

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN

**ГЕОЛОГИЯ ЖӘНЕ ТЕХНИКАЛЫҚ ҒЫЛЫМДАР
СЕРИЯСЫ**

◆
СЕРИЯ
ГЕОЛОГИИ И ТЕХНИЧЕСКИХ НАУК

◆
SERIES
OF GEOLOGY AND TECHNICAL SCIENCES

4 (424)

ШІЛДЕ – ТАМЫЗ 2017 ж.
ИЮЛЬ – АВГУСТ 2017 г.
JULY – AUGUST 2017

ЖУРНАЛ 1940 ЖЫЛДАН ШЫГА БАСТАФАН
ЖУРНАЛ ИЗДАЕТСЯ С 1940 г.
THE JOURNAL WAS FOUNDED IN 1940.

ЖЫЛЫНА 6 РЕТ ШЫГАДЫ
ВЫХОДИТ 6 РАЗ В ГОД
PUBLISHED 6 TIMES A YEAR

АЛМАТЫ, ҚР ҰФА
АЛМАТЫ, НАН РК
ALMATY, NAS RK

Бас редакторы
Э. Г. д., профессор, КР ҰҒА академигі
И.К. Бейсембетов
Бас редакторының орынбасары
Жолтаев Г.Ж. проф., геол.-мин. ф. докторы
Редакция алқасы:

Абаканов Т.Д. проф. (Қазақстан)
Абишева З.С. проф., академик (Қазақстан)
Алиев Т. проф., академик (Әзірбайжан)
Бакиров А.Б. проф., (Қыргызстан)
Беспаев Х.А. проф. (Қазақстан)
Бишимбаев В.К. проф., академик (Қазақстан)
Буктуков Н.С. проф., академик (Қазақстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Тәжікстан)
Грэвис Р.М. проф. (АҚШ)
Ерғалиев Г.Х. проф., академик (Қазақстан)
Жуков Н.М. проф. (Қазақстан)
Кенжалиев Б.К. проф. (Қазақстан)
Қожахметов С.М. проф., академик (Казахстан)
Конторович А.Э. проф., академик (Ресей)
Курскеев А.К. проф., академик (Қазақстан)
Курчавов А.М. проф., (Ресей)
Медеу А.Р. проф., академик (Қазақстан)
Мұхамеджанов М.А. проф., корр.-мүшесі (Қазақстан)
Нигматова С.А. проф. (Қазақстан)
Оздоев С.М. проф., академик (Қазақстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Қазақстан)
Сейтов Н.С. проф., корр.-мүшесі (Қазақстан)
Сейтмуратова Э.Ю. проф., корр.-мүшесі (Қазақстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (АҚШ)
Штейнер М. проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология мен техникалық ғылымдар сериясы».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Меншіктенуші: «Қазақстан Республикасының Үлттық ғылым академиясы» РКБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрагат комитетінде 30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылдан 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://nauka-namrk.kz/geology-technical.kz>

© Қазақстан Республикасының Үлттық ғылым академиясы, 2017

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыра көш., 69а.

мекенжайы: К. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «Аруна» ЖҚ, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д. э. н., профессор, академик НАН РК
И. К. Бейсембетов
Заместитель главного редактора
Жолтаев Г.Ж. проф., доктор геол.-мин. наук

Р е д а к ц и о н а я к о л л е г и я:

Абаканов Т.Д. проф. (Казахстан)
Абишева З.С. проф., академик (Казахстан)
Алиев Т. проф., академик (Азербайджан)
Бакиров А.Б. проф., (Кыргызстан)
Беспаев Х.А. проф. (Казахстан)
Бишимбаев В.К. проф., академик (Казахстан)
Буктуков Н.С. проф., академик (Казахстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Таджикистан)
Грэвис Р.М. проф. (США)
Ергалиев Г.Х. проф., академик (Казахстан)
Жуков Н.М. проф. (Казахстан)
Кенжалиев Б.К. проф. (Казахстан)
Кожахметов С.М. проф., академик (Казахстан)
Конторович А.Э. проф., академик (Россия)
Курскеев А.К. проф., академик (Казахстан)
Курчавов А.М. проф., (Россия)
Медеу А.Р. проф., академик (Казахстан)
Мухамеджанов М.А. проф., чл.-корр. (Казахстан)
Нигматова С.А. проф. (Казахстан)
Оздоев С.М. проф., академик (Казахстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Казахстан)
Сеитов Н.С. проф., чл.-корр. (Казахстан)
Сейтмуратова Э.Ю. проф., чл.-корр. (Казахстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (США)
Штейнер М. проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,
<http://nauka-namrk.kz/geology-technical.kz>

© Национальная академия наук Республики Казахстан, 2017

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

Editor in chief
doctor of Economics, professor, academician of NAS RK

I. K. Beisembetov

Deputy editor in chief

Zholtayev G.Zh. prof., dr. geol-min. sc.

Editorial board:

Abakanov T.D. prof. (Kazakhstan)
Abisheva Z.S. prof., academician (Kazakhstan)
Aliyev T. prof., academician (Azerbaijan)
Bakirov A.B. prof., (Kyrgyzstan)
Bespayev Kh.A. prof. (Kazakhstan)
Bishimbayev V.K. prof., academician (Kazakhstan)
Buktukov N.S. prof., academician (Kazakhstan)
Bulat A.F. prof., academician (Ukraine)
Ganiyev I.N. prof., academician (Tadzhikistan)
Gravis R.M. prof. (USA)
Yergaliев G.Kh. prof., academician (Kazakhstan)
Zhukov N.M. prof. (Kazakhstan)
Kenzhaliyev B.K. prof. (Kazakhstan)
Kozhakhmetov S.M. prof., academician (Kazakhstan)
Kontorovich A.Ye. prof., academician (Russia)
Kurskeyev A.K. prof., academician (Kazakhstan)
Kurchavov A.M. prof., (Russia)
Medeu A.R. prof., academician (Kazakhstan)
Muhamedzhanov M.A. prof., corr. member. (Kazakhstan)
Nigmatova S.A. prof. (Kazakhstan)
Ozdoyev S.M. prof., academician (Kazakhstan)
Postolatii V. prof., academician (Moldova)
Rakishev B.R. prof., academician (Kazakhstan)
Seitov N.S. prof., corr. member. (Kazakhstan)
Seitmuratova Ye.U. prof., corr. member. (Kazakhstan)
Stepanets V.G. prof., (Germany)
Humphery G.D. prof. (USA)
Steiner M. prof. (Germany)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,
<http://nauka-namrk.kz/geology-technical.kz>

© National Academy of Sciences of the Republic of Kazakhstan, 2017

Editorial address: Institute of Geological Sciences named after K.I. Satpayev
69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES OF GEOLOGY AND TECHNICAL SCIENCES

ISSN 2224-5278

Volume 4, Number 424 (2017), 225 – 232

E. G. Baikonurov¹, G. A. Usoltseva¹, O. V. Chernyshova², D. V. Drobot², R. S. Akpanbayev¹¹NJSC Kazakh national research technical university after K. I. Satpaev, Almaty, Kazakhstan,²Moscow technological university, Russia.E-mail: erden_baikonurov@mail.ru , nota-vesna@yandex.kz, oxcher@mitht.ru, dvdrobot@mail.ru.
rinat2401@mail.ru

**THERMODYNAMIC EVALUATION OF PROBABILITY
OF DISSOLUTION OF SECONDARY HEAT-RESISTANT
NICKEL-CONTAINING ALLOY GS32-VI
BY MINERAL ACIDS SOLUTIONS**

Abstract. The thermodynamic probability of the transition of the components of the heat-resisting nickel-containing alloy GS32-VI to the aqueous phase under the influence of solutions of hydrochloric, sulfuric and nitric acids is considered in the article. Chemical composition of the alloy GS32-VI, wt. %: Ni - 60,05; Co - 9,3; W - 8,6; Al - 6,0; Cr - 5,0; Re - 4,0; Ta - 4,0; Y - 0,005; Nb - 1,6; Mo - 1,1; C - 0,16; B - 0,15; Ce - 0,025; La - 0,005. The main crystalline phases of the alloy are the compounds AlNi_3 , $\text{Cr}_{0,4}\text{Ni}_{0,6}$, $\text{Co}_{0,9}\text{W}_{0,1}$, $\text{Cr}_4\text{Ni}_{15}\text{W}$, $(\text{Al}_{0,7}\text{Cr}_{0,3})\text{Ni}_3$ and C_5Nb_6 , that has been revealed by the means of X-ray phase analysis. The thermodynamic probability of dissolution of GS32-VI alloy components was estimated on values of isobaric and isothermal potential of probable reactions of interaction of the main components and phases with solutions of the specified mineral acids. On the basis of the thermodynamic analysis it is established that the possibility of transition to solution of some main components of alloy depending on type of mineral acid decreases in ranks:

- for nickel, cobalt, aluminum and rhenium: $\text{HNO}_3 > \text{H}_2\text{SO}_4 > \text{HCl}$;
- for chrome: $\text{H}_2\text{SO}_4 > \text{HCl} > \text{HNO}_3$.

It is shown that nickel, cobalt, aluminum, rhenium and chromium can have the greatest probability of transition into the aqueous phase in the acidic pH region. At the same time, niobium, tungsten, tantalum and molybdenum will most likely remain in the cake as insoluble compounds in aqueous solutions.

Keywords: dissolution, heat-resisting nickel-containing alloy, hydrochloric acid, sulfuric acid, nitric acid, thermodynamics, isobaric and isothermal coefficient, equilibrium constant.

Introduction. Heat resisting nickel-containing alloys are used in many branches of the national economy, their main part is applied in aircraft industry, elements of the equipment of combined heat and power plant and thermal power plant. Their basic purpose is working under loading at high temperatures. Now a significant amount of such fulfilled alloys has collected, and need for their processing has ripened. Especially as a significant amount not only non-ferrous metals, but rare and rare-earth elements which need to be returned in production is their part [1, 2].

Hydrometallurgical and electrochemical methods of processing of such alloys with usage of mineral acids solutions [3-5] are considered as perspective methods. These methods, especially electrochemical, allow not only to take and transfer valuable components to solution but to receive almost ready-made products in the form of powders of individual metals and their mixes that makes hydrometallurgical and electrochemical methods of processing of the fulfilled alloys even more attractive [6-8].

The relevance of hydrometallurgical and electrochemical processing of heat-resistant alloys is also contained in the fact that it is possible to separate the elements and obtain concentrates of rare and rare-earth metals that cannot be done by pyrometallurgical processing [9, 10].

To substantiate the probability of dissolution of the secondary heat-resistant nickel-containing alloy GS32-VI with solutions of mineral acids, a thermodynamic analysis of possible dissolution reactions of the components and compounds included in this alloy was considered.

Methods of research and thermodynamic calculations. The object of the research was the heat-resistant nickel-containing alloy GS32-VI the elemental analysis of which was carried out using an ICP mass spectrometer for isotope and elemental analysis of ELAN DRC-e (Perkin Elmer, Canada). The alloy had the following composition, wt. %: Ni - 60.05; Co - 9.3; W = 8.6; Al is 6.0; Cr is 5.0; Re - 4.0; Ta - 4.0; Y = 0.005; Nb = 1.6; Mo - 1.1; C = 0.16; B - 0.15; Ce - 0.025; La is 0.005. That is, the main components of the alloy GS32-VI are nickel, cobalt, tungsten, aluminum, chromium, rhenium, niobium and tantalum.

The phase analysis of alloy was made with use of the Shimadzu XDR 6000 diffractometer (radiation CuK α , rotation of a sample, continuous (1 deg/min.), stepwise (a step 0,02 °, an exposure 10 s) the modes in the range of corners 2Θ 10-90. The phase analysis has shown that the main crystal phases of nickel-containing GS32-VI alloy besides metals (nickel, cobalt, aluminum and chrome) are the compounds AlNi₃, Cr_{0.4}Ni_{0.6}, Co_{0.9}W_{0.1}, Cr₄Ni₁₅W, (Al_{0.7}Cr_{0.3}) of Ni₃ and C₅Nb₆ (figure 1, table 1).

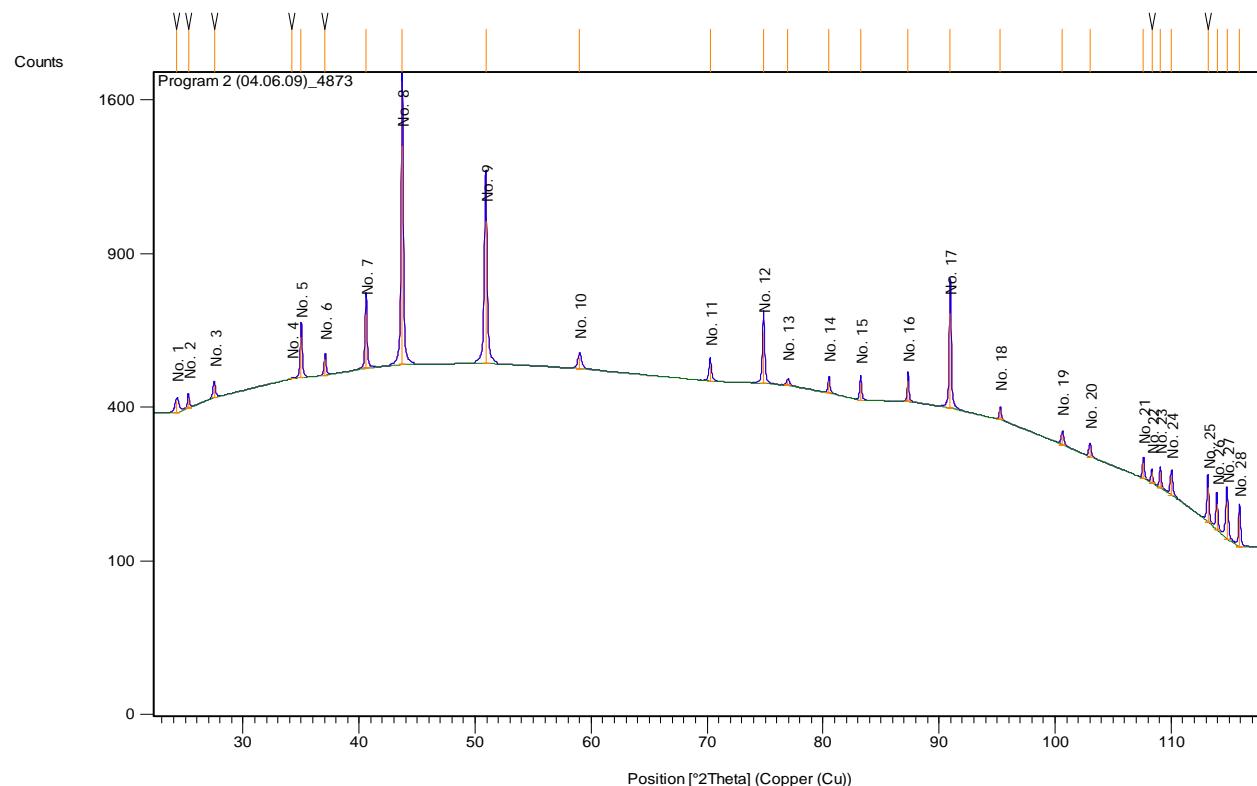


Figure 1 – X-ray diffraction pattern of the nickel-containing alloy GS32-VI

To substantiate the choice of reagents for chemical and electrochemical dissolution of the chosen heat resisting alloy it is necessary to make the thermodynamic analysis of process of conversion in solution of the color, rare and rare-earth elements which are a part of GS32-VI alloy.

Calculation of thermodynamic characteristics (isobaric and isothermal potential and equilibrium constant) of possible reactions of chemical dissolution of components of GS32-VI alloy in solutions of mineral acids was carried out by means of the program of thermodynamic calculations HSC Chemistry 5.11 of the Outokumpu Technology Engineering Research company.

Along with the calculations of Gibbs energy and the equilibrium constant, the possible state of nickel and cobalt, the main components of the alloy, on contact with mineral acids at a temperature of 25 °C was analyzed, starting from the thermodynamic calculations of the Purbax diagrams constructed using the same program.

Thermodynamics of chemical dissolution of components of nickel-containing alloy GS32-VI in solutions of mineral acids. Thermodynamic analysis of possible reactions of dissolution of the main components of the alloy GS32-VI in solutions of mineral acids is carried out for two temperatures of 20

Table 1 – Phase composition of the nickel-containing alloy ZhS32-VI using the Shimadzu XDR 6000 diffractometer database

| Phase | Reference code of the card | Latin name of phase | Chemical formula | Correspondence to the peaks on the roentgenogram | Content, wt. % |
|-------|----------------------------|---------------------------|---|--|----------------|
| 1 | 03-065-1160 | Niobium Carbide | C ₅ Nb ₆ | 5, 7, 9-13, 15-21, 23, 24, 26-28 | 7 |
| 2 | 03-065-9928 | Cobalt Tungsten | Co _{0,9} W _{0,1} | 9, 12, 17 | 17 |
| 3 | 01-072-2720 | Aluminum Nickel | AlNi ₃ | 8, 9, 12, 17, 21 | 14 |
| 4 | 03-065-8387 | Rhenium Tungsten | W ₁₃ Re ₇ | 7, 10, 28 | 1 |
| 5 | 01-089-2120 | Niobium Carbide | Nb ₄ C ₃ | 5, 7, 10, 11, 13, 14 | 3 |
| 6 | 01-071-3771 | Molybdenum | Mo | 7, 16, 28 | 1 |
| 7 | 01-071-7326 | Cobalt Molybdenum | (Co _{0,08} Mo _{0,92}) | 7, 10 | 2 |
| 8 | 03-065-5108 | Chromium Nickel Tungsten | Cr ₄ Ni ₁₅ W | 8, 9, 12, 17 | 12 |
| 9 | 01-072-3080 | Rhenium Tungsten | (Re _{0,35} W _{0,65}) | 7, 10, 28 | 1 |
| 10 | 01-071-7596 | Chromium Nickel | (Cr _{0,4} Ni _{0,6}) | 8, 9, 12, 17 | 25 |
| 11 | 01-071-5711 | Aluminum Chromium Nickel | (Al _{0,7} Cr _{0,3})Ni ₃ | 8, 9, 14, 21 | 13 |
| 12 | 01-089-7251 | Chromium Tantalum Carbide | Cr _{0,1} Ta _{0,9} C | 5, 7, 10, 11 | 2 |

Note. The peaks of X-ray diffraction patterns No. 1-4, 6, 22, 25 were not identified.

Table 2 – Thermodynamic analysis of possible dissolution reactions of the main components of GS32-VI alloy with solutions of sulfuric acid

| Reaction | $\Delta G^0, \text{KJ/mol}$ | | $\lg K_p$ | |
|---|-----------------------------|-----------|-----------|---------|
| | 20°C | 60°C | 20°C | 60°C |
| 1 Ni + H ₂ SO ₄ = NiSO ₄ + H ₂ ↑ | -72,190 | -73,927 | 12,864 | 11,592 |
| 2 Ni ₃ Al + 4,5H ₂ SO ₄ + 2,25O ₂ ↑ = = 3NiSO ₄ + 0,5Al ₂ (SO ₄) ₃ + 4,5H ₂ O | -1402,929 | -1409,306 | 249,834 | 220,836 |
| 3 Al + 1,5H ₂ SO ₄ = Al ₂ (SO ₄) ₃ + 1,5H ₂ ↑ | -514,646 | -516,615 | 91,709 | 81,007 |
| 4 Co + H ₂ SO ₄ = CoSO ₄ + H ₂ ↑ | -92,183 | -94,565 | 16,427 | 14,828 |
| 5 Co + H ₂ SO ₄ + 0,5O ₂ = CoSO ₄ + H ₂ O | -275,207 | -277,375 | 49,009 | 43,464 |
| 6 Co + H ₂ SO ₄ = CoO↓ + H ₂ O + SO ₂ ↑ | -5,480 | -19,121 | 0,976 | 2,996 |
| 7 Cr + 1,5H ₂ SO ₄ = Cr ₂ (SO ₄) ₃ + 1,5H ₂ ↑ | -253,917 | -256,485 | 45,248 | 40,218 |

and 60 °C. To perform a comparison of the energy indices of chemical reactions, calculations are made for 1 mole of the soluble component. The most technological acid is sulfuric acid, so the thermodynamic calculations of the dissolution of the alloy GS32-VI with the participation of sulfuric acid were performed in the first place. The results of thermodynamic calculations are presented in Table 2.

As follows from Table 2, the dissolution of the intermetallic compound Ni₃Al is the most probable, and its dissolution will be more active in the presence of an oxidizer, which was conventionally taken as oxygen. It is also probable that reactions 3, 5 and 7 will occur. Less possibly – 1 and 4. Reaction 6 is the least probable at dissolution of nickel-containing GS32-VI alloy solutions of sulfuric acid. Based on the above analysis and the composition of the GS32-VI alloy, it can be concluded that all the components listed in Table 2 will pass into the solution upon contact with sulfuric acid.

There is information about the dissolution of nickel-containing alloys with solutions of hydrochloric and nitric acids [3-5]. Table 3 presents the thermodynamic analysis of possible dissolution reactions of the main components of the alloy GS32-VI in hydrochloric and nitric acids.

Thus, the greatest likelihood of dissolution in hydrochloric and nitric acids is observed for the intermetallic compound Ni₃Al, which increases when the oxidant is added to the system. If we compare the effect of all acids, the thermodynamic probability of the reaction of dissolving Ni₃Al in nitric acid is higher than in hydrochloric and sulfuric. At the same time, comparing the values of Gibbs energy for

Table 3 – Thermodynamic analysis of possible dissolution reactions of the main components of GS32-VI alloy with solutions of hydrochloric and nitric acids

| Reaction | ΔG^0 , KJ / mol | | $\lg K_p$ | | |
|----------------------------------|---|-----------|-----------|---------|---------|
| | 20°C | 60°C | 20°C | 60°C | |
| Dissolution in hydrochloric acid | | | | | |
| 1 | $\text{Ni} + 2\text{HCl} = \text{NiCl}_2 + \text{H}_2\uparrow$ | -45,825 | -44,630 | 8,166 | 6,998 |
| 2 | $\text{Ni}_3\text{Al} + 9\text{HCl} = 3\text{NiCl}_2 + \text{AlCl}_3 + 4,5\text{H}_2\uparrow$ | -473,810 | -481,330 | 84,432 | 72,652 |
| 3 | $\text{Ni}_3\text{Al} + 9\text{HCl} + 2,25\text{O}_2 = 3\text{NiCl}_2 + \text{AlCl}_3 + 4,5\text{H}_2\text{O}$ | -1143,67 | -1131,83 | 203,665 | 177,357 |
| 4 | $\text{Co} + 2\text{HCl} = \text{CoCl}_2 + \text{H}_2\uparrow$ | 61,773 | 62,310 | -11,080 | -9,770 |
| 5 | $\text{Co} + 3\text{HCl} = \text{CoCl}_3 + 1,5\text{H}_2\uparrow$ | 132,930 | 138,655 | -23,689 | -21,742 |
| 6 | $\text{Al} + 3\text{HCl} = \text{AlCl}_3 + 1,5\text{H}_2\uparrow$ | -488,330 | -481,280 | 73,520 | 75,466 |
| 7 | $\text{Cr} + 2\text{HCl} = \text{CrCl}_2 + \text{H}_2\uparrow$ | -164,900 | -165,098 | 29,385 | 25,888 |
| 8 | $\text{Cr} + 3\text{HCl} = \text{CrCl}_3 + 1,5\text{H}_2\uparrow$ | -207,155 | -201,039 | 36,915 | 31,535 |
| 9 | $\text{Cr} + \text{HCl} + \text{H}_2\text{O} = 0,5\text{H}_2\text{CrO}_4 + 0,5\text{CrCl}_2 + 2\text{H}_2\uparrow$ | 64,137 | 59,332 | -11,429 | -9,304 |
| Dissolution in nitric acid | | | | | |
| 10 | $\text{Ni} + 2,4\text{HNO}_3 = \text{Ni}(\text{NO}_3)_2 + 0,2\text{N}_2\uparrow + 1,2\text{H}_2\text{O}$ | -313,954 | -310,019 | 55,946 | 48,612 |
| 11 | $\text{Ni} + 2,5\text{HNO}_3 = \text{Ni}(\text{NO}_3)_2 + 0,25\text{N}_2\text{O}\uparrow + 1,25\text{H}_2\text{O}$ | -291,784 | -288,026 | 51,995 | 45,163 |
| 12 | $\text{Ni} + 2\text{HNO}_3 + 0,5\text{O}_2 = \text{Ni}(\text{NO}_3)_2 + \text{H}_2\text{O}$ | -283,784 | -276,118 | 50,750 | 43,296 |
| 13 | $\text{Ni}_3\text{Al} + 9\text{HNO}_3 + 2,25\text{O}_2 = 3\text{Ni}(\text{NO}_3)_2 + \text{Al}(\text{NO}_3)_3 + \text{H}_2\text{O}$ | -1544,620 | -1550,026 | 275,250 | 235,993 |
| 14 | $\text{Co} + 2,5\text{HNO}_3 = \text{Co}(\text{NO}_3)_2 + 0,25\text{N}_2\text{O}\uparrow + 1,25\text{H}_2\text{O}$ | -293,851 | -289,789 | 52,364 | 45,440 |
| 15 | $\text{Co} + 2\text{HNO}_3 + 0,5\text{O}_2 = \text{Co}(\text{NO}_3)_2 + \text{H}_2\text{O}$ | -176,300 | -169,290 | 31,396 | 26,528 |
| 16 | $\text{Al} + 3,6\text{HNO}_3 = \text{Al}(\text{NO}_3)_3 + 0,3\text{N}_2\uparrow + 1,8\text{H}_2\text{O}$ | -958,387 | -945,912 | 170,784 | 148,322 |
| 17 | $\text{Cr} + 6\text{HNO}_3 = \text{CrO}_3\downarrow + 6\text{NO}_2\uparrow + 3\text{H}_2\text{O}$ | -410,456 | -440,432 | 73,143 | 69,061 |
| 18 | $\text{Cr} + 4\text{HNO}_3 = \text{CrO}_2\downarrow + 4\text{NO}_2\uparrow + 2\text{H}_2\text{O}$ | -468,826 | -488,911 | 83,544 | 76,663 |

nickel and cobalt, it should be said that the probability of dissolution of these metals in nitric acid is much higher than in hydrochloric and sulfuric. The behavior of chromium in solutions of these acids is special. In nitric acid, in addition to soluble chromium (III) nitrate, which is formed in dilute nitric acid solutions [11], chromium (II) and (III) oxides are formed, which can inhibit the dissolution of the alloy. In hydrochloric and sulfuric acids, chromium forms soluble salts with acids, and the thermodynamic probability of chromium dissolution with the formation of chromium (II) sulfate in the solution of sulfuric acid is somewhat higher than the formation of chromium (II) chloride. Concentrated sulfuric and nitric acids passivate chromium [12].

In addition to the behavior of the main components of the GS32-VI alloy with dissolution by mineral acids, the possibility of transferring rare and rare-earth elements to the aqueous phase is considered: tungsten (8.6 wt.%), Rhenium (4.0 wt.%), Tantalum (4.0 wt%), niobium (1.6 wt%), molybdenum (1.1 wt%).

The results of the thermodynamic analysis of possible reactions of mineral acids with rare and rare-earth elements that are part of GS32-VI alloy are given in Table 4.

From the results of the thermodynamic analysis given in Table 4, it follows that rhenium (in solutions of sulfuric and nitric acids) and tungsten (in solutions of sulfuric and hydrochloric acids) can be detected in aqueous solution in dissolved form (in the form of mono- and dibasic acids). Some experimental data indicate that in hydrochloric and sulfuric acid solutions hexavalent molybdenum is in the form of polymerized cations [12]. Tantalum and niobium do not pass into an aqueous solution when dissolved with acids under any conditions [11]. Along with soluble compounds, mineral acids can form a number of insoluble compounds with rare and rare-earth elements, some of which are presented in Table 4.

If we analyze the Gibbs energy values for the dissolution processes in mineral acids of each component separately, we can easily find the following decrease in the thermodynamic probability of formation of water-soluble compounds in the series:

- for nickel, cobalt, aluminum and rhenium: $\text{HNO}_3 > \text{H}_2\text{SO}_4 > \text{HCl}$;
- for chromium $\text{H}_2\text{SO}_4 > \text{HCl} > \text{HNO}_3$.

Table 4 – Thermodynamic analysis of possible reactions of solutions of mineral acids with rare and rare-earth elements that make up the alloy GS32-VI

| Reaction | $\Delta G^0, \Delta G^0, \text{ KJ}$ | | $\lg K_p$ | |
|--|--------------------------------------|----------|-----------|---------|
| | 20°C | 60°C | 20°C | 60°C |
| Sulfuric acid | | | | |
| 1 $\text{W} + \text{H}_2\text{SO}_4 + 1,5\text{O}_2 = \text{WO}_3 \downarrow + \text{SO}_3 \uparrow + \text{H}_2\text{O}$ | -628,070 | -630,530 | 111,848 | 98,803 |
| 2 $\text{W} + \text{H}_2\text{SO}_4 = \text{H}_2\text{WO}_4 + \text{S} \downarrow$ | -172,440 | -173,420 | 30,708 | 27,175 |
| 3 $\text{Mo} + 2\text{H}_2\text{SO}_4 = \text{MoO}_2 \downarrow + 2\text{SO}_2 \uparrow + 2\text{H}_2\text{O}$ | -116,183 | -142,278 | 20,704 | 22,310 |
| 4 $\text{Mo} + 3\text{H}_2\text{SO}_4 = \text{MoO}_3 \downarrow + 3\text{SO}_2 \uparrow + 3\text{H}_2\text{O}$ | -41,450 | -81,510 | 7,382 | 12,773 |
| Hydrochloric acid | | | | |
| 5 $\text{W} + 3\text{HCl} = \text{WCl}_3 \downarrow + 1,5\text{H}_2 \uparrow$ | 154,241 | 147,617 | -27,486 | -23,147 |
| 6 $\text{W} + 2\text{HCl} + 2\text{O}_2 = \text{H}_2\text{WO}_4 + \text{Cl}_2 \uparrow$ | -656,18 | -644,48 | 116,851 | 100,989 |
| 7 $\text{Re} + 4/3\text{HCl} + 8/3\text{H}_2\text{O} = 2/3\text{HReO}_4 + 3\text{H}_2 \uparrow + 1/3\text{ReCl}_4 \downarrow$ | 289,205 | 277,206 | -51,536 | -65,200 |
| 8 $\text{Re} + \text{HCl} + 2\text{O}_2 = \text{HReO}_4 + 0,5\text{Cl}_2 \uparrow$ | -564,820 | -557,280 | 100,583 | 87,325 |
| 9 $\text{Ta} + 3\text{HCl} = \text{TaCl}_3 \downarrow + 1,5\text{H}_2 \uparrow$ | -92,688 | -99,134 | 16,517 | 15,545 |
| 10 $\text{Ta} + 5\text{HCl} = \text{TaCl}_5 \downarrow + 2,5\text{H}_2 \uparrow$ | -89,063 | -99,479 | 15,871 | 15,599 |
| 11 $\text{Nb} + 3\text{HCl} = \text{NbCl}_3 \downarrow + 1,5\text{H}_2 \uparrow$ | -120,466 | -126,822 | 21,467 | 19,886 |
| 12 $\text{Nb} + 4\text{HCl} = \text{NbCl}_4 \downarrow + 2\text{H}_2 \uparrow$ | -76,677 | -88,152 | 14,198 | 13,822 |
| 13 $\text{NbC}_{0,83} + 4\text{HCl} + 1,83\text{O}_2 = \text{NbCl}_4 \downarrow + 2\text{H}_2\text{O} + 0,83\text{CO}_2 \uparrow$ | -761,520 | -757,470 | 135,612 | 118,694 |
| 14 $\text{Mo} + 2\text{HCl} = \text{MoCl}_2 \downarrow + \text{H}_2 \uparrow$ | 19,624 | 15,688 | -3,497 | -2,460 |
| 15 $\text{Mo} + \text{HCl} + \text{H}_2\text{O} = 0,5\text{MoCl}_2 \downarrow + 0,5\text{MoO}_2 \downarrow + 1,5\text{H}_2 \uparrow$ | -19,441 | -24,140 | 3,465 | 3,785 |
| Nitric acid | | | | |
| 16 $\text{W} + 4/3\text{HNO}_3 = \text{WO}_2 \downarrow + 4/3\text{NO} \uparrow + 2/3\text{H}_2\text{O}$ | -467,086 | -472,561 | 83,234 | 74,099 |
| 17 $\text{Re} + \text{HNO}_3 + \text{O}_2 = \text{HReO}_4 + \text{NO} \uparrow$ | -496,540 | -497,550 | 88,424 | 77,965 |
| 18 $\text{Re} + 7/3\text{HNO}_3 = \text{HReO}_4 + 7/3\text{NO} \uparrow + 2/3\text{H}_2\text{O}$ | -420,228 | -431,785 | 74,884 | 67,705 |
| 19 $\text{Ta} + 5\text{HNO}_3 = 0,5\text{Ta}_2\text{O}_5 \downarrow + 5\text{NO}_2 \uparrow + 2,5\text{H}_2\text{O}$ | -881,197 | -906,025 | 157,028 | 142,068 |
| 20 $\text{Nb} + 5\text{HNO}_3 = 0,5\text{Nb}_2\text{O}_5 \downarrow + 5\text{NO}_2 \uparrow + 2,5\text{H}_2\text{O}$ | -807,329 | -832,272 | 143,865 | 130,503 |
| 21 $\text{NbC}_{0,83} + \text{HNO}_3 + 1,83\text{O}_2 \uparrow = \text{HNbO}_3 \downarrow + \text{NO}_2 \uparrow + 0,83\text{CO}_2 \uparrow$ | -993,850 | -988,660 | 176,983 | 154,921 |
| 22 $\text{NbC}_{0,75} + \text{HNO}_3 + 1,75\text{O}_2 \uparrow = \text{HNbO}_3 \downarrow + \text{NO}_2 \uparrow + 0,75\text{CO}_2 \uparrow$ | -958,410 | -953,030 | 170,674 | 149,339 |

Analysis of the Purbaix diagrams constructed for the main components of the alloy GS32-VI. In this paper, an analysis of the Purbaix diagram at 25 °C is given only for nickel and cobalt, the content of which in the alloy is 60.05 and 9.3 wt. %, respectively (Figures 2 and 3). The diagrams of the state of nickel and cobalt in aqueous solutions in the presence of chlorine, sulfur and nitrogen in the system are constructed for clarity by imposing individual phase diagrams. Since the article considers the possibility of dissolution of a nickel-containing alloy by acid solutions, we were interested in the acidic pH range of the combined diagram.

On the combined diagram of the state of nickel (Figure 2), the same regions of existence for all types of acids are observed only for the following nickel forms: NiO^*OH , Ni , $\text{NiH}_{0,68}$.

In the presence of hydrochloric acid, along with the nickel Ni^{2+} ion in the acidic pH range, undissociated nickel chloride- NiCl^2 is stable. These water-soluble forms are stable up to pH = 5. In the presence of sulfuric acid there is a wide range of existence of the four-water nickel sulfate crystal hydrate, which extends up to pH = 9. The presence of nitric acid in the aqueous solution expands the region of existence of the Ni^{2+} nickel cation by the values of the oxidation potential. It should be noted that the water-soluble forms of nickel are stable only in the region of oxidation potentials and the pH of the aqueous phase is less than 5.

As can be seen from the combined diagram of the cobalt state (Figure 3), the same regions of existence for all types of acids are characteristic only of Co(OH)_3 and metallic Co. All other areas have features depending on the type of acid. In the solution of hydrochloric acid, the presence of the CoCl^+ ion

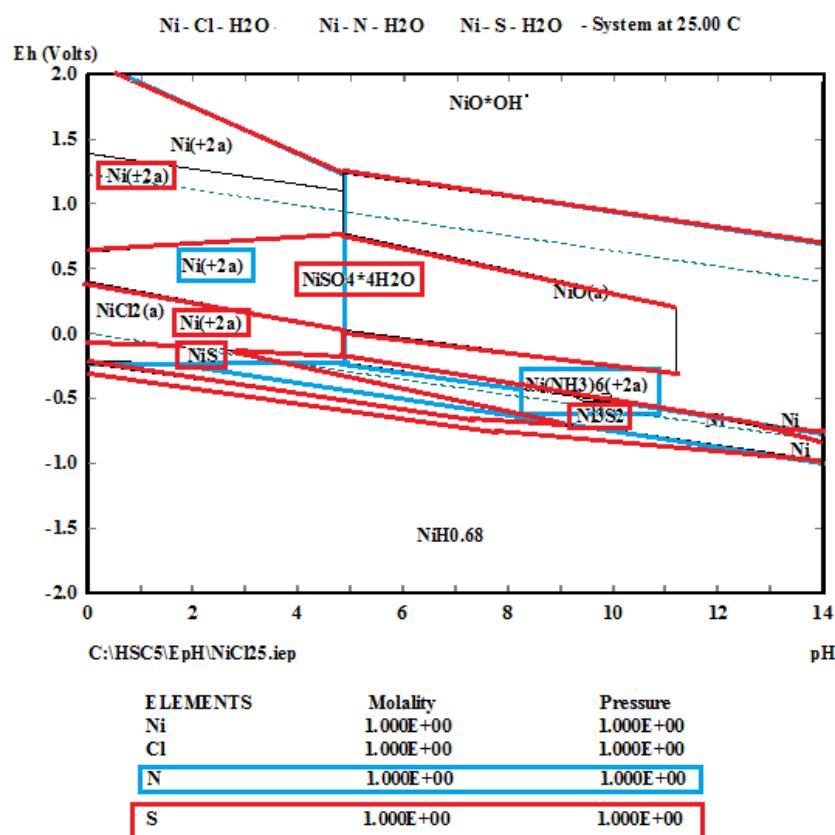


Figure 2 – Combined diagram of Ni-Cl-N-S-H₂O nickel state in aqueous solutions

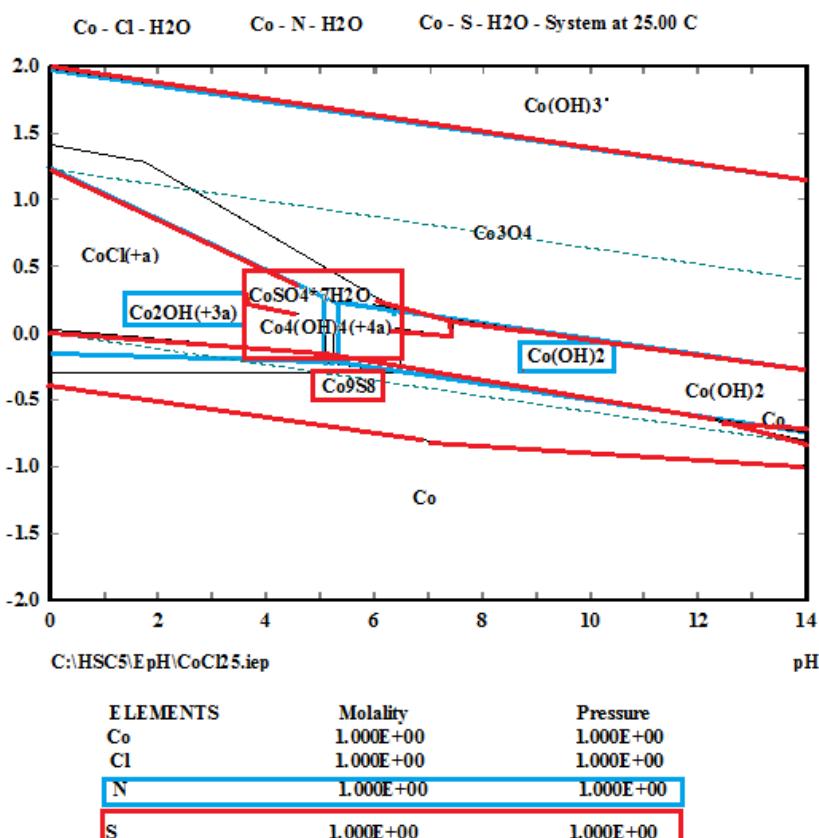


Figure 3 – Combined diagram of the Co-Cl-N-S-H₂O cobalt state in aqueous solutions

should be predicted, whose existence range extends up to pH = 7. In the presence of nitric acid, up to pH = 5, the formation of a complex cobalt ion $[Co_2OH]^{3+}$ is possible, which then passes into the $[Co_4(OH)_4]^{4+}$. The presence of sulfuric acid in the aqueous solution, like that of nitric acid, leads to the formation of $[Co_2OH]^{3+}$, which then, depending on the potential in the system, can either go to the $[Co_4(OH)_4]^{4+}$ state, or to the seven-hydrate sulphatecobalt crystal hydrate. Thus, the presence of acids in the aqueous solution promotes the conversion of cobalt into water-soluble forms.

Conclusions:

- thermodynamic analysis of possible dissolution reactions of nickel-containing alloy GS32-VI with solutions of mineral acids showed that the following components will pass into the aqueous solution: nickel, cobalt, aluminum, chromium, rhenium and, possibly, tungsten;
- rare and rare-earth elements (except rhenium) basically either form insoluble compounds with acids, or remain unchanged;
- a decrease in the thermodynamic probability of formation of water-soluble compounds in the series was established: for nickel, cobalt, aluminum and rhenium: $HNO_3 > H_2SO_4 > HCl$; for chromium - $H_2SO_4 > HCl > HNO_3$;
- analysis of the state of nickel and cobalt in aqueous solutions showed that the main amount of water-soluble compounds of these metals is stable in the acidic pH range.

REFERENCES

- [1] Heat-resisting and heat-resistant metal materials: Phys.-Chem. Principles of creation. Col. Art. Academy of Sciences of the USSR, Baykov A.A. Institute of Metallurgy. Ed. Bannykh O.A., Povarova K.B. M.: Nauka, 1987, 172 p. (in Russ.).
- [2] Petrova A.M., Kasikov A.G. Sulfuric acid processing of scrap waste of heat-resistant alloys. Scientific and practical problems in the field of chemistry and chemical technologies: materials of a scientific conference, Apatity, April 8-10, 2009. Russian Acad. Sciences.Council of the Russian Academy of Sciences "Scientific foundations of chemical technology", Kola Scientific Center, Institute of Chemistry and Technology of Rare Elements and Mineral Raw Materials. Murmansk State Technical University. Administration of the Murmansk region. Ed.: Nikolaev A.I., Nesterev D.P.. Apatity: Publishing House of the Kola Science. Center of the Russian Academy of Sciences, 2009. 153 p. (in Russ.).
- [3] Khudyakov I.F., Tikhonov A.I. Metallurgy of copper, nickel and cobalt. M.: Metallurgy, 1976, 230 p. (in Russ.).
- [4] Istrashkina M.V., Peredeeva Z.A., Fomin S.S. Perspective technologies of rhenium extraction from waste nickel alloys. Giredmet has 70 years of service in the metallurgy of rare metals and semiconductors. M.: CINAO, 2001. 111-119. (in Russ.).
- [5] Srivastava R., Kim M., Lee J. et al. *Journal of Materials Science*. 2014. 49. Iss. 14. 4671 (in Eng.).
- [6] Palant A.A., Levchuk O.M., Bryukvin V.A. Complex electrochemical technology for processing waste of heat-resistant nickel alloys containing rhenium. Non-ferrous metallurgy. 2007. 11. 11-12. (in Russ.).
- [7] Palant A.A., Bryukvin V.A., Levin A.M., Levchuk O.M. Complex electrochemical technology for the processing of waste products of high-temperature nickel alloys containing rhenium, tungsten, tantalum, niobium and other valuable metals. Metals. 2014. 1. 25-27. (in Russ.).
- [8] Lutz L.J. Recycling of Contaminated Superalloy Scrap via Electrochemical Processing. TMS, 1993. (in Eng.).
- [9] Baikonurov E.G., Chernyshova O.V., Ussoltseva G.A., Drobot D.V. Effect of the composition of the electrolyte on the characteristics of the cathode product obtained during processing of rhenium-containing heat-resistant alloy. Vestnik JezU. 2015. 2 (30). 362-366. (in Russ.).
- [10] Pat. 2412267 (RF). A method for extracting rhenium from metal wastes of nickel-containing high-temperature alloys. Kasikov A.G., Petrova A.M., Bagrova E.G., Serba N.V., Kalinnikov V.T.. Published on: 20.02.2011. Bul. № 5.
- [11] Busev A.I. Analytical chemistry of molybdenum. M.: Academy of Sciences of the USSR, 1962. 305 p. (in Russ.).
- [12] Krasitsky V. Interaction of nitric acid with metals. - Online: <http://studydoc.ru/doc/2195622/vzaimodejstvie-azotnoj-kislotoj-s-metallami> (in Russ.).

Е. Г. Байконуров¹, Г. А. Усольцева¹, О. В. Чернышова², Д. В. Дробот², Р. С. Акпанбаев¹

¹НАО Казахский национальный исследовательский технический университет им. К. И. Сатпаева,
Алматы, Казахстан,

²Московский технологический университет, Россия

ТЕРМОДИНАМИЧЕСКАЯ ОЦЕНКА ВЕРОЯТНОСТИ РАСТВОРЕНИЯ ВТОРИЧНОГО ЖАРОПРОЧНОГО НИКЕЛЬСОДЕРЖАЩЕГО СПЛАВА ЖС32-ВИ РАСТВОРАМИ МИНЕРАЛЬНЫХ КИСЛОТ

Аннотация. Рассмотрена термодинамическая вероятность перехода компонентов жаропрочного никельсодержащего сплава ЖС32-ВИ в водную фазу при воздействии на сплав растворов соляной, серной и азотной кислот. Химический состав сплава ЖС32-ВИ, масс. %: Ni - 60,05; Co - 9,3; W - 8,6; Al - 6,0; Cr - 5,0; Re - 4,0; Ta - 4,0; Y - 0,005; Nb - 1,6; Mo - 1,1; C - 0,16; B - 0,15; Ce - 0,025; La - 0,005. Основными кристал-

лическими фазами сплава являются соединения AlNi_3 , $\text{Cr}_{0.4}\text{Ni}_{0.6}$, $\text{Co}_{0.9}\text{W}_{0.1}$, $\text{Cr}_4\text{Ni}_{15}\text{W}$, $(\text{Al}_{0.7}\text{Cr}_{0.3})\text{Ni}_3$ и C_5Nb_6 , что было выявлено с помощью рентгенофазового анализа. Термодинамическая вероятность растворения компонентов сплава ЖС32-ВИ оценивалась по значениям изобарно-изотермического потенциала вероятных реакций взаимодействия основных компонентов и фаз с растворами указанных минеральных кислот. На основании термодинамического анализа установлено, что возможность перехода в раствор некоторых основных компонентов сплава в зависимости от типа минеральной кислоты уменьшается в рядах:

- для никеля, кобальта, алюминия и рения: $\text{HNO}_3 > \text{H}_2\text{SO}_4 > \text{HCl}$;
- для хрома: $\text{H}_2\text{SO}_4 > \text{HCl} > \text{HNO}_3$.

Показано, что наибольшую вероятность перехода в водную fazу в кислой области pH могут иметь никель, кобальт, алюминий, рений и хром. В то же время ниобий, вольфрам, tantal и молибден, скорее всего, будут оставаться в кеке в виде нерастворимых в водных растворах соединений.

Ключевые слова: растворение, жаропрочный никельсодержащий сплав, соляная кислота, серная кислота, азотная кислота, термодинамика, изобарно-изотермический коэффициент, константа равновесия.

Е. Г. Байконуров¹, Г. А. Усольцева¹, О. В. Чернышова², Д. В. Дробот², Р. С. Акпанбаев¹

¹К. И. Сәтбаев атындағы Қазақ ұлттық техникалық зерттеу университеті КЕАҚ, Алматы, Қазақстан,

²Мәскеу технологиялық университеті, Ресей

МИНЕРАЛДЫ ҚЫШҚЫЛДАР ЕРІТІНДІЛЕРІМЕН ЖС32-ВИ НИКЕЛЬҚУРАМДЫ ҚАЙТАЛАМА ҚЫЗУҒА БЕРИК ҚОРЫТПАСЫ ЕРУ ҮКТІМАЛДЫЛЫҒЫНЫң ТЕРМОДИНАМИКАЛЫҚ БАҒАСЫ

Аннотация. Макалада ЖС32-ВИ никельқұрамды қызуға берік қорытпаға тұз, күкірт және азот қышқылдары ерітінділерінің әсері кезінде қорытпа компоненттерінің сулы фазаға өтуінің термодинамикалық мүмкіншілігі қарастырылған. ЖС32-ВИ қорытпасының химиялық құрамы, масс. %: Ni - 60,05; Co - 9,3; W - 8,6; Al - 6,0; Cr - 5,0; Re - 4,0; Ta - 4,0; Y - 0,005; Nb - 1,6; Mo - 1,1; C - 0,16; B - 0,15; Ce - 0,025; La - 0,005. Қорытпандың негізгі кристалдық фазалары, рентгенофазалық талдау көмегімен анықталған AlNi_3 , $\text{Cr}_{0.4}\text{Ni}_{0.6}$, $\text{Co}_{0.9}\text{W}_{0.1}$, $\text{Cr}_4\text{Ni}_{15}\text{W}$, $(\text{Al}_{0.7}\text{Cr}_{0.3})\text{Ni}_3$ және C_5Nb_6 қосылыстары болып табылады. ЖС32-ВИ қорытпа компоненттерінің еру термодинамикалық үкітімалдылығы негізгі компоненттер мен фазалардың көрсетілген минералды қышқылдар ерітінділерімен үкітімалды өзара әрекеттесу реакциялардың изобарлы-изотермиялық потенциалдар мәні бойынша бағаланған. Термодинамикалық талдау негізінде ерітіндіге қорытпандың кейбір негізгі компоненттерінің өту мүмкіншілігі минералды қышқыл түріне байланысты кемитін анықталған:

- никель, кобальт, алюминий мен рений үшін: $\text{HNO}_3 > \text{H}_2\text{SO}_4 > \text{HCl}$;
- хром үшін: $\text{H}_2\text{SO}_4 > \text{HCl} > \text{HNO}_3$.

РН қышқыл облысында никель, кобальт, алюминий, рений мен хром сулы фазаға өту үкітімалдылығы жоғары екендігі көрсетілген. Сол мезетте ниобий, вольфрам, tantal және молибден кекте сулы ерітінділерде ерімейтін қосылыстар түрінде қалады.

Түйін сөздер: еру, никельқұрамды қызуға берік қорытпа, тұз қышқылы, күкірт қышқылы, азот қышқылы, термодинамика, изобарлы-изотермиялық коэффициент, тепе-тендлік константасы.

Сведения об авторах:

Байконуров Е.Г. – докторант PhD кафедры «Металлургические процессы, теплотехника и технология специальных материалов» Казахского национального исследовательского университета им. К. И. Сатпаева, erden_baikonurov@mail.ru

Усольцева Г.А. – канд. техн. наук, ассистент профессора кафедры «Металлургические процессы, теплотехника и технология специальных материалов» Казахского национального исследовательского университета имени К. И. Сатпаева, nota-vesna@yandex.ru

Чернышова О.В. – канд. техн. наук, доцент кафедры «Химия и технология редких и рассеянных элементов, наноразмерных и композиционных материалов им. К. А. Большакова» Института тонких химических технологий Московского технологического университета, oxcher@mitht.ru

Дробот Д.В. – д-р хим. наук, проф. кафедры «Химия и технология редких и рассеянных элементов, наноразмерных и композиционных материалов им. К. А. Большакова» Института тонких химических технологий Московского технологического университета, dvdrobot@mail.ru

Акпанбаев Р.С. – д-рPhD, ассистент профессора кафедры «Металлургические процессы, теплотехника и технология специальных материалов» Казахского национального исследовательского университета им. К. И. Сатпаева, rinat2401@mail.ru

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

www:nauka-nanrk.kz

ISSN 2518-170X (Online), ISSN 2224-5278 (Print)

<http://geolog-technical.kz/index.php/kz/>

Верстка Д. Н. Калкабековой

Подписано в печать 11.07.2017.
Формат 70x881/8. Бумага офсетная. Печать – ризограф.
18,2 п.л. Тираж 300. Заказ 4.

*Национальная академия наук РК
050010, Алматы, ул. Шевченко 28, т. 272-13-19, 272-13-18*