

ISSN 2518-170X (Online),  
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ  
Қ. И. Сәтпаев атындағы Қазақ ұлттық техникалық зерттеу университеті

# Х А Б А Р Л А Р Ы

## ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК  
РЕСПУБЛИКИ КАЗАХСТАН  
Казакский национальный исследовательский  
технический университет им. К. И. Сатпаева

## NEWS

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF KAZAKHSTAN  
Kazakh national research technical university  
named after K. I. Satpayev

### ГЕОЛОГИЯ ЖӘНЕ ТЕХНИКАЛЫҚ ҒЫЛЫМДАР СЕРИЯСЫ



### СЕРИЯ ГЕОЛОГИИ И ТЕХНИЧЕСКИХ НАУК



### SERIES OF GEOLOGY AND TECHNICAL SCIENCES

**2 (428)**

НАУРЫЗ – СӘУІР 2018 ж.  
МАРТ – АПРЕЛЬ 2018 г.  
MARCH – APRIL 2018

ЖУРНАЛ 1940 ЖЫЛДАН ШЫҒА БАСТАҒАН  
ЖУРНАЛ ИЗДАЕТСЯ С 1940 г.  
THE JOURNAL WAS FOUNDED IN 1940.

ЖЫЛЫНА 6 РЕТ ШЫҒАДЫ  
ВЫХОДИТ 6 РАЗ В ГОД  
PUBLISHED 6 TIMES A YEAR

---

---

*NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.*

*Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.*

*НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.*

Б а с р е д а к т о р ы  
э. ғ. д., профессор, ҚР ҰҒА академигі

**И.К. Бейсембетов**

Бас редакторының орынбасары

**Жолтаев Г.Ж.** проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

**Абаканов Т.Д.** проф. (Қазақстан)  
**Абишева З.С.** проф., академик (Қазақстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Әзірбайжан)  
**Бакиров А.Б.** проф., (Қырғыстан)  
**Беспаев Х.А.** проф. (Қазақстан)  
**Бишимбаев В.К.** проф., академик (Қазақстан)  
**Буктуков Н.С.** проф., академик (Қазақстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Тәжікстан)  
**Грэвис Р.М.** проф. (АҚШ)  
**Ерғалиев Г.К.** проф., академик (Қазақстан)  
**Жуков Н.М.** проф. (Қазақстан)  
**Кенжалиев Б.К.** проф. (Қазақстан)  
**Қожахметов С.М.** проф., академик (Қазақстан)  
**Конторович А.Э.** проф., академик (Ресей)  
**Курскеев А.К.** проф., академик (Қазақстан)  
**Курчавов А.М.** проф., (Ресей)  
**Медеу А.Р.** проф., академик (Қазақстан)  
**Мұхамеджанов М.А.** проф., корр.-мүшесі (Қазақстан)  
**Нигматова С.А.** проф. (Қазақстан)  
**Оздоев С.М.** проф., академик (Қазақстан)  
**Постолатий В.** проф., академик (Молдова)  
**Ракишев Б.Р.** проф., академик (Қазақстан)  
**Сейтов Н.С.** проф., корр.-мүшесі (Қазақстан)  
**Сейтмуратова Э.Ю.** проф., корр.-мүшесі (Қазақстан)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (АҚШ)  
**Штейнер М.** проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология мен техникалық ғылымдар сериясы».

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде  
30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,  
<http://nauka-nanrk.kz/geology-technical.kz>

---

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2018

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыра көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р  
д. э. н., профессор, академик НАН РК

**И. К. Бейсембетов**

Заместитель главного редактора

**Жолтаев Г.Ж.** проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

**Абаканов Т.Д.** проф. (Казахстан)  
**Абишева З.С.** проф., академик (Казахстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Азербайджан)  
**Бакиров А.Б.** проф., (Кыргызстан)  
**Беспаяев Х.А.** проф. (Казахстан)  
**Бишимбаев В.К.** проф., академик (Казахстан)  
**Буктуков Н.С.** проф., академик (Казахстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Таджикистан)  
**Грэвис Р.М.** проф. (США)  
**Ергалиев Г.К.** проф., академик (Казахстан)  
**Жуков Н.М.** проф. (Казахстан)  
**Кенжалиев Б.К.** проф. (Казахстан)  
**Кожаметов С.М.** проф., академик (Казахстан)  
**Конторович А.Э.** проф., академик (Россия)  
**Курскеев А.К.** проф., академик (Казахстан)  
**Курчавов А.М.** проф., (Россия)  
**Медеу А.Р.** проф., академик (Казахстан)  
**Мухамеджанов М.А.** проф., чл.-корр. (Казахстан)  
**Нигматова С.А.** проф. (Казахстан)  
**Оздоев С.М.** проф., академик (Казахстан)  
**Постолатий В.** проф., академик (Молдова)  
**Ракишев Б.Р.** проф., академик (Казахстан)  
**Сейтов Н.С.** проф., чл.-корр. (Казахстан)  
**Сейтмуратова Э.Ю.** проф., чл.-корр. (Казахстан)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (США)  
**Штейнер М.** проф. (Германия)

**«Известия НАН РК. Серия геологии и технических наук».**

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,  
<http://nauka-nanrk.kz/geology-technical.kz>

---

© Национальная академия наук Республики Казахстан, 2018

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

**I. K. Beisembetov**

Deputy editor in chief

**Zholtayev G.Zh.** prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

**Abakanov T.D.** prof. (Kazakhstan)  
**Abisheva Z.S.** prof., academician (Kazakhstan)  
**Agabekov V.Ye.** academician (Belarus)  
**Aliyev T.** prof., academician (Azerbaijan)  
**Bakirov A.B.** prof., (Kyrgyzstan)  
**Bespayev Kh.A.** prof. (Kazakhstan)  
**Bishimbayev V.K.** prof., academician (Kazakhstan)  
**Buktukov N.S.** prof., academician (Kazakhstan)  
**Bulat A.F.** prof., academician (Ukraine)  
**Ganiyev I.N.** prof., academician (Tadjikistan)  
**Gravis R.M.** prof. (USA)  
**Yergaliev G.K.** prof., academician (Kazakhstan)  
**Zhukov N.M.** prof. (Kazakhstan)  
**Kenzhaliyev B.K.** prof. (Kazakhstan)  
**Kozhakhmetov S.M.** prof., academician (Kazakhstan)  
**Kontorovich A.Ye.** prof., academician (Russia)  
**Kurskeyev A.K.** prof., academician (Kazakhstan)  
**Kurchavov A.M.** prof., (Russia)  
**Medeu A.R.** prof., academician (Kazakhstan)  
**Muhamedzhanov M.A.** prof., corr. member. (Kazakhstan)  
**Nigmatova S.A.** prof. (Kazakhstan)  
**Ozdoev S.M.** prof., academician (Kazakhstan)  
**Postolatii V.** prof., academician (Moldova)  
**Rakishev B.R.** prof., academician (Kazakhstan)  
**Seitov N.S.** prof., corr. member. (Kazakhstan)  
**Seitmuratova Ye.U.** prof., corr. member. (Kazakhstan)  
**Stepanets V.G.** prof., (Germany)  
**Humphery G.D.** prof. (USA)  
**Steiner M.** prof. (Germany)

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.**

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,  
<http://nauka-nanrk.kz/geology-technical.kz>

---

© National Academy of Sciences of the Republic of Kazakhstan, 2018

Editorial address: Institute of Geological Sciences named after K.I. Satpayev  
69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

**NEWS**

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

**SERIES OF GEOLOGY AND TECHNICAL SCIENCES**

ISSN 2224-5278

Volume 2, Number 428 (2018), 104 – 111

UDC 691.16:625.7

**A. Iskakbayev<sup>1,2</sup>, B. B. Teltayev<sup>1</sup>, C. Oliviero Rossi<sup>3</sup>, G. M. Yensebayeva<sup>2</sup>**

<sup>1</sup>Kazakhstan Highway Research Institute, Almaty, Kazakhstan,

<sup>2</sup>Al-Farabi Kazakh National University, Almaty, Kazakhstan,

<sup>3</sup>University of Calabria, Rende, Italy.

E-mail: bagdatbt@yahoo.com cesare.oliviero@unical.it iskakbayeva@inbox.ru Gulzat-y83@list.ru

**EXPERIMENTAL INVESTIGATION OF  
AN ASPHALT CONCRETE DEFORMATION  
UNDER CYCLIC LOADING**

**Abstract.** In the paper results of experimental investigation of an asphalt concrete deformation under cyclic loading on the scheme of direct tension are presented. Two series of the conventional hot dense asphalt concrete were tested. Durations of loading and rest periods were equal to 600 seconds. A stress has been applied to the tested sample quickly (within 1 second) and kept constant for the following 600 seconds. Then the stress was removed quickly and the sample was free of stress for the following 600 seconds. In the next cycle a stress greater than the preceding one was applied to the sample. In the first and second series 10 and 12 samples of the asphalt concrete were tested. In the first of them cyclic stresses were equal to 0.041; 0.111; 0.148; 0.183 and 0.219 MPa, in the second one stresses were equal to 0.744; 1.448; 2.232 and 2.976 MPa. Test temperature was 22-24°C. The tests were carried out in an equipment constructed especially. The sample strain was measured by means of two clock typed indicators and was recorded in a video camera.

Results of the tests showed that in each cycle maximum creep strain of an asphalt concrete occurs in the end of loading period and maximum recovered strain occurs in the end of relax period. Both these strains increase with the growth of cycle number, but the increase rate of the first one is higher than of the second one. In the considered test conditions (durations of loading and relax periods equal to 600 seconds, values of applied stresses from 0.041 MPa till 3.0 MPa, temperature  $T=22-24^{\circ}\text{C}$ ) an asphalt concrete is a very plastic body: the total amount of plastic strain is equal to 80-87% from the strain achieved in the end of loading period in each cycle.

**Key words:** asphalt concrete, cyclic loading, loading period, rest period, stress, strain.

**Introduction.** An asphalt pavement of a highway mainly affected by multiple actions of mechanical stresses from truck wheels. Therefore experimental investigation of deformation and failure of an asphalt concrete under cyclic loadings with parameters close to real ones on highways is practically important.

Regarding asphalt concrete the specialists know well so-called the viscoelastic continuum damage mechanics approach (VECD) which is based on the extended elastic-viscoelastic correspondence principle proposed R.A. Schapery [1]. This approach, used for the first time by Little D.N. and Kim Y.R. [2-5], has been often applied by other researchers for characterization of asphalt concrete fatigue considering non-linear strain and healing [6, 7]. In the VECD- approach the physical strain and physical stiffness of the viscoelastic material (asphalt concrete) are replaced for their pseudo similarities, i.e. for pseudo strain and pseudo stiffness respectively, which are varied from one loading cycle to another. Calculation of pseudo strain requires knowledge of dynamic modulus and phase angle, which can be determined experimentally by appropriate devices.

In recent years experimental and theoretical investigations of deformation and failure processes of asphalt concretes under different conditions of loading were started by us [8-13]. This paper is a continuation of the above mentioned our works and it contains results of testing of an asphalt concrete under cyclic loadings.

**Materials.** In this paper bitumen of grade 100-130 has been used meeting the requirements of the Kazakhstan standard ST RK 1373-2013 [14]. The bitumen grade on Superpave is PG 64-40 [15]. Bitumen has been produced by Pavlodar processing plant from crude oil of Western Siberia (Russia) by the direct oxidation method.

Hot dense asphalt concrete of type B meeting the requirements of the Kazakhstan standard ST RK 1225-2013 [16] was prepared using aggregate fractions of 5-10 mm (20 %), 10-15 mm (13 %), 15-20 mm (10 %) from Novo-Alekseevsk rock pit (Almaty region), sand of fraction 0-5 mm (50 %) from the plant “Asphaltconcrete-1” (Almaty city) and activated mineral powder (7%) from Kordai rock pit (Zhambyl region).

Bitumen content of grade 100-130 in the asphalt concrete is 4,8 % by weight of dry mineral material.

Samples of the hot asphalt concrete are prepared in form of a rectangular prism with length of 150 mm, width of 50 mm and height of 50 mm in two step procedures. The first step, the asphalt concrete samples were prepared in form of a square slab by means of the Cooper compactor (UK, model CRT-RC2S) according to the standard EN 12697-33 [17]. The second step, the samples were cut from the asphalt concrete slabs in form of a prism. Deviations in sizes of the samples did not exceed 2 mm.

A detailed information about standard characteristics of the bitumen and the asphalt concrete and about the asphalt concrete samples one can find in the authors’ work [12] published early.

**Experiment.** Tests of hot asphalt concrete samples in a form of rectangular prism on cyclic creep were carried out according to the direct tensile scheme until a complete failure.

Two parts of cyclic tests were realized. In the first of them 10 asphalt concrete samples were tested. A stress has been applied to the tested sample quickly and kept constant for 600 seconds (figure 1). Then the stress was removed quickly and the sample was free of stress for the following 600 seconds. In consequent cycles values of the stress were equal to 0,041; 0,111; 0,148; 0,183 and 0,219 MPa respectively. In the second part 12 asphalt concrete samples were tested. In the test all conditions were the same only excluding that values of the applied stress were 0,744; 1,448; 2,232 and 2,976 MPa. The test temperature was equal to 22-24 °C. The tests were carried out in a special assembled equipment, which allows applying a load to an asphalt concrete sample within 1 second. The sample strain was measured by means of two clock typed indicators and was recorded in a video camera. More detailed information about the equipment one can find in the authors’ works [12].

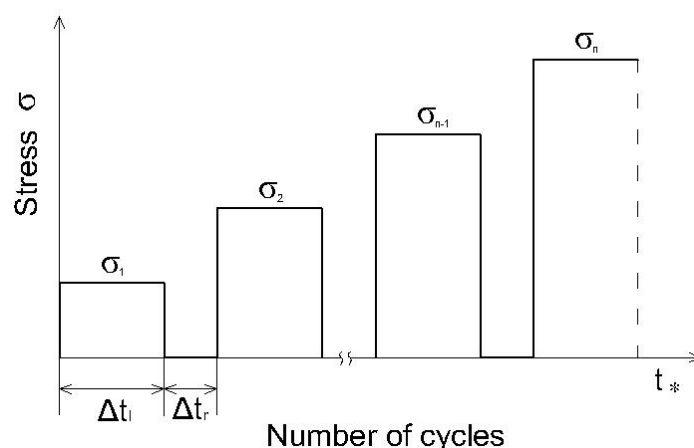


Figure 1 – Scheme of cyclic loading

**Results and discussion.** Figures 2 and 3 show the graphs of cyclic deformation for two asphalt concrete samples from the above mentioned tests parts respectively. The first sample (figure 2) have resisted to full 5 cycles “load-relax” and it was failed in the 6<sup>th</sup> cycle. The second of them (figure 3) have resisted to full 3 cycles, it was failed in the 4<sup>th</sup> cycle. Failure times were equal to 6067 and 3892 seconds respectively. Each cycle consists of loading period and relax period. The graphs, showing increasing of strain under stress and its recovery during relax period in cycles, are presented in figures 4-7. It is clearly seen how the increase of creep strain rate unde stress as well as the rate of its recovery during relax period increase with the growth of cycle number.

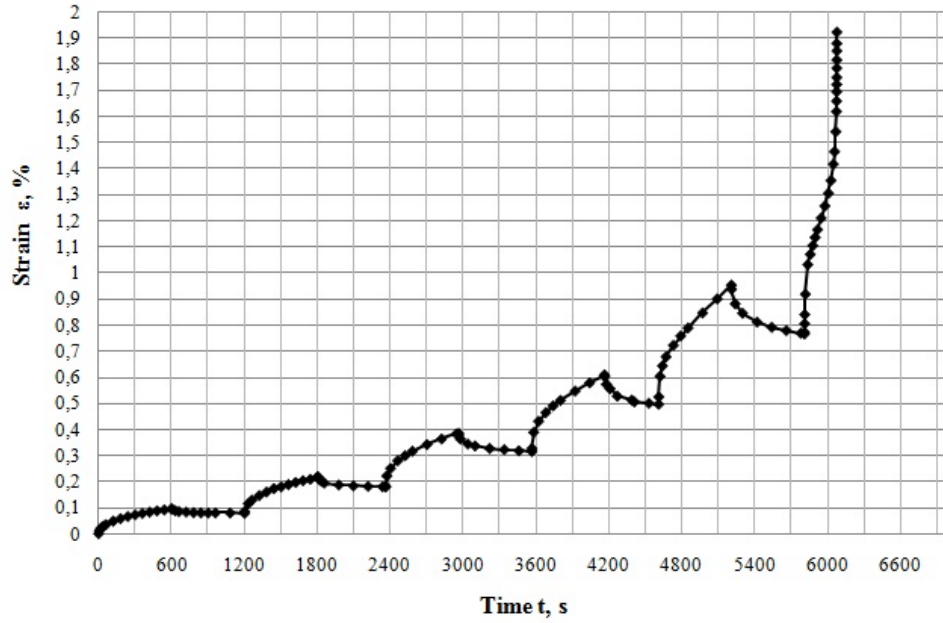


Figure 2 – Cyclic deformation of the asphalt concrete (sample No. 258)

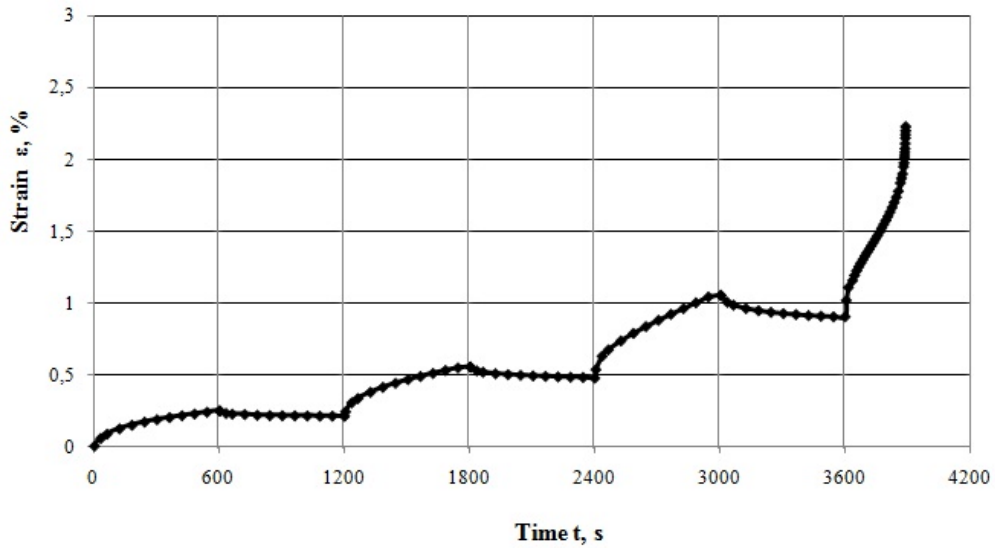


Figure 3 – Cyclic deformation of the asphalt concrete (sample No. 76)

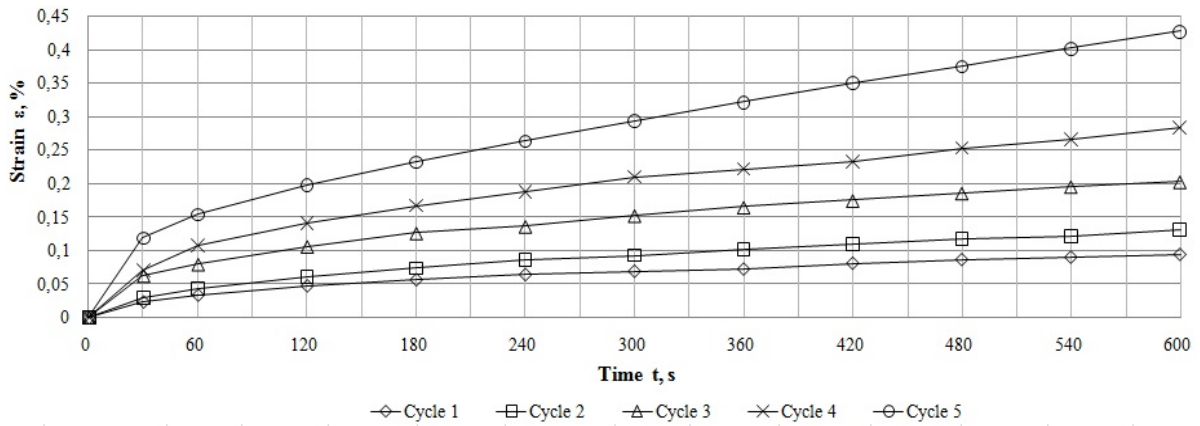


Figure 4 – Deformation of the asphalt concrete under stress in different cycles (Sample No. 258)



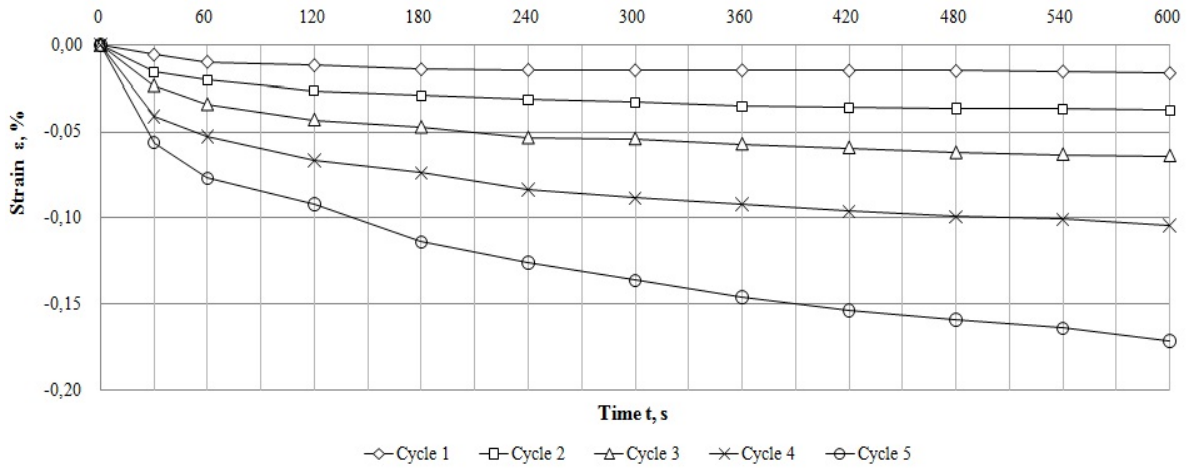


Figure 5 – Recovery of the asphalt concrete strain after removing of the stress in different cycles (Sample No. 258)

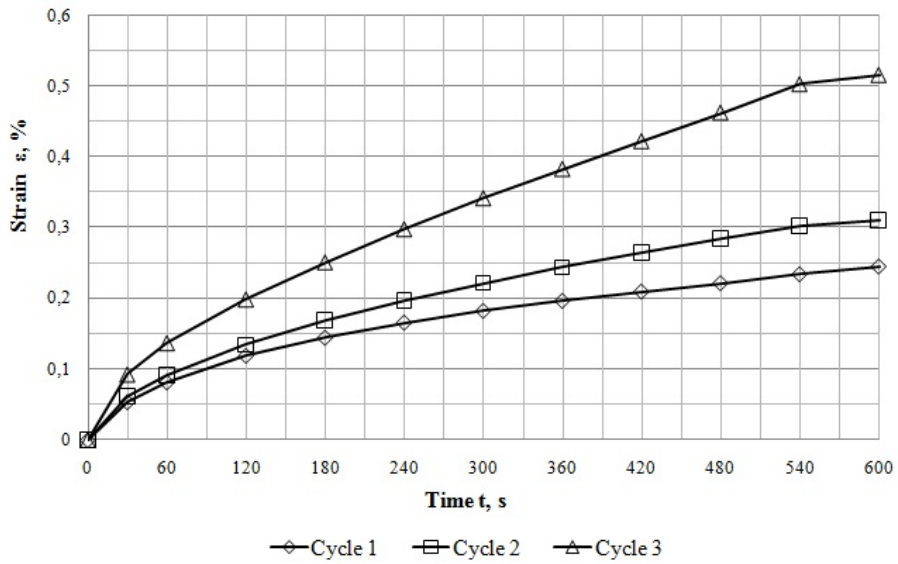


Figure 6 – Deformation of the asphalt concrete under stress in different cycles (Sample No. 76)

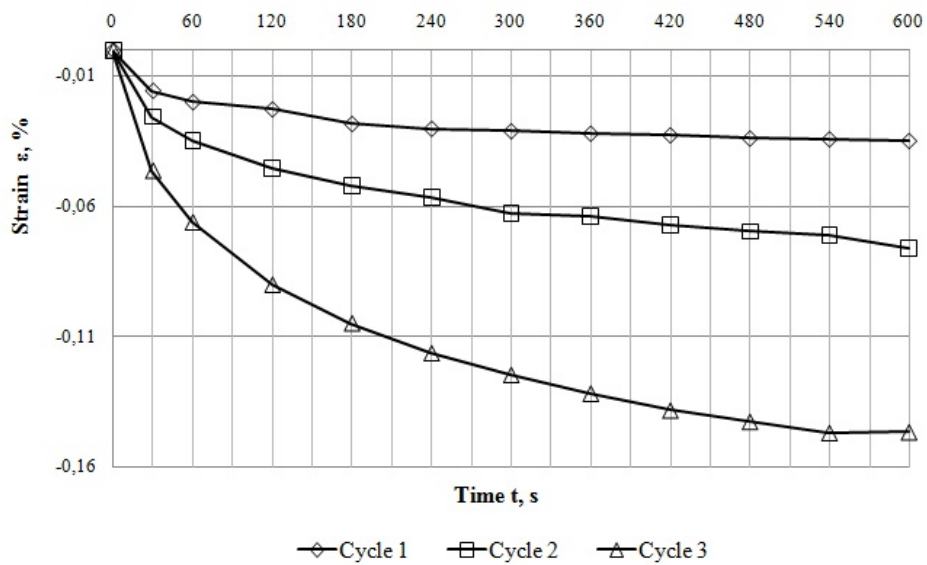


Figure 7 – Recovery of the asphalt concrete strain after removing of the stress in different cycles (Sample No. 76)

It is clear that maximum creep strain of each cycle occurs in the end of loading period and maximum recovered strain occurs in the end of relax period. As it is seen from the Figures 8 and 9, both these strains increase with the growth of cycle number, but the increase rate of the first one is higher than of the second one.

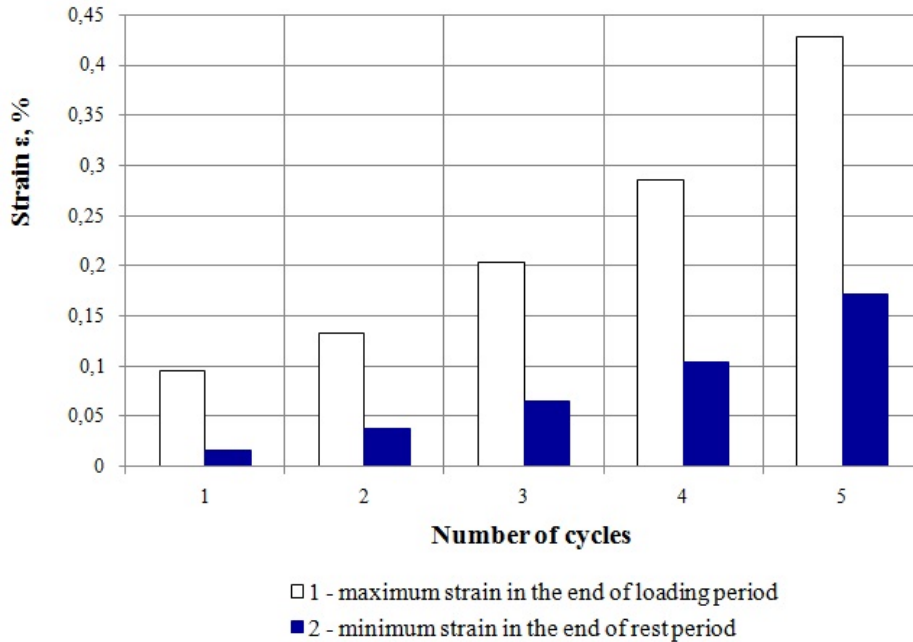


Figure 8 – Values of the maximum strain in the end of loading period and the minimum strain in the end of rest period (Sample No. 258)

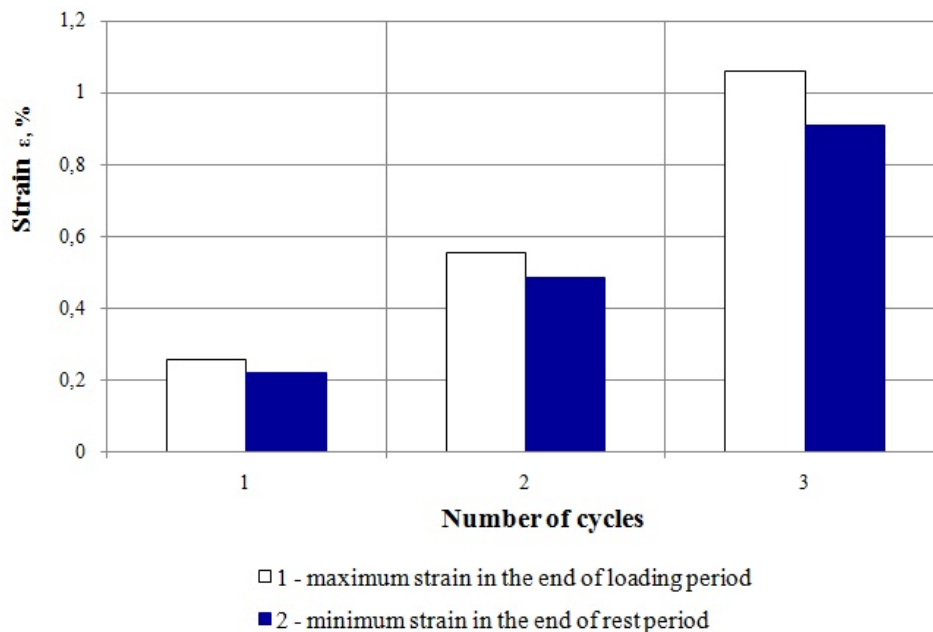


Figure 9 – Values of the maximum strain in the end of loading period and the minimum strain in the end of rest period (Sample No. 76)

It was found that in the considered test conditions (durations of loading and relax periods, values of applied stresses, temperature) the asphalt concrete is a very plastic body: the amount of the plastic strain is equal to 80-87% from the total one achieved in the end of loading period in each cycle (tables 1 and 2).

Table 1 – Values of viscoelastic and plastic strains in cycles (Sample No. 258)

Number of cycle	Strain, %*	
	viscoelastic	plastic
1	17.8	82.2
2	17.3	82.7
3	18.0	82.0
4	18.2	81.8
5	19.6	80.4

\*% from the maximum strain achieved in the end of loading period.

Table 2 – Values of viscoelastic and plastic strains in cycles (Sample No. 76)

Number of cycle	Strain, %	
	viscoelastic	plastic
1	15.0	85.0
2	13.0	87.0
3	14.2	85.8

**Conclusions.** In the work on the basis of the results obtained by experimental investigation of asphalt concretes deformation under cyclic loading the following conclusions may be made:

1. In each cycle maximum creep strain of an asphalt concrete occurs in the end of loading period and maximum recovered strain occurs in the end of relax period. Both these strains increase with the growth of cycle number, but the increase rate of the first one is higher than of the second one.

2. In the considered test conditions (durations of loading and relax periods equal to 600 seconds, values of applied stresses from 0.041 MPa till 3.0 MPa, temperature  $T = 22-24^{\circ}\text{C}$ ) an asphalt concrete is a very plastic body: the total amount of plastic strain is equal to 80-87% from the strain achieved in the end of loading period in each cycle.

#### REFERENCES

- [1] Schapary R.A. Correspondence principle and a generalized J-integral for lardge deformation and fracture analysis of viscoelastic media. *International Journal of Fracture*. 1984, 25, 195-223. (in Eng.).
- [2] Kim Y.R. Evaluation of healing and constitutive modeling of asphalt concrete by means of theory of nonlinear viscoelasticity and damage mechanics. PhD thesis, Texas A&M, College Station, Texas. 1988. (in Eng.).
- [3] Kim Y.R., Lee Y.C., Lee H.Y. Correspondence principle for characterization of asphalt concrete. *Journal of Materials In Civil Engineering*, 1995, 7(1), 59-68. (in Eng.).
- [4] Kim Y.R., Little D.N. One-dimensional constitutive modeling of asphalt concrete. *Journal of Engineering Mechanics*, 1990, 116 (4), 751-772. (in Eng.).
- [5] Kim Y.R., Little D.N., Lytton R.L. Fatigue and healing characterization of asphalt mixtures. *Journal of Materials In Civil Engineering*, 2003, 15(1), 75-83. (in Eng.).
- [6] Levenberg E., Uzan J. Exposing the nonlinear viscoelastic behavior of asphalt-aggregate mixes. *Mechanics of Time-Dependent Materials*, 2012. 16, 129-143. (in Eng.).
- [7] Levenberg E. Modeling asphalt concrete viscoelasticity with damage and healing. *International Journal of Pavement Engineering*. 2015, 1-13. (in Eng.).
- [8] Iskabayev A., Teltayev B., Alexandrov S. Determination of the creep parameters of linear viscoelastic materials. *Journal of Applied Mathematics*, 2016, pp. 1-6. (in Eng.).
- [9] Alibay Iskabayev, Bagdat Teltayev, Femistokl Andriadi, Kayrat Estayev, Elena Suppes, Ainur Iskabayeva. Experimental research of creep, recovery and fracture processes of asphalt concrete under tension, *Proceedings of the 24<sup>th</sup> International Congress of Theoretical and Applied Mechanics (XXIV ICTAM)*, 2016, Monreal, Canada, pp. 1-2. (in Eng.).
- [10] Teltayev B.B., Iskabayev A., Rossi C. Oliviero. Regularities of creep and long-term strength of hot asphalt concrete under tensile. *Proceedings of the 4<sup>th</sup> Chinese-European Workshop on Functional Pavement Design, Cew 2016, Delft, The Netherlands*, pp.169-178. (in Eng.).

[11] Iskakbayev A., Teltayev B., Oliviero Rossi C. Deformation and strength of asphalt concrete under static and step loadings. Transport Infrastructure and Systems. Proceedings of the АИТ International Congress on Transport Infrastructure and Systems (TIS 2017), Rome, Italy, 10-12 April 2017, pp. 3-8. (in Eng.).

[12] Iskakbayev A., Teltayev B., Rossi C. Oliviero. Steady-state creep of asphalt concrete. Applied Sciences, 2017, 7, p. 2-13. (in Eng.).

[13] Iskakbayev A., Teltayev B., Rossi C.O. Modeling of cyclic strength for the asphalt concrete considering damage accumulation. Applied Sciences, 2017, 7, pp. 2-11. (in Eng.).

[14] ST RK 1373-2005, Bitumen and bituminous binders. Oil road viscous bitumens, Technical specifications, Astana, Kazakhstan, 2005. (in Russ.).

[15] Superpave series No. 1. Performance graded asphalt binder specification and testing, Asphalt Institute, Lexington. 2003. (in Eng.).

[16] ST RK 1225-2013. 2003. Hot mix asphalt for roads and airfields. Technical specifications. Astana. (in Russ.).

[17] EN 12697-33 (2003). Bituminous Mixtures. Test Methods for Hot Mix Asphalt. Part 33: Specimen prepared by roller compactor. European Committee for Standardization. Brussels. (in Eng.).

**Ә. Ысқақбаев<sup>1,2</sup>, Б. Б. Телтаев<sup>1</sup>, С. О. Rossi<sup>3</sup>, Г. М. Еңсебаева<sup>2</sup>**

<sup>1</sup>Қазақстан жол ғылыми-зерттеу институты, Алматы, Қазақстан,

<sup>2</sup>әл-Фараби атындағы Қазақ ұлттық университеті, Алматы, Қазақстан,

<sup>3</sup>Калабрия университеті, Ренде, Италия

### **АСФАЛЬТБЕТОННЫҢ ЦИКЛДЫҚ ЖҮКТЕУДЕГІ ДЕФОРМАЦИЯЛАНУЫН ТӘЖРИБЕЛІК ЗЕРТТЕУ**

**Аннотация.** Мақалада асфальтбетонның созылудағы циклдық деформациялануын тәжірибелік зерттеу нәтижелері берілген. Дәстүрлі тығыз асфальтбетон үлгілерінің екі сериясы сынақтан өтті. Жүктеу және тынығу периодтарының ұзақтықтары 600 секунд болып қабылданды. Асфальтбетон үлгісіне жылдам (1 секундтың ішінде) кернеу жүктелді және ол келесі 600 секунд бойы тұрақты қалпында сақталды, одан кейін кернеу жылдап алынып, келесі 600 секунд бойы үлгі кернеусіз күйде болды. Келесі циклда үлгіге бұрынғыдан үлкен кернеу жүктелді. Бірінші және екенші серияларда 10 және 12 асфальтбетон үлгілері сыналды. Бірінші серияда кернеу мәндері 0,041; 0,111; 0,148; 0,183 және 0,219 МПа, ал екенші серияда 0,744; 1,448; 2,232 және 2,976 МПа болды. Сынақ температурасы 22-24°C. Сынақтар арнайы жасалған қондырғыда жүргізілді. Үлгілердің деформациялары сағат тәрізді индекаторлар көмегімен өлшенді және бейнекамераға жазылды.

Сынақ нәтижелері әр циклда асфальтбетонның ең үлкен деформациясы жүктеу периодының соңында, ал ең үлкен қайту деформациясы тынығу периодының соңында болатынын көрсетті. Бұл деформациялар циклдар санының артуына қарай өседі, бірақ олардың алғашқысының өсу жылдамдығы соңғысынікінен үлкен. Қарастырылған жағдайда (жүктеу және тынығу периодтарының ұзақтығы 600 секунд, кернеулер мәні 0,041-3,0 МПа аралығында, температура  $T = 22-24$  °C) асфальтбетон өте пластикалық дене болып табылады: пластикалық деформация мөлшері жүктеу периодының соңындағы жалпы деформацияның 80-87%-ын құрайды.

**Түйін сөздер:** асфальтбетон, циклдық жүктеу, жүктеу периоды, тынығу периоды, кернеу, деформация.

**А. Искақбаев<sup>1,2</sup>, Б. Б. Телтаев<sup>1</sup>, С. О. Rossi<sup>3</sup>, Г. М. Еңсебаева<sup>2</sup>**

<sup>1</sup>Казахстанский дорожный научно-исследовательский институт, Алматы, Казахстан,

<sup>2</sup>Казахский национальный университет им. аль-Фараби, Алматы, Казахстан,

<sup>3</sup>Университет Калабрии, Ренде, Италия

### **ЭКСПЕРИМЕНТАЛЬНОЕ ИССЛЕДОВАНИЕ ДЕФОРМИРОВАНИЯ АСФАЛЬТОБЕТОНА ПРИ ЦИКЛИЧЕСКОМ НАГРУЖЕНИИ**

**Аннотация.** В статье представлены результаты экспериментального исследования деформирования асфальтобетона при циклическом нагружении по схеме прямого растяжения. Было испытано две серии образцов традиционного плотного асфальтобетона. Продолжительности периода нагружения и периода отдыха были выбраны равными 600 секунд. Образцы асфальтобетона быстро (в течение 1 секунды) прикладывались

напряжение и в течение 600 секунд оно сохранялось постоянным, затем напряжение быстро снималось и в течение последующих 600 секунд образец оставался свободным от напряжения. В следующем цикле образцу прикладывалось напряжение большее чем предыдущее. В первой и второй сериях были испытаны 10 и 12 образцов асфальтобетона. В первой серии напряжения в циклах были равными 0,041; 0,111; 0,148; 0,183 и 0,219 МПа, а на второй серии – 0,744; 1,448; 2,232 и 2,976 МПа. Температура испытания 22-24°C. Испытания были проведены в специально созданной установке. Деформации образцов измерялись посредством двух индикаторов часового типа и записывались видеокамерой.

Результаты испытаний показали, что в каждом цикле максимальная деформация асфальтобетона имеет место в конце периода нагружения и максимальная восстанавливаемая деформация имеет место в конце периода отдыха. Обе эти деформации увеличиваются с увеличением числа циклов, но скорость увеличения первой из них больше, чем у последней. В рассмотренных условиях (длительности периодов нагружения и отдыха равны 600 секунд, значения приложенных напряжений от 0,041 МПа до 3,0 МПа, температура  $T = 22-24$  °C) асфальтобетон является очень пластическим телом: величина пластической деформации составляет 80-87 % от общей деформации, достигнутой в конце периода нагружения.

**Ключевые слова:** асфальтобетон, циклическое нагружение, период нагружения, период отдыха, напряжение, деформация.

**Information about the authors:**

Iskakbayev Alibai – Doctor of physical and mathematical Sciences, Professor, Department of Mechanics, Al-Farabi Kazakh National University, Almaty, Kazakhstan. iskakbayeva@inbox.ru

Teltayev Bagdat Burkhanbaiuly – Doctor of Technical Sciences, Professor, President of JSC “Kazakhstan Highway Research Institute”, Almaty, Kazakhstan. bagdatbt@yahoo.com

Rossi C.O. – Department of Chemistry and Chemical Technologies, University of Calabria, Rende, Italy. cesare.oliviero@unical.it

Yensebayeva Gulzat Muratbekovna – Department of Mechanics, Al-Farabi Kazakh National University, Almaty, Kazakhstan, PhD student. Gulzat-y83@list.ru

**Publication Ethics and Publication Malpractice  
in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

[www.nauka-nanrk.kz](http://www.nauka-nanrk.kz)

**ISSN 2518-170X (Online), ISSN 2224-5278 (Print)**

<http://geolog-technical.kz/index.php/kz/>

Верстка *Д. Н. Калкабековой*

Подписано в печать 02.04.2018.

Формат 70x881/8. Бумага офсетная. Печать – ризограф.

16,9 п.л. Тираж 300. Заказ 2.