

ISSN 2518-170X (Online),
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ
Қ. И. Сәтпаев атындағы Қазақ ұлттық техникалық зерттеу университеті

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
Казакский национальный исследовательский
технический университет им. К. И. Сатпаева

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
Kazakh national research technical university
named after K. I. Satpayev

ГЕОЛОГИЯ ЖӘНЕ ТЕХНИКАЛЫҚ ҒЫЛЫМДАР СЕРИЯСЫ



СЕРИЯ ГЕОЛОГИИ И ТЕХНИЧЕСКИХ НАУК



SERIES OF GEOLOGY AND TECHNICAL SCIENCES

3 (429)

МАМЫР – МАУСЫМ 2018 ж.
МАЙ – ИЮНЬ 2018 г.
MAY – JUNE 2018

ЖУРНАЛ 1940 ЖЫЛДАН ШЫҒА БАСТАҒАН
ЖУРНАЛ ИЗДАЕТСЯ С 1940 г.
THE JOURNAL WAS FOUNDED IN 1940.

ЖЫЛЫНА 6 РЕТ ШЫҒАДЫ
ВЫХОДИТ 6 РАЗ В ГОД
PUBLISHED 6 TIMES A YEAR

NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.

Б а с р е д а к т о р ы

э. ғ. д., профессор, ҚР ҰҒА академигі

И.К. Бейсембетов

Бас редакторының орынбасары

Жолтаев Г.Ж. проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

Абаканов Т.Д. проф. (Қазақстан)
Абишева З.С. проф., академик (Қазақстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Әзірбайжан)
Бакиров А.Б. проф., (Қырғыстан)
Беспәев Х.А. проф. (Қазақстан)
Бишимбаев В.К. проф., академик (Қазақстан)
Буктуков Н.С. проф., академик (Қазақстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Тәжікстан)
Грэвис Р.М. проф. (АҚШ)
Ерғалиев Г.К. проф., академик (Қазақстан)
Жуков Н.М. проф. (Қазақстан)
Кенжалиев Б.К. проф. (Қазақстан)
Қожахметов С.М. проф., академик (Қазақстан)
Конторович А.Э. проф., академик (Ресей)
Курскеев А.К. проф., академик (Қазақстан)
Курчавов А.М. проф., (Ресей)
Медеу А.Р. проф., академик (Қазақстан)
Мұхамеджанов М.А. проф., корр.-мүшесі (Қазақстан)
Нигматова С.А. проф. (Қазақстан)
Оздоев С.М. проф., академик (Қазақстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Қазақстан)
Сейтов Н.С. проф., корр.-мүшесі (Қазақстан)
Сейтмуратова Э.Ю. проф., корр.-мүшесі (Қазақстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (АҚШ)
Штейнер М. проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология мен техникалық ғылымдар сериясы».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2018

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыра көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д. э. н., профессор, академик НАН РК

И. К. Бейсембетов

Заместитель главного редактора

Жолтаев Г.Ж. проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

Абаканов Т.Д. проф. (Казахстан)
Абишева З.С. проф., академик (Казахстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Азербайджан)
Бакиров А.Б. проф., (Кыргызстан)
Беспаяев Х.А. проф. (Казахстан)
Бишимбаев В.К. проф., академик (Казахстан)
Буктуков Н.С. проф., академик (Казахстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Таджикистан)
Грэвис Р.М. проф. (США)
Ергалиев Г.К. проф., академик (Казахстан)
Жуков Н.М. проф. (Казахстан)
Кенжалиев Б.К. проф. (Казахстан)
Кожаметов С.М. проф., академик (Казахстан)
Конторович А.Э. проф., академик (Россия)
Курскеев А.К. проф., академик (Казахстан)
Курчавов А.М. проф., (Россия)
Медеу А.Р. проф., академик (Казахстан)
Мухамеджанов М.А. проф., чл.-корр. (Казахстан)
Нигматова С.А. проф. (Казахстан)
Оздоев С.М. проф., академик (Казахстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Казахстан)
Сейтов Н.С. проф., чл.-корр. (Казахстан)
Сейтмуратова Э.Ю. проф., чл.-корр. (Казахстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (США)
Штейнер М. проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© Национальная академия наук Республики Казахстан, 2018

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

I. K. Beisembetov

Deputy editor in chief

Zholtayev G.Zh. prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

Abakanov T.D. prof. (Kazakhstan)
Abisheva Z.S. prof., academician (Kazakhstan)
Agabekov V.Ye. academician (Belarus)
Aliyev T. prof., academician (Azerbaijan)
Bakirov A.B. prof., (Kyrgyzstan)
Bespayev Kh.A. prof. (Kazakhstan)
Bishimbayev V.K. prof., academician (Kazakhstan)
Buktukov N.S. prof., academician (Kazakhstan)
Bulat A.F. prof., academician (Ukraine)
Ganiyev I.N. prof., academician (Tadjikistan)
Gravis R.M. prof. (USA)
Yergaliev G.K. prof., academician (Kazakhstan)
Zhukov N.M. prof. (Kazakhstan)
Kenzhaliyev B.K. prof. (Kazakhstan)
Kozhakhmetov S.M. prof., academician (Kazakhstan)
Kontorovich A.Ye. prof., academician (Russia)
Kurskeyev A.K. prof., academician (Kazakhstan)
Kurchavov A.M. prof., (Russia)
Medeu A.R. prof., academician (Kazakhstan)
Muhamedzhanov M.A. prof., corr. member. (Kazakhstan)
Nigmatova S.A. prof. (Kazakhstan)
Ozdoev S.M. prof., academician (Kazakhstan)
Postolatii V. prof., academician (Moldova)
Rakishev B.R. prof., academician (Kazakhstan)
Seitov N.S. prof., corr. member. (Kazakhstan)
Seitmuratova Ye.U. prof., corr. member. (Kazakhstan)
Stepanets V.G. prof., (Germany)
Humphery G.D. prof. (USA)
Steiner M. prof. (Germany)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© National Academy of Sciences of the Republic of Kazakhstan, 2018

Editorial address: Institute of Geological Sciences named after K.I. Satpayev
69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES OF GEOLOGY AND TECHNICAL SCIENCES

ISSN 2224-5278

Volume 3, Number 429 (2018), 6 – 11

UDC 669.213:541

Sh. Ch. Altynbek^{1,2}, L. C. Bolotova², B. Mishra³, A. O. Baikonurova¹

¹Kazakh National Research Technical University named after K. I. Satpayev, Almaty, Kazakhstan,

²The Branch of the Republican State Enterprise «National center on complex processing of mineral raw materials of the Republic of Kazakhstan»

State scientific-industrial association of industrial ecology "Kazmekhanobr", Almaty, Kazakhstan,

³Worcester Polytechnic Institute, Worcester, USA.

E-mail: Altynbek.shinar@gmail.com, L_bolotova@yahoo.com, bmishra@wpi.edu, a.baikonurova@yandex.kz

**DEVELOPMENT OF THE REGENERATION TECHNOLOGY
OF AM-2B ION EXCHANGE RESIN
IN THE PROCESS OF SORPTION OF GOLD RECOVERY
FROM POLYCOMPONENT GOLD-BEARING SOLUTIONS**

Abstract. The principal technological scheme of desorption of gold and accompanying metal-impurities from the AM-2B resin phase used for the sorption processing of gold-bearing ores is considered. The proposed combined scheme, involving the use of two independent traditional methods of gold elution, involves desorption of metal impurities from the resin with alkaline solutions of sodium thiocyanate, and gold - with sulfuric acid solutions of thiourea.

The results of studies of the gold elution and impurity metals from anionite saturated with the following components are given, mg/g: Au = 2.6; Cu - 3.5; Zn - 1.3; Ni - 2.9; Co - 3.3. It is shown that the main amount of impurity metals is desorbed from the resin under its thiocyanate treatment, while the transition of gold into the eluate is negligible. The composition of the eluate in the thiocyanate treatment of saturated resin, mg/l: Au - 14.66; Cu - 669.2; Zn = 222.1; Ni - 493.0; Co - 412.6. Subsequent processing of the resin with sulfuric acid solutions of thiourea makes it possible to transit 98.67 % of gold from the ionite containing a small amount of impurities to the eluate. The resulting eluates containing ~ 377 mg/l of gold are target solutions for obtaining a valuable metal.

The ion exchanger resin was regenerated by washing with water and treating with an alkaline solution of sodium to convert it to an OH⁻-form, at which sorption of gold from cyanide solutions of heap leaching takes place.

Residual contents of components in the resin after regeneration were, mg/g: Au - 0.06; Cu - 0.02; Zn - 0.02; Ni - 0.01; Co - 1.2, which allows the successful use of the regenerated resin at the next stage of sorption.

Keywords: elution, desorption, combined technology, anion exchange resin, thiocyanate solutions, acid thiourea solutions.

Introduction. Gold-bearing productive cyanide solutions formed during heap leaching, in addition to gold, contain complex cyanide compounds of silver - NaAg(CN)₂ and metal impurities, of which the most characteristic are cyanide copper compounds NaCu(CN)₂, Na₂Cu(CN)₃ and Na₃Cu(CN)₄, of zinc Na₂Zn(CN)₄, nickel Na₂Ni(CN)₄, iron Na₄Fe(CN)₆ and cobalt Na₄Co(CN)₆ [1-4]. In this regard, saturated ion-exchange resins, along with gold and silver, contain impurity metals, which mass content in the resin is sometimes 2-3 times higher than the content of noble metals.

In the process of regeneration of anion exchange resin, it is necessary to achieve the most complete desorption of both noble metals and impurities. The impurities remaining on the resin when it is reused in the sorption process deteriorate the kinetics of the process, reduce the resin capacity of noble metals, and increase the loss of dissolved gold in the liquid phase of tails. As practice shows, the content of residual components in the anion exchange resin after regeneration can be: gold - no more than 0.1-0.3 mg/g, impurities - no more than 3-5 mg/g of air-dry sorbent [5].

Analysis of technologies for the desorption of gold from saturated ion-exchange resins showed that among the tested eluents the most suitable are alkaline solutions of zinc cyanide [6], sodium thiocyanate and ammonium [7], as well as solutions of thiourea in the presence of mineral acids [8].

However, zinc tetracyanate is effective as an eluent only for anion exchangers having guanidyl groups. The anion exchangers used in the CIS contain other functional groups, and zinc cyanide has low values. To reuse anion exchangers, a deep removal of zinc from the resin, which is carried out by solutions of mineral acids, is necessary. The process is ineffective and has not found industrial application [9-11].

On an industrial scale, mainly thiocyanate and thiourea solutions are used, while the latter is given preference in terms of technical and economic indicators. The costs of reagents for thiourea technology are 1.91 times lower than the costs of thiocyanate technology.

Acid-thiourea technology of gold desorption and resin regeneration includes several operations, the main ones are the treatment of the resin with a hot cyanide solution to remove iron and copper, sulfuric acid for desorption of zinc and nickel, sorption of thiourea, desorption of gold and silver directly with thiourea sulfuric acid solution, thiourea washing and transferring the resin to the OH-form by treatment with sodium hydroxide. All operations, except for aqueous washing of slurries, alkaline treatment and washing of alkali are conducted at a temperature of 55-60 °C and atmospheric pressure [5, 12].

In the operation of acid-thiourea resin processing technology, its serious drawbacks were revealed: when using strong hot cyanide solutions for desorption of copper and iron, gold and silver are partially desorbed from the ion exchanger; zinc and iron are incompletely desorbed and almost no cobalt is extracted. In this regard, zinc, iron and cobalt are accumulated in the ion exchange resin, which leads to a deterioration of its sorption properties; complexity and multi-operation scheme; a long duration of the sorption-desorption-regeneration cycle (250-300 hours) [5].

In order to eliminate these shortcomings, a study of the combined processing technology of saturated anionite proposed by the authors has been conducted. This technology includes three stages of desorption: the first and the second - selective elution of impurity metals, the third one - gold elution with the use of specific complexing reagents at each stage, and the regeneration of the ion exchanger with an alkali solution.

Instead of using strong hot cyanide solutions for desorption of copper and iron, it is suggested to use weak alkaline thiocyanate solutions that successfully desorb these impurity metals but leave gold in the resin [13], then desorb zinc and nickel with a solution of sulfuric acid with simultaneous conversion of the resin from thiocyanate form into sulphate, and then desorption of gold with the acid solution of thiourea. Also, the task was to maximally desorb cobalt from the resin, which according to the existing technology is almost not extracted.

The implementation of the combined technology will eliminate the shortcomings of the existing industrial technology and ensure the production of high-quality gold-bearing eluate without accompanying impurities, which will improve the quality of the finished product.

Methods of the research

Researches used the AM-2B resin produced by GC "Smoly" (Ukraine) [14]. AM-2B anionite is a macroporous ion-exchange resin based on styrene copolymer with divinylbenzene containing strong and weakly basic functional groups in its structure.

Studies on the combined technology of gold desorption and resin regeneration were carried out in dynamic conditions in a laboratory sorption column with a height of 160 mm and a diameter of 40 mm. The height of the resin layer was maintained to 140 mm, the volume of the resin was 60 ml. All the process steps were carried out by passing the solution through the resin layer in the bottom-up column. The flow rate of the solution was 100-120 ml/h, which corresponds to a specific load (SL) of 2-2.4 h⁻¹. The proposed technological scheme of the combined technology of gold desorption and resin regeneration is presented in figure 1.

After completion of the gold elution from the resin phase, the ion exchanger is regenerated by its successive washing with water at an elevated temperature of 55 °C and room temperature. Then alkaline treatment of the ion exchanger (3 % NaOH) is carried out in order to neutralize the sulfuric acid residues and transfer the resin to the OH⁻ form, which is most favorable for the gold sorption from alkaline cyanide heap leaching solutions. Spent solutions from alkaline treatment are combined with solutions from acid treatment and aqueous washing from thiourea and are sent for neutralization.

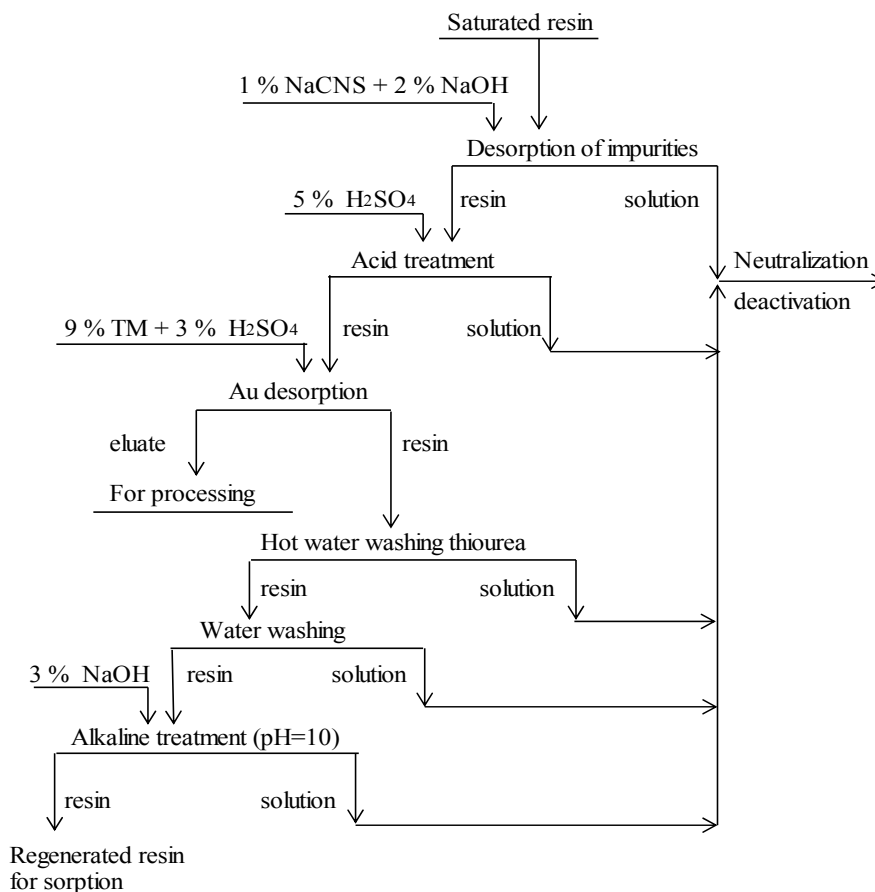


Figure 1 – Principal flow chart of the combined technology of gold desorption and AM-2B resin regeneration

Results of tests of combined thiocyanate-thiourea resin regeneration technology

Volume of the passed solution, sp.v.		Metal content in solution, mg/l					Residual metal content in the resin, mg/g				
in operation	in aggregate	Au	Cu	Ni	Zn	Co	Au	Cu	Ni	Zn	Co
Desorbing solution of 1 % NaSCN and 2 % NaOH											
1,97	1,97	1,45	589,0	184,0	192,5	296,0	2,59	0,45	1,95	0,30	1,77
1,97	3,93	4,87	65,10	220,0	18,4	62,0	2,57	0,11	0,81	0,21	1,45
1,90	5,83	4,80	5,88	65,0	4,0	11,0	2,54	0,09	0,48	0,19	1,39
0,47	6,30	3,54	9,21	24,0	7,2	43,6	2,54	0,07	0,45	0,18	1,34
Processing 5 % H ₂ SO ₄											
1,93	1,93	0,98	1,13	6,80	0,09	3,28	2,53	0,07	0,42	0,18	1,32
2,17	4,10	0,0	1,38	35,60	3,90	0,14	2,53	0,06	0,22	0,16	1,32
0,40	4,50	0,0	0,37	16,2	2,10	0,05	2,53	0,06	0,20	0,15	1,32
Desorbing solution of 9 % CS(NH ₂) ₂ and 3 % H ₂ SO ₄											
2,47	2,47	194,0	1,95	7,50	2,00	0,17	1,27	0,05	0,15	0,14	1,32
2,70	5,17	122,0	1,24	2,00	3,50	0,11	0,41	0,04	0,14	0,12	1,32
2,40	7,57	34,0	0,73	1,20	3,70	0,02	0,19	0,03	0,13	0,09	1,32
2,37	9,93	15,5	1,13	3,40	3,18	0,13	0,10	0,03	0,11	0,07	1,32
2,03	11,97	6,5	0,70	4,05	2,88	0,13	0,06	0,02	0,09	0,06	1,32
2,07	14,03	2,65	0,58	3,30	2,68	0,08	0,05	0,02	0,07	0,04	1,32
2,50	16,53	1,95	0,55	3,03	2,98	0,08	0,03	0,02	0,05	0,02	1,32
Washing H ₂ O											
2,00	2,00	0,84	0,24	1,53	2,20	0,02	0,03	0,02	0,04	0,01	1,32
2,50	4,50	0,30	0,04	0,33	1,50	0,00	0,03	0,01	0,04	0,01	1,32
Processing 3 % NaOH											
2,00	2,00	0,18	0,25	0,19	1,29	1,58	0,03	0,01	0,04	0,01	1,31

Note: The content of ions of metal-impurities in the regenerated resin, mg/g: Au = 0,06; Cu - 0,02; Ni - 0,01; Zn - 0,02; Co - 1,2.

Results and their discussion

The results of the experiments are shown in table and in figures 2 and 3.

Figures 2 and 3 show graphical data on the desorption of metals by different eluting solutions.

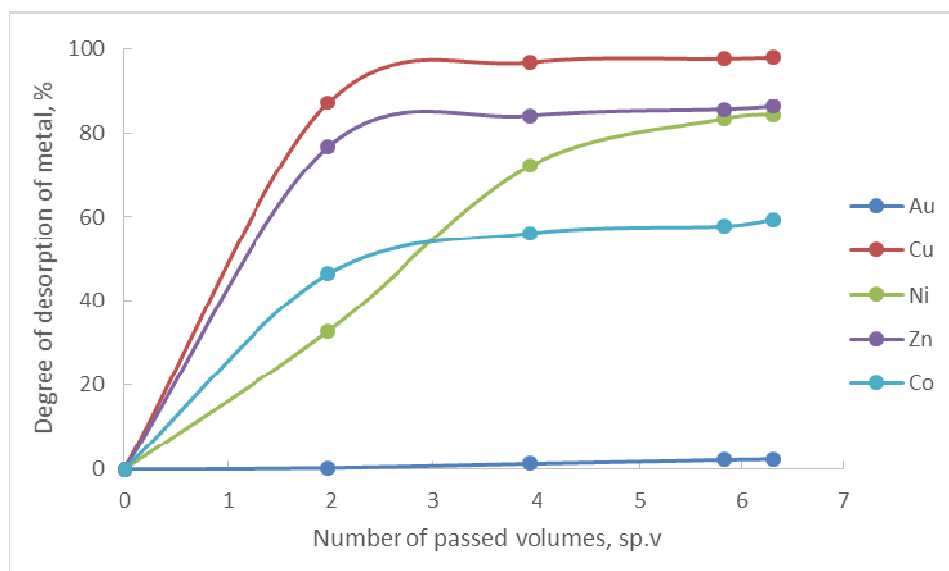


Figure 2 – Dependence of metal desorption on the volume of the passed solution upon desorption of metals-impurities with solutions of 1% NaSCN and 2% NaOH

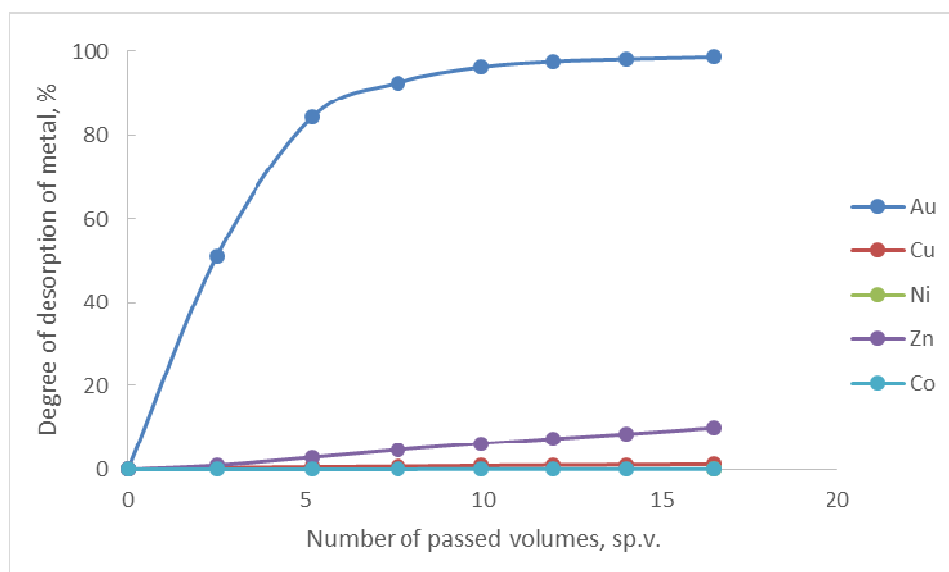


Figure 3 – Dependence of metal desorption on the volume of the passed solution upon desorption of metals-impurities by solutions of 9 % CS(NH₂)₂ and 3 % H₂SO₄

From the presented data, it can be seen that the majority of the metal impurities are desorbed using an alkaline thiocyanate solution. At the same time, to the eluate there are transferred, %: copper 97.88, nickel 84.32, zinc 86.18, cobalt 59.43. Further acid treatment of the ion exchange resin allows to desorb mainly nickel (from 84.32 % to 93.10 %) and zinc (86.18 % to 88.10 %).

Figure 3 shows the data using the acidic thiourea solution (9 % CS(NH₂)₂ and 3 % H₂SO₄) as the eluent. It can be seen that the metals-impurities are not desorbed practically, and gold is desorbed to 98.67 %.

REFERENCES

- [1] Meretukov M.A. Zoloto: khimiia, mineralogiia, metallurgii. M.: Ruda i metally, 2008. P. 528.
- [2] Barchenkov V.V. Tekhnologiia gidrometallurgicheskoi pererabotki zolotosoderzhashchikh flotokonsentratov s primeneniem aktivnykh uglei. Chita: Poisk, 2004. P. 242.
- [3] Altynbek Sh.Ch., Bolotova L.S. Izuchenie sostava produktivnykh zolotosoderzhashchikh rastvorov kuchnogo vyshchelachivaniia s tsel'iu vybora naibolee effektivnogo sorbenta dlia izvlecheniia zolota // Nauch.-tekhn. zhurn. Promyshlennost' Kazakhstana. Almaty, 2013. N 5(80), 10. P. 91-95.
- [4] Turysbekova G.S., Meretukov M.A., Bektaï E.K. Zoloto, innovatsii v khimii i metallurgii, Almaty, 2015. P. 632.
- [5] Strizhko L.S. Metallurgiiia zolota i serebra: Uchebnoe posobie dlia vuzov. M.: MISIS, 2001. 336 p.
- [6] HENKEL CORPORATION PCT (11) NO 9710367A1, (21) PCT/US 96113817, S22V11/08, 1997.
- [7] Bolotova L.S. i dr. O primeneniï ferromagnitnykh smol v gidrometallurgii zolota: Sbornik rabot po khimii. Alma-Ata, 1977. Vyp.5. P. 144-155.
- [8] Altynbek Sh.Ch., Baikonurova A.O., Mishra B. Vliianie tsianidnykh kompleksov metallov na ravnovesnoe raspredelenie zolota v sisteme anionit-rastvor // Materials of the international scientific-practical conference «Prospects for the development of modern science». Jerusalem, Israel, May 4-6, 2016. P. 124-130.
- [9] Bolotova L.S. Ionoobmennaiia tekhnologiia v gidrometallurgii zolota // Geologiia i razvedka neдр Kazakhstana. 2001. N 2. P. 52-56.
- [10] Bolotova L.S. Tekhnologiia CIP/CIL i RIP/RIL v gidrometallurgii zolota // Sbornik statei Aktsionernaia kompaniia «Altynalmas», 2003. P. 25-35.
- [11] Burkurmanov B.B., Malimbaev M.S. Novyi metod desorbtsii zolota s anionitov, Promyshlennost' Kazakhstana, 2000. P. 74-75.
- [12] Plaksin I.N., Tetaru S.A. Gidrometallurgiiia s primeneniem ionitov. M.: Metallurgiiia, 1964. 282 p.
- [13] Vitkovskaia A.P., Kuznetsov V.N., Zaitseva V.N. Beskislotnaia regeneratsiia anionitov // Tsvetnyemetally. 1977. N 5. P. 77-80.
- [14] Katalog produktsii GP «Smoly». Ukrainskii proizvoditel' ionoobmennnykh smol, 2017.

Ш. Ч. Алтынбек^{1,2}, Л. С. Болотова², В. Mishra³, А. О. Байконурова¹

¹Қ. И. Сәтбаев атындағы Қазақ ұлттық техникалық зерттеу университеті, Алматы, Қазақстан,
²«ҚР МШКҚӨҰО» РМК Мемлекеттік өнеркәсіптік экология ғылыми-өндірістік бірлестігі филиалы
«Қазмеханообр», Алматы, Қазақстан,
³Вустер политехникалық институты, Вустер, АҚШ

**ПОЛИКОМПОНЕНТТИ АЛТЫНҚҰРАМДЫ ЕРІТІНДІЛЕРДЕН АЛЫНҒАН ШАЙЫРЛАРДАН
АЛТЫНДЫ ДЕСОРБЦИЯЛАУ ЖӘНЕ ШАЙЫРДЫ ҚАЛПЫНА КЕЛТІРУ БАҒЫТЫ БОЙЫНША
БІРІККЕН ТЕХНОЛГИЯСЫНДАМУ**

Аннотация. Алтынқұрамды кендерден алтынды АМ-2Б маркалы шайырынан десорбциялау және шайырды қайта өңдеудің біріккен технологиясын қолданудың негізгі технологиялық сұлбасы ұсынылған. Бұл сұлба алтынды десорбциялық өңдеуде қолданылатын екі дәстүрлі технологияны қамтиды.

Шайырлардан қоспа металдарды сілтілік роданидті ерітінділермен десорбциялау және алтынды қышқыл тиомочевинді ерітінділермен десорбциялауды қамтитын ұсынылған біріккен технологияны қолдану кезінде қоспа металдардың әрекеті зерттелді.

Зерттеулер алтынды десорбциялау және ион алмастырғыш шайырды қалпына келтіру бағытында ұсынылған аралас технология бойынша өткізілді. Келесі компоненттермен қаныққан ион алмастырғыш шайыр пайдаланылды, мг/г: Au – 2,6; Cu – 3,5; Zn – 1,3; Ni – 2,9; Co – 3,3. Қалпына келтірілген ион алмастырғыш шайырдың қалдық құрамы, мг/г: Au – 0,06; Cu – 0,02; Zn – 0,02; Ni – 0,01; Co – 1,2.

Қоспаметалдардың басым мөлшері мен алтынның аз мөлшері сілтілі роданидті ерітінділерді қолдану кезінде элюатқа өтетіні көрсетілді. Роданидті өңдеу кезінде элюаттағы металдардың құрамы, мг/л: Au – 14,66; Cu – 669,2; Zn – 222,1; Ni – 493,0; Co – 412,6. Ионит құрамындағы алтынның 98,67 % алтынқұрамды ерітінділерге өтеді, ал элюат құрамындағы алтынның құрамы 376,6 мг/л дейін барады.

Түйін сөздер: десорбциялау, біріккен технология, анион алмастырғыш шайыр, роданидті ерітінділер, қышқыл тиомочевинді ерітінділер.

Ш. Ч. Алтынбек^{1,2}, Л. С. Болотова², В. Mishra³, А. О. Байконурова¹

¹Казахский национальный исследовательский технический университет им. К. И. Сатпаева,
Алматы, Казахстан,

²Филиал РГП «НЦ КПМС РК» Государственное научно-производственное объединение
промышленной экологии «Казмеханобр», Алматы, Казахстан,

³Вустерский политехнический институт, Вустер, США

РАЗРАБОТКА ТЕХНОЛОГИИ РЕГЕНЕРАЦИИ ИОНООБМЕННОЙ СМОЛЫ МАРКИ АМ- 2Б В ПРОЦЕССЕ СОРБЦИОННОГО ИЗВЛЕЧЕНИЯ ЗОЛОТА ИЗ ПОЛИКОМПОНЕНТНЫХ ЗОЛОТОСОДЕРЖАЩИХ РАСТВОРОВ

Аннотация. Рассмотрена принципиальная технологическая схема десорбции золота и сопутствующих металлов-примесей из фазы смолы марки АМ-2Б, используемой при сорбционной переработке золотосодержащих руд. Предлагаемая комбинированная схема, предусматривающая применение двух традиционных независимых друг от друга способов элюирования золота, включает десорбцию металлов-примесей со смолы щелочными растворами роданида натрия, а золота – серноокислыми растворами тиомочевины.

Приведены результаты исследований элюирования золота и примесных металлов из анионита, насыщенного следующими компонентами, мг/г: Au – 2,6; Cu – 3,5; Zn – 1,3; Ni – 2,9; Co – 3,3. Показано, что основное количество металлов-примесей десорбируются со смолы при ее роданидной обработке, при этом переход золота в элюат незначителен. Состав элюата при роданидной обработке насыщенной смолы, мг/л: Au – 14,66; Cu – 669,2; Zn – 222,1; Ni – 493,0; Co – 412,6. Последующая обработка смолы серноокислыми растворами тиомочевины позволяет перевести в элюат 98,67 % золота от содержавшегося в ионите с небольшим количеством примесей. Полученные элюаты, содержащие ~ 377 мг/л золота, представляют собой целевые растворы для получения ценного металла.

Проведена регенерация ионита путем промывки водой и обработки щелочным раствором натрия для перевода ее в OH⁻ - форму, при которой осуществляется сорбция золота из цианидных растворов кучного.

Остаточные содержания компонентов в смоле после регенерации составили, мг/г: Au – 0,06; Cu – 0,02; Zn – 0,02; Ni – 0,01; Co – 1,2, что позволяет успешно использовать регенерированную смолу на следующей стадии сорбции.

Ключевые слова: элюирование, десорбция, комбинированная технология, анионит, роданидные растворы, кислые тиомочевинные растворы.

Information about the authors:

Altynbek Shynar Chaibekkizi – PhD student, Kazakh National Research Technical University named after K. I. Satpayev, Almaty, Kazakhstan; Improver of laboratory of noble metals, The Branch of the RSE «NC CPMS RK» State scientific-industrial association of industrial ecology «Kazmekhanobr», Altynbek.shinar@gmail.com

Bolotova Lyudmila Sergeevna – Candidate of Chemical Sciences, Head of the laboratory of noble metals, The Branch of the RSE «NC CPMS RK» State scientific-industrial association of industrial ecology «Kazmekhanobr», Almaty, Kazakhstan, L_bolotova@yahoo.com

Brajendra Mishra – Ph. D, professor, Worcester Polytechnic Institute, Worcester, Massachusetts, the USA, bmishra@wpi.edu

Baikonurova Aliya Omirkhanovna – Doctor of Technical Sciences, Professor, Kazakh National Research Technical University named after K. I. Satpayev, Almaty, Kazakhstan, a.baikonurova@yandex.kz

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

www.nauka-nanrk.kz

ISSN 2518-170X (Online), ISSN 2224-5278 (Print)

<http://geolog-technical.kz/index.php/kz/>

Верстка Д. Н. Калкабековой

Подписано в печать 14.05.2018.
Формат 70x881/8. Бумага офсетная. Печать – ризограф.
24,2 п.л. Тираж 300. Заказ 3.