

ISSN 2518-170X (Online),
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ
Қ. И. Сәтпаев атындағы Қазақ ұлттық техникалық зерттеу университеті

Х А Б А Р Л А Р Ы

ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН
Казакский национальный исследовательский
технический университет им. К. И. Сатпаева

NEWS

OF THE ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN
Kazakh national research technical university
named after K. I. Satpayev

**SERIES
OF GEOLOGY AND TECHNICAL SCIENCES**

3 (435)

MAY – JUNE 2019

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, NAS RK

NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.

Б а с р е д а к т о р ы
э. ғ. д., профессор, ҚР ҰҒА академигі

И.К. Бейсембетов

Бас редакторының орынбасары

Жолтаев Г.Ж. проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

Абаканов Т.Д. проф. (Қазақстан)
Абишева З.С. проф., академик (Қазақстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Әзірбайжан)
Бакиров А.Б. проф., (Қырғыстан)
Беспәев Х.А. проф. (Қазақстан)
Бишимбаев В.К. проф., академик (Қазақстан)
Буктуков Н.С. проф., академик (Қазақстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Тәжікстан)
Грэвис Р.М. проф. (АҚШ)
Ерғалиев Г.К. проф., академик (Қазақстан)
Жуков Н.М. проф. (Қазақстан)
Қожахметов С.М. проф., академик (Қазақстан)
Конторович А.Э. проф., академик (Ресей)
Курскеев А.К. проф., академик (Қазақстан)
Курчавов А.М. проф., (Ресей)
Медеу А.Р. проф., академик (Қазақстан)
Мұхамеджанов М.А. проф., корр.-мүшесі (Қазақстан)
Нигматова С.А. проф. (Қазақстан)
Оздоев С.М. проф., академик (Қазақстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Қазақстан)
Сейтов Н.С. проф., корр.-мүшесі (Қазақстан)
Сейтмуратова Э.Ю. проф., корр.-мүшесі (Қазақстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (АҚШ)
Штейнер М. проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология мен техникалық ғылымдар сериясы».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде
30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://www.geolog-technical.kz/index.php/en/>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2019

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыра көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «Аруна» ЖК, Алматы қ., Муратбаева көш., 75.

Г л а в н ы й р е д а к т о р
д. э. н., профессор, академик НАН РК

И. К. Бейсембетов

Заместитель главного редактора

Жолтаев Г.Ж. проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

Абаканов Т.Д. проф. (Казахстан)
Абишева З.С. проф., академик (Казахстан)
Агабеков В.Е. академик (Беларусь)
Алиев Т. проф., академик (Азербайджан)
Бакиров А.Б. проф., (Кыргызстан)
Беспаяев Х.А. проф. (Казахстан)
Бишимбаев В.К. проф., академик (Казахстан)
Буктуков Н.С. проф., академик (Казахстан)
Булат А.Ф. проф., академик (Украина)
Ганиев И.Н. проф., академик (Таджикистан)
Грэвис Р.М. проф. (США)
Ергалиев Г.К. проф., академик (Казахстан)
Жуков Н.М. проф. (Казахстан)
Кожаметов С.М. проф., академик (Казахстан)
Конторович А.Э. проф., академик (Россия)
Курскеев А.К. проф., академик (Казахстан)
Курчавов А.М. проф., (Россия)
Медеу А.Р. проф., академик (Казахстан)
Мухамеджанов М.А. проф., чл.-корр. (Казахстан)
Нигматова С.А. проф. (Казахстан)
Оздоев С.М. проф., академик (Казахстан)
Постолатий В. проф., академик (Молдова)
Ракишев Б.Р. проф., академик (Казахстан)
Сейтов Н.С. проф., чл.-корр. (Казахстан)
Сейтмуратова Э.Ю. проф., чл.-корр. (Казахстан)
Степанец В.Г. проф., (Германия)
Хамфери Дж.Д. проф. (США)
Штейнер М. проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы)

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год

Тираж: 300 экземпляров

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© Национальная академия наук Республики Казахстан, 2019

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: ИП «Аруна», г. Алматы, ул. Муратбаева, 75

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

I. K. Beisembetov

Deputy editor in chief

Zholtayev G.Zh. prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

Abakanov T.D. prof. (Kazakhstan)
Abisheva Z.S. prof., academician (Kazakhstan)
Agabekov V.Ye. academician (Belarus)
Aliyev T. prof., academician (Azerbaijan)
Bakirov A.B. prof., (Kyrgyzstan)
Bespayev Kh.A. prof. (Kazakhstan)
Bishimbayev V.K. prof., academician (Kazakhstan)
Buktukov N.S. prof., academician (Kazakhstan)
Bulat A.F. prof., academician (Ukraine)
Ganiyev I.N. prof., academician (Tadjikistan)
Gravis R.M. prof. (USA)
Yergaliev G.K. prof., academician (Kazakhstan)
Zhukov N.M. prof. (Kazakhstan)
Kozhakhmetov S.M. prof., academician (Kazakhstan)
Kontorovich A.Ye. prof., academician (Russia)
Kurskeyev A.K. prof., academician (Kazakhstan)
Kurchavov A.M. prof., (Russia)
Medeu A.R. prof., academician (Kazakhstan)
Muhamedzhanov M.A. prof., corr. member. (Kazakhstan)
Nigmatova S.A. prof. (Kazakhstan)
Ozdoev S.M. prof., academician (Kazakhstan)
Postolatii V. prof., academician (Moldova)
Rakishev B.R. prof., academician (Kazakhstan)
Seitov N.S. prof., corr. member. (Kazakhstan)
Seitmuratova Ye.U. prof., corr. member. (Kazakhstan)
Stepanets V.G. prof., (Germany)
Humphery G.D. prof. (USA)
Steiner M. prof. (Germany)

News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.

ISSN 2518-170X (Online),

ISSN 2224-5278 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty)

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010

Periodicity: 6 times a year

Circulation: 300 copies

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,
<http://nauka-nanrk.kz/geology-technical.kz>

© National Academy of Sciences of the Republic of Kazakhstan, 2019

Editorial address: Institute of Geological Sciences named after K.I. Satpayev
69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: ST "Aruna", 75, Muratbayev str, Almaty

NEWS

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

SERIES OF GEOLOGY AND TECHNICAL SCIENCES

ISSN 2224-5278

Volume 3, Number 435 (2019), 67 – 72

<https://doi.org/10.32014/2019.2518-170X.69>

UDC 691

B. T. Assakunova¹, M. A. Jussupova², G. R. Baimenova³, S. T. Kulshikova⁴

Kyrgyz State N. Issanov University of Construction, Transport and Architecture, Bishkek, Kyrgyzstan.

E-mail: Kafedra_pesmik@mail.ru, dzmahavat@gmail.com, gulnaz.baymenova@mail.ru, saule.kulshikova@mail.ru

**UTILIZATION OF HEAT POWER INDUSTRY WASTE
IN THE FORM OF BINDING COMPOSITE MATERIALS
IN KYRGYZSTAN**

Abstract. This paper discusses the urgent problem of expanding the raw material base of the construction industry using fuel slags in cements. The influence of various methods of preparation and introduction of fuel slags on the basic properties of composite cementing materials was evaluated. It is shown how the properties of the composite cement-slag binder vary depending on the application method and the activation degree of the slag.

Key words: technogenic raw material; ash and slag mix; mixing; grinding; composite binding material; glass phase; hydraulic activity; chemical and mineralogical composition; dispersability; water demand; strength.

One of the research priorities in the development of the Kyrgyz Republic is the rational use of natural resources.

For the construction industry, the most promising resource and energy saving solution is the integrated use of affordable, cheap local raw materials, which include industrial waste such as ash and slag of thermal power plants that are in huge quantities accumulated in dumps, causing significant damage to the environment.

If the use of ash and slag wastes (ASW) in the developed countries is 50-90%, in Central Asian countries this figure is less than 4%.

In the city of Bishkek a huge stockpiling of ash and slag wastes, as well as wet ash discharge, fly ash and sulfogypsum were accumulated, which are formed as a result of desulfurization of flue gases. Utilization of waste from thermal power plants is of considerable interest both in solving the environmental problem and for the economic efficiency of the enterprise.

The research aim: development of gypsum binders from waste from Bishkek TPP.

Materials and methods. Sulfogypsum, which is formed as a result of desulfurization of flue gases, is characterized by a specific surface area ($S = 2800-3000 \text{ cm}^2/\text{g}$); by the content of $\text{CaSO}_4 \cdot 2\text{H}_2\text{O} - 93-95\%$; $\text{CaCO}_3 - 1.6-1.7\%$; pH 4.5-9; $\rho_{\text{bulk}} - 520-530 \text{ kg}/\text{m}^3$; $\rho_{\text{true}} - 2.35-2.37 \text{ g}/\text{cm}^3$; $W = 20-27\%$. It can be attributed to high-quality gypsum raw materials of Class I and the production of gypsum binders on their basis is of undoubted interest.

The chemical composition of the HPP waste is given in the table 1.

Table 1 – Chemical composition of raw materials

| No. | Oxide content, % | | | | | | | | | |
|--------------------------|------------------|--------------------------------|--------------------------------|------|-------|------|-----------------|-------------------|------------------|--------|
| | SiO ₂ | Al ₂ O ₃ | Fe ₂ O ₃ | FeO | CaO | MgO | SO ₃ | Na ₂ O | K ₂ O | П.п.п. |
| Sulfogypsum | 0.09 | 0.23 | 0.36 | | 55.72 | 0.76 | 0.07 | – | – | 41.55 |
| Fly ash | 55.4 | 23.15 | 4.30 | | 2.18 | 1.35 | 1.08 | 1.72 | 2.08 | 4.94 |
| Wet ash discharge | 52.0 | 21.58 | 0.97 | 0.97 | 6.47 | 1.14 | 0.21 | 0.9 | 1.7 | 12.13 |
| Cement of KCSP | 22.44 | 4.65 | 4.11 | | 65.59 | 1.75 | 0.33 | – | – | 0.2 |
| Sand from Vassiliyevskiy | 68.72 | 14.21 | 3.24 | | 3.25 | 2.68 | 2.61 | – | – | |

The laboratory of Kyrgyz State N. Issanov University of construction, transport and architecture obtained the construction gypsum based on sulfogypsum. Gypsum was cooked at a temperature of 150 °C with an exposure time of 90 minutes at the indicated temperature; time of temperature rise - 40 min.

The test of construction gypsum was carried out in accordance with GOST (National Standards) 23789-79. According to physical and mechanical properties, the construction gypsum from sulfogypsum corresponds to grade G-4-B-III (table 2).

Table 2 – Physical and mechanical properties of the construction gypsum from sulfogypsum

| Temperature of burning, °C | Grinding fineness 02, % | Standard consistency, % | Setting time, min | | Sample density, g/cm ³ | Strength limit after 2 hours in MPa | |
|----------------------------|-------------------------|-------------------------|-------------------|-----|-----------------------------------|-------------------------------------|-------------------|
| | | | start | end | | R _{flex} | R _{rupt} |
| 150 | 0 | 68 | 12 | 16 | 1.64 | 1.86 | 4.2 |

Since the construction gypsum based on sulfogypsum has a low resistance to environmental influences and a sharp decrease in strength in moistening, the fillers and additives were modified to improve the water resistance of gypsum binders. As a basic component of the binder, G-4 gypsum, obtained from sulfogypsum, was used.

Ash of Bishkek TPP with a specific surface of $S_{spec} = 350-400 \text{ m}^2/\text{kg}$ was used as a filler in gypsum binders. They have pozzolanic activity as they contain clay-firing products: amorphous clayey material such as metakaolinite, amorphous SiO_2 , Al_2O_3 , Fe_2O_3 and aluminosilicate glass. High hydraulic activity of the amorphous clay substance is associated with its high specific surface, which is created as a result of the decomposition ($\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2$) into amorphous alumina and silica.

The thermally treated quartz which is contained in the ash, due to increased solubility, interacts with calcium hydroxide. The higher the concentration of hydroxide in the liquid phase is, the more active the ash is.

According to the characteristics of the ash activity modulus $M_0 = \text{CaO} + \text{MgO} / \text{SiO}_2 + \text{Al}_2\text{O}_3 = 0.045$, the alumina module $p = \text{Al}_2\text{O}_3 / \text{Fe}_2\text{O}_3$, the modulus of activity $M_a = \text{Al}_2\text{O}_3 / \text{SiO}_2 = 0.41$, it can be inferred that for $M_0 < 1$, the ash has increased activity. In this case, the higher the activity modulus is, the faster the ash hardens in the grinded state. An important feature of ash is its high intensive grinding capacity.

Lime of the 1st grade and portland cement were used to activate low-calcium acid ash. Lime is characterized by the content of $\text{CaO} + \text{MgO}$ within 92% and the content of unhydrated, unslaked particles is 0.5%.

The addition of K_2SO_4 together with lime in the composition of the binder causes high concentrations of potassium and sulfate ions. Calcium sulphate and potassium sulfate can be isolated as a double salt, as a result of recrystallization of which the spatial structure of $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ is formed. Phase transformations of crystalline hydrate new-growths stimulate a change in the kinetics of expansion of the system and a general decrease in deformation.

Research findings and their discussion. During the research, a 4-factor experiment was carried out according to the B_4 plan, consisting of 24 experimental points. Each of the prescription factors performs a certain role in the formation of the structure of the gypsum binder and changed at three levels: X_1 - ash (0..15 ... 30%); X_2 -lime (0 ... 2 ... 4%); X_3 - K_2SO_4 (0 ... 1.5 ... 3.0%); X_4 -cement (0 ... 5 ... 10%); the rest is gypsum-waste of TPP.

As the main parameters of gypsum binder are selected: Y_1 - Normal thickness, Y_2 initial setting period, min .; %; Y_3 - end of setting, min .; Y_4 - R_{bend} , MPa; Y_5 - R_{compress} , MPa; Y_6 - R_{compress} of wet, MPa; the softening factor is Y_7 .

Optimization criteria $K_p \geq 0,6$ and strength $R_{\text{dry compress}} \geq 10 \text{ MPa}$.

Table 4 – Experiment plan B₄

| No. | Encoded variables | | | | Experiment results | | | | | | | |
|-----|-------------------|----------------|----------------|----------------|----------------------------|--|--|--|---|---|----------------------------------|---------------------------|
| | x ₁ | x ₂ | x ₃ | x ₄ | Y ₁ HF, % | Y ₂ Average setting start (min) | Y ₃ Average set end:min | Y ₄ R _{bend} . MPa | Y ₅ R _{dry compr} MPa | Y ₆ R _{wet compr} . MPa | Y ₇ K _p | Y ₈ W, % |
| 1 | + | + | + | + | 68 | 6.21 | 7.75 | 1.13 | 5.68 | 2.89 | 0.51 | 34.5 |
| 2 | + | + | + | - | 65 | 6.33 | 8.0 | 1.25 | 5.76 | 2.76 | 0.48 | 37.9 |
| 3 | + | + | - | + | 67 | 14.55 | 20.25 | 1.67 | 6.88 | 3.50 | 0.51 | 36.9 |
| 4 | + | + | - | - | 67 | 19.75 | 29.25 | 1.97 | 5.88 | 2.64 | 0.45 | 38.8 |
| 5 | + | - | + | + | 70 | 2.81 | 3.60 | 1.37 | 5.28 | 2.48 | 0.47 | 42.2 |
| 6 | + | - | + | - | 68 | 2.25 | 2.83 | 1.33 | 5.12 | 1.28 | 0.25 | 43.9 |
| 7 | + | - | - | + | 67 | 10.16 | 17.58 | 2.55 | 7.68 | 4.37 | 0.57 | 31.0 |
| 8 | + | - | - | - | 67 | 10.75 | 19.16 | 2.47 | 7.0 | 3.92 | 0.56 | 30.8 |
| 9 | + | + | + | + | 67 | 5.75 | 7.41 | 2.51 | 10.52 | 5.04 | 0.48 | 34.9 |
| 10 | - | + | + | - | 68 | 5.75 | 7.48 | 2.16 | 8.72 | 3.31 | 0.38 | 34.9 |
| 11 | - | + | - | + | 70 | 15.16 | 19.50 | 2.8 | 10.26 | 4.51 | 0.44 | 38.2 |
| 12 | - | + | - | - | 67 | 13.50 | 19.91 | 2.93 | 13.24 | 6.22 | 0.47 | 35.4 |
| 13 | - | - | + | + | 67 | 2.08 | 3.58 | 2.45 | 10.44 | 5.01 | 0.48 | 35.5 |
| 14 | + | - | + | - | 65 | 2.20 | 2.95 | 2.65 | 8.84 | 4.98 | 0.46 | 43.1 |
| 15 | - | - | - | + | 63 | 8.83 | 15.08 | 3.32 | 10.7 | 6.54 | 0.61 | 33.8 |
| 16 | - | - | - | - | 60 | 12.66 | 18.83 | 2.81 | 8.56 | 4.24 | 0.48 | 39.6 |
| 17 | + | 0 | 0 | 0 | 70 | 4.83 | 8.75 | 1.69 | 8.6 | 5.16 | 0.6 | 32.3 |
| 18 | - | 0 | 0 | 0 | 62 | 6.50 | 11.10 | 2.64 | 10.32 | 5.26 | 0.51 | 34.0 |
| 19 | 0 | + | 0 | 0 | 63 | 8.86 | 13.93 | 1.84 | 8.88 | 4.97 | 0.56 | 36.8 |
| 20 | 0 | - | 0 | 0 | 63 | 3.25 | 4.58 | 2.35 | 22.8 | 14.82 | 0.65 | 34.2 |
| 21 | 0 | 0 | + | 0 | 68 | 5.03 | 6.11 | 1.9 | 8.68 | 5.2 | 0.60 | 35.9 |
| 22 | 0 | 0 | - | 0 | 70 | 14.08 | 22.18 | 2.65 | 8.72 | 5.23 | 0.60 | 40.6 |
| 23 | 0 | 0 | 0 | + | 68 | 6.86 | 8.58 | 2.28 | 10.12 | 6.27 | 0.62 | 39.5 |
| 24 | 0 | 0 | 0 | - | 67 | 6.83 | 8.33 | 2.29 | 11.0 | 6.71 | 0.61 | 32.3 |

Based on the results of the experiment, specifying the average error S and significance level $\alpha = 0.01$, the mathematical models of the properties of the gypsum binder were obtained.

Y₂- Start of the setting, min.

$$(Y_2) = 6.48 + 0.29x_1 - 0.82x_1^2 + 0.41x_1x_2 - 0.20x_1x_3 - 0.19x_1x_4 + 2.27x_2 - 0.43x_2^2 - 0.37x_2x_3 - 0.02x_2x_4 - 4.502x_3 + 3.072x_3^2 + 0.517x_3x_4 - 0.423x_4 + 0.362x_4^2 \quad (1)$$

Y₃- End of setting, min.

$$(Y_3) = 9.694 + 0.629x_1 + 0.231x_1^2 + 0.514x_1x_2 - 0.76x_1x_3 - 0.404x_1x_4 + 2.516x_2 - 0.39x_2^2 - 0.036x_2x_3 - 0.363x_2x_4 - 7.335x_3 + 4.451x_3^2 + 0.989x_3x_4 - 0.745x_4 - 1.239x_4^2 \quad (2)$$

Y₄- R_{bend}. Bending resistance, MPa

$$(Y_4) = 2.209 + 0.491x_1 - 0.054x_1x_2 - 0.093x_1x_3 - 0.052x_1x_4 - 0.0169x_2 + 0.064x_2x_3 - 0.357x_3 - 0.006x_3x_4 \quad (3)$$

Y_5 - $R_{dry\ compr.}$ MPa

$$(Y_5) = 12.133 - 1.873 x_1 - 2.673 x_1^2 - 0.317 x_1 x_2 - 0.085 x_1 x_3 - 0.05 x_1 x_4 - 0.589 x_2 + 3.707 x_2^2 - 0.082 x_2 x_3 - 0.302 x_2 x_4 - 0.549 x_3 - 3.433 x_3^2 + 0.165 x_3 x_4 + 0.191 x_4 - 1.573 x_4^2 \quad (4)$$

Y_7 - K_{soft} - softening factor

$$(Y_7) = 0.633 + 0.005 x_1 - 0.078 x_1^2 + 0.022 x_1 x_2 - 0.011 x_1 x_3 + 0.006 x_1 x_4 - 0.014 x_2 - 0.028 x_2^2 + 0.034 x_2 x_3 - 0.014 x_2 x_4 - 0.032 x_3 - 0.033 x_3^2 + 0.012 x_3 x_4 + 0.031 x_4 - 0.018 x_4^2 \quad (5)$$

A preliminary analysis of the ES coefficients of the models (1, 2) of the setting time of the composite gypsum binder showed that the setting time is significantly accelerated with the addition of K_2SO_4 , which indicates the crystallization effect. So for model (1) the setting start, the linear coefficient at factor x_3 was $b_3 = -4.502$. For the model (2), the end-of-setting, the linear effect is $b_3 = -7.335$.

Linear effects at the factor x_2 (lime) indicate an increase at the start and end of the setting of the gypsum binder. For the model (1), $b_2 = + 2.271$, and for the model (2) $b_2 = + 2.516$, because lime reduces the solubility of gypsum, thereby prolonging the setting time.

The presence of ash (x_1) and cement (x_4) does not significantly affect the setting time of the gypsum binder ($b_1 = 0.289$ and $b_4 = -0.423$) and ($b_1 = 0.629$ and $b_4 = -0.745$).

Analysis of flexural and compressive strength models of gypsum binder (3, 4) showed that the presence of ash (x_1) and cement (x_4) should be at the optimal level ($b_{11} = -2.673$) and ($b_{44} = -1.573$). Their maximum content leads to a large utilization of ash, but results in a decrease in the strength of the binder. Increasing the amount of cement is not advisable, because it increases the amount of ettringite, which is formed during the hydration of cement. The content of lime additives (x_2) and K_2SO_4 (x_3) should be optimized, as can be seen from the quadratic effects ($b_{22} = 3.707$ и $b_{33} = -3.433$).


The K_{soft} factor of the softening agent (Y_7) of the gypsum binder is within the permissible range of $K_{soft} \geq 0.6$, provided that there is an ash additive ($b_1 = 0.005$), but in the optimal amount ($b_{11} = -0.078$). This fact shows the formation of insoluble compounds, as a result of the interaction of ash with calcium hydroxide, which contribute to an increase in water resistance. The optimal cement content also provides ($b_{44} = -0.018$) an increase in the water resistance of the gypsum binder ($b_4 = + 0.031$). To ensure the required K_{soft} , the lime (x_2) and K_2SO_4 (x_3) content is a prerequisite and depends on the amount of ash ($b_{12} = 0.022$, $b_{13} = -0.011$, $b_{14} = + 0.006$).

The softening coefficient of samples from gypsum as seen from the results of the experiment for all points of the plan varies between $0.25 \leq K_{soft} \leq 0.65$. According to the optimization conditions, $K_{soft} > 0.6$ is achieved if the optimum formulation of the constituent components is fulfilled: the amount of ash $X_1 = 15\%$, lime $X_2 = 1.5 \dots 2\%$, K_2SO_4 $X_3 = 1 \dots 1.5\%$, cement $X_4 = 1.5 \dots 3.0\%$.

In figure, it is clearly possible to observe an area where an increased value of the coefficient $K_{soft} > 0.6$ (an unpainted zone) is provided. Here it is necessary to adhere to the formula mentioned above.

Thus, studies have shown the utilization possibility of the ash in gypsum binders while maintaining the required quality indicators. Moreover, with the optimal amount of additive components, the strength characteristics and the softening factor increase.

To obtain waterproof gypsum binders with $K_{soft} \geq 0.6$ and strength $R_{dry\ compr.} \geq 10$ MPa, the following formula is recommended: fly ash 15 ... 22%; lime 1.5 ... 2%; cement 1.5% and K_2SO_4 1.5%.

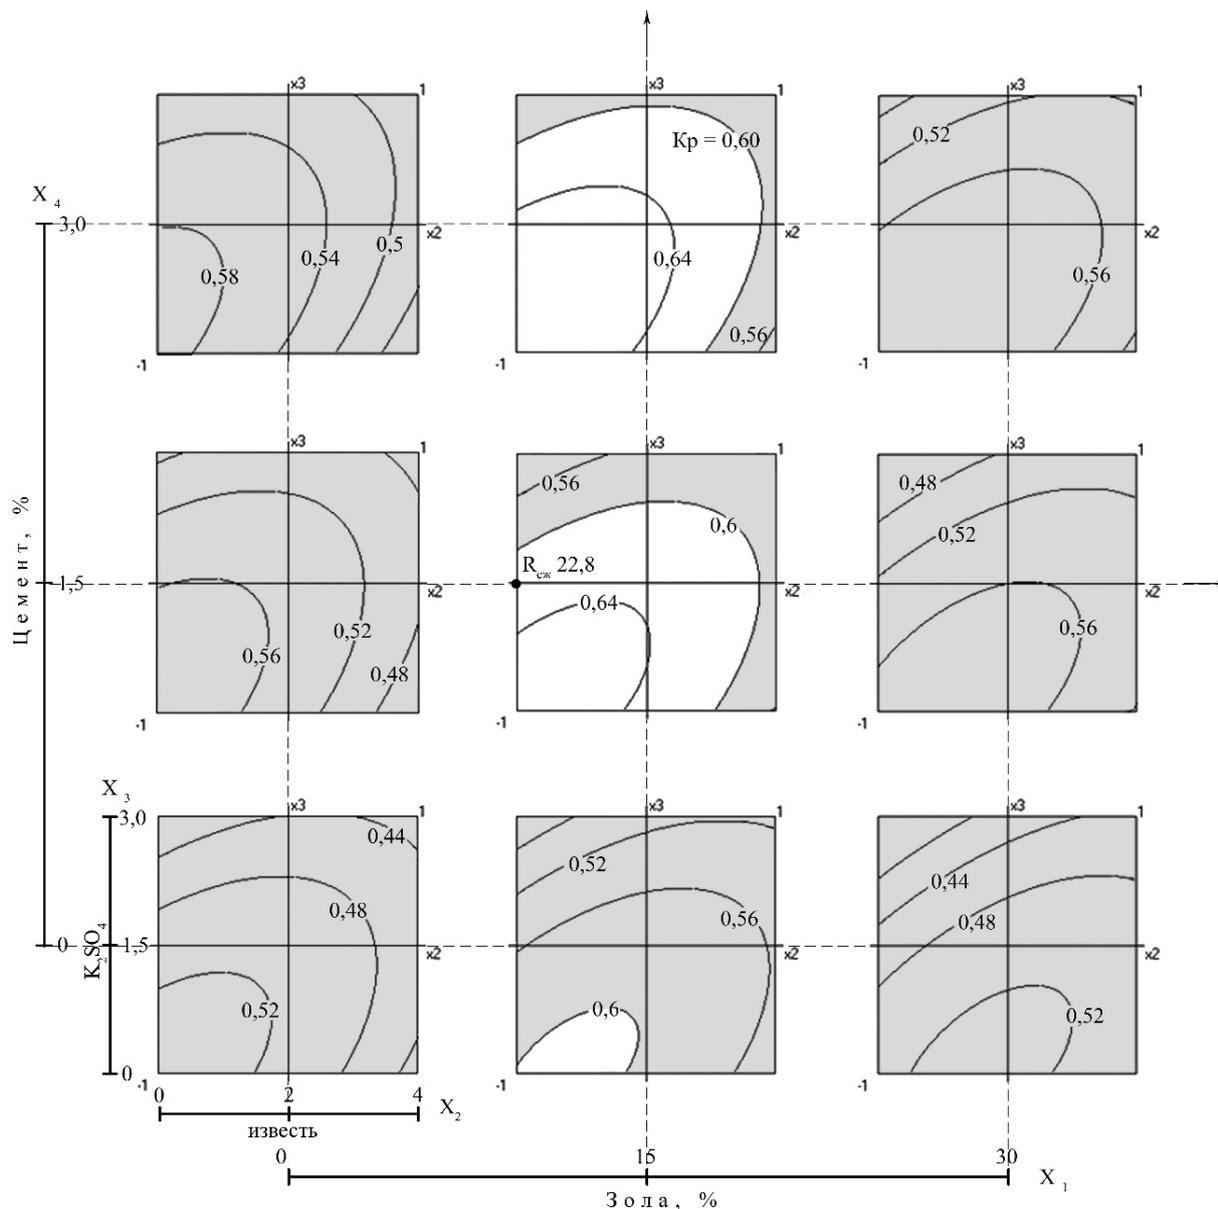

The isolines of the softening coefficient of samples from gypsum $Y_7(K_{\text{soft}}) = f(x_2, x_3)$ in nine points of the factor space x_1 and x_4

Conclusion:

- Sulphogypsum was obtained at the Bishkek TPP by desulfurizing industrial gases, which can be attributed to gypsum raw materials of grade I;

- Construction gypsum G4-B-III was obtained on the basis of sulfogypsum;

- To increase the water resistance of gypsum binders the experimental-statistical modeling has been conducted which revealed that the use of fly ash as a filler together with lime and K_2SO_4 promotes the regulation of the setting time (elongation), which is important in the technological plan. Growth of the K_{soft} and of the water absorption of gypsum stone shows an increase in water resistance of gypsum products due to the formation of insoluble hydrosilicates in the process of hydration of ash and clinker minerals of cement with lime.

- Waterproof modified gypsum binders can find application for the manufacture of products for various purposes.

- Within the framework of one enterprise, ash and sulfogypsum are recycled, which is economically feasible.

Б. Т. Ассакунова¹, М. А. Джусупова², Г. Р. Байменова³, С. Т. Кульшикова⁴

Н. Исанов атындағы Қырғыз мемлекеттік құрылыс, көлік және сәулет университеті, Бішкек, Қырғызстан

ҚЫРҒЫЗСТАННЫҢ ЖЫЛУ ЭНЕРГЕТИКАСЫНЫҢ ҚАЛДЫҚТАРЫН КОМПОЗИЦИЯЛЫҚ БАЙЛАНЫСТЫРҒЫШ ЗАТТАРДА ПАЙДАЛАНУ

Аннотация. Мақалада цементтердегі отын шлактарын пайдалана отырып, құрылыс индустриясының шикізат базасын кеңейтудің өзекті мәселесі туралы айтылады. Композициялық байланыстырғыштардың негізгі сипаттарына отын шлактарын дайындау және енгізу түрлерінің тәсілдеріне баға жасалды. Шлақты енгізу тәсілі мен белсендіру дәрежесіне қарай композициялық цементті-шлакты байланыстырғыштың сипатының қалай өзгеретіндігі анықталды.

Түйін сөздер: техногендік шикізат; күл қоспасы; араластыру; ұсақтау; композициялық байланыстырғыш; шыны фазасы; гидравликалық белсенділік; химиялық-минералдық құрам; дисперсия, су сұранысы, төзімділік.

Б. Т. Ассакунова¹, М. А. Джусупова², Г. Р. Байменова³, С. Т. Кульшикова⁴

Кыргызский государственный университет строительства, транспорта и архитектуры им. Н. Исанова,
Бишкек, Кыргызстан

ИСПОЛЬЗОВАНИЕ ОТХОДОВ ТЕПЛОЭНЕРГЕТИКИ КЫРГЫЗСТАНА В КОМПОЗИЦИОННЫХ ВЯЖУЩИХ ВЕЩЕСТВАХ

Аннотация. Статья посвящена актуальной проблеме расширения сырьевой базы строительной индустрии за счет использования топливных шлаков в цементах. Проведена оценка влияния различных способов подготовки и введения топливных шлаков на основные свойства композиционных вяжущих. Показано как изменяются свойства композиционного цементно-шлакового вяжущего в зависимости от способа введения и степени активизации шлака.

Ключевые слова: техногенное сырье; золошлаковая смесь; смешение; измельчение; композиционное вяжущее; стеклофаза; гидравлическая активность; химико-минералогический состав; дисперсность, водопотребность, прочность.

Information about authors:

Assakunova B.T., Kyrgyz State N. Issanov University of Construction, Transport and Architecture, Bishkek, Kyrgyzstan; Kafedra_pesmik@mail.ru; <https://orcid.org/0000-0002-1713-2793>

Jussupova M.A., Kyrgyz State N. Issanov University of Construction, Transport and Architecture, Bishkek, Kyrgyzstan; dzmahavat@gmail.com; <https://orcid.org/0000-0002-2873-9355>

Baimenova G.R., Kyrgyz State N. Issanov University of Construction, Transport and Architecture, Bishkek, Kyrgyzstan; gulnaz.baimenova@mail.ru; <https://orcid.org/0000-0003-3959-5374>

Kulshikova S.T., Kyrgyz State N. Issanov University of Construction, Transport and Architecture, Bishkek, Kyrgyzstan; saule.kulshikova@mail.ru; <https://orcid.org/0000-0001-5412-8454>

REFERENCES

- [1] Alaskhanov A.Kh., Murtazaev S.-A.Yu., Chernysheva N.V. (2013). Use of ash and slag mixtures of thermal power plants for the production of composite gypsum binders // *Ecology and industry of Russia*. July 2013. P. 26-29.
- [2] Feronkaya A.V. (2008). Gypsum in low-height construction // Under the general ed. A. V. Feronkaya. M.: ASV Publishing House, 2008. 240 p. M.: ASB, 2008. 240 p.
- [3] Dvorkin L.I., Dworkin O.L. (2007). Building materials from industrial waste. Rostov-na-Donu: Phoenix, 2007. 368 p.
- [4] Kokubu M. (1972). Ash and ash cements // *Proceedings of the International Congress on Chemistry of Cement*. M., 1972.
- [5] Koroviakov V.F. (2005). Increase of water resistance of gypsum waterproof binders and expansion of their application areas // *Building materials, equipment, technologies of the XXI century*, 2005. N 3. P. 14-17.
- [6] Ratinov V.R. (1984), doctor of chemical sciences (MADI), Ivanicii V.V., candidate of technical sciences, D.I. Stekaov, engineer. (P.P. Budnikov SRI - VNIИstrom). *Building materials*. November 1984. N 11(359).
- [7] Canadian J. // *Civil Engineering*. 1987. Va: 14. N 5. P. 667- 682.
- [8] Wirsching F. (1983). *Chemische Technologie*. Band 3. Gips. Carl Hanser Verlag München, Wien, 1983.
- [9] FGD Gypsum: quality criteria and analysis methods // www.eurogypsum.org

**Publication Ethics and Publication Malpractice
in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

www.nauka-nanrk.kz

ISSN 2518-170X (Online), ISSN 2224-5278 (Print)

<http://www.geolog-technical.kz/index.php/en/>

Верстка Д. Н. Калкабековой

Подписано в печать 11.06.2019.
Формат 70x881/8. Бумага офсетная. Печать – ризограф.
15,7 п.л. Тираж 300. Заказ 3.