

ISSN 2518-170X (Online),  
ISSN 2224-5278 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ  
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ  
Satbayev University

# Х А Б А Р Л А Р Ы

---

---

## ИЗВЕСТИЯ

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК  
РЕСПУБЛИКИ КАЗАХСТАН  
Satbayev University

## NEWS

OF THE ACADEMY OF SCIENCES  
OF THE REPUBLIC OF KAZAKHSTAN  
Satbayev University

**SERIES  
OF GEOLOGY AND TECHNICAL SCIENCES**

**2 (440)**

**MARCH – APRIL 2020**

THE JOURNAL WAS FOUNDED IN 1940

PUBLISHED 6 TIMES A YEAR

ALMATY, KAZAKHSTAN

---

---

*NAS RK is pleased to announce that News of NAS RK. Series of geology and technical sciences scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of News of NAS RK. Series of geology and technical sciences in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential content of geology and engineering sciences to our community.*

*Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді геология және техникалық ғылымдар бойынша контентке адалдығымызды білдіреді.*

*НАН РК сообщает, что научный журнал «Известия НАН РК. Серия геологии и технических наук» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Известия НАН РК. Серия геологии и технических наук в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному контенту по геологии и техническим наукам для нашего сообщества.*

Б а с р е д а к т о р ы  
э. ғ. д., профессор, ҚР ҰҒА академигі

**И.К. Бейсембетов**

Бас редакторының орынбасары

**Жолтаев Г.Ж.** проф., геол.-мин. ғ. докторы

Р е д а к ц и я а л қ а с ы:

**Абаканов Т.Д.** проф. (Қазақстан)  
**Абишева З.С.** проф., академик (Қазақстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Әзірбайжан)  
**Бакиров А.Б.** проф., (Қырғызстан)  
**Беспәев Х.А.** проф. (Қазақстан)  
**Бишимбаев В.К.** проф., академик (Қазақстан)  
**Буктуков Н.С.** проф., академик (Қазақстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Тәжікстан)  
**Грэвис Р.М.** проф. (АҚШ)  
**Ерғалиев Г.К.** проф., академик (Қазақстан)  
**Жуков Н.М.** проф. (Қазақстан)  
**Қожахметов С.М.** проф., академик (Қазақстан)  
**Конторович А.Э.** проф., академик (Ресей)  
**Курскеев А.К.** проф., академик (Қазақстан)  
**Курчавов А.М.** проф., (Ресей)  
**Медеу А.Р.** проф., академик (Қазақстан)  
**Мұхамеджанов М.А.** проф., корр.-мүшесі (Қазақстан)  
**Нигматова С.А.** проф. (Қазақстан)  
**Оздоев С.М.** проф., академик (Қазақстан)  
**Постолатий В.** проф., академик (Молдова)  
**Ракишев Б.Р.** проф., академик (Қазақстан)  
**Сейтов Н.С.** проф., корр.-мүшесі (Қазақстан)  
**Сейтмуратова Э.Ю.** проф., корр.-мүшесі (Қазақстан)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (АҚШ)  
**Штейнер М.** проф. (Германия)

«ҚР ҰҒА Хабарлары. Геология және техникалық ғылымдар сериясы».

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы» РҚБ (Алматы қ.).

Қазақстан республикасының Мәдениет пен ақпарат министрлігінің Ақпарат және мұрағат комитетінде 30.04.2010 ж. берілген №10892-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Мерзімділігі: жылына 6 рет.

Тиражы: 300 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,  
<http://www.geolog-technical.kz/index.php/en/>

---

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2020

Редакцияның Қазақстан, 050010, Алматы қ., Қабанбай батыр көш., 69а.

мекенжайы: Қ. И. Сәтбаев атындағы геология ғылымдар институты, 334 бөлме. Тел.: 291-59-38.

Типографияның мекенжайы: «NurNaz GRACE», Алматы қ., Рысқұлов көш., 103.

Г л а в н ы й р е д а к т о р  
д. э. н., профессор, академик НАН РК

**И. К. Бейсембетов**

Заместитель главного редактора

**Жолтаев Г.Ж.** проф., доктор геол.-мин. наук

Р е д а к ц и о н н а я к о л л е г и я:

**Абаканов Т.Д.** проф. (Казахстан)  
**Абишева З.С.** проф., академик (Казахстан)  
**Агабеков В.Е.** академик (Беларусь)  
**Алиев Т.** проф., академик (Азербайджан)  
**Бакиров А.Б.** проф., (Кыргызстан)  
**Беспаяев Х.А.** проф. (Казахстан)  
**Бишимбаев В.К.** проф., академик (Казахстан)  
**Буктуков Н.С.** проф., академик (Казахстан)  
**Булат А.Ф.** проф., академик (Украина)  
**Ганиев И.Н.** проф., академик (Таджикистан)  
**Грэвис Р.М.** проф. (США)  
**Ергалиев Г.К.** проф., академик (Казахстан)  
**Жуков Н.М.** проф. (Казахстан)  
**Кожаметов С.М.** проф., академик (Казахстан)  
**Конторович А.Э.** проф., академик (Россия)  
**Курскеев А.К.** проф., академик (Казахстан)  
**Курчавов А.М.** проф., (Россия)  
**Медеу А.Р.** проф., академик (Казахстан)  
**Мухамеджанов М.А.** проф., чл.-корр. (Казахстан)  
**Нигматова С.А.** проф. (Казахстан)  
**Оздоев С.М.** проф., академик (Казахстан)  
**Постолатий В.** проф., академик (Молдова)  
**Ракишев Б.Р.** проф., академик (Казахстан)  
**Сейтов Н.С.** проф., чл.-корр. (Казахстан)  
**Сейтмуратова Э.Ю.** проф., чл.-корр. (Казахстан)  
**Степанец В.Г.** проф., (Германия)  
**Хамфери Дж.Д.** проф. (США)  
**Штейнер М.** проф. (Германия)

«Известия НАН РК. Серия геологии и технических наук».

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Собственник: Республиканское общественное объединение «Национальная академия наук Республики Казахстан (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации и архивов Министерства культуры и информации Республики Казахстан №10892-Ж, выданное 30.04.2010 г.

Периодичность: 6 раз в год.

Тираж: 300 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел.: 272-13-19, 272-13-18,  
<http://www.geolog-technical.kz/index.php/en/>

---

© Национальная академия наук Республики Казахстан, 2020

Адрес редакции: Казахстан, 050010, г. Алматы, ул. Кабанбай батыра, 69а.

Институт геологических наук им. К. И. Сатпаева, комната 334. Тел.: 291-59-38.

Адрес типографии: «NurNaz GRACE», г. Алматы, ул. Рыскулова, 103.

E d i t o r i n c h i e f

doctor of Economics, professor, academician of NAS RK

**I. K. Beisembetov**

Deputy editor in chief

**Zholtayev G.Zh.** prof., dr. geol-min. sc.

E d i t o r i a l b o a r d:

**Abakanov T.D.** prof. (Kazakhstan)  
**Abisheva Z.S.** prof., academician (Kazakhstan)  
**Agabekov V.Ye.** academician (Belarus)  
**Aliyev T.** prof., academician (Azerbaijan)  
**Bakirov A.B.** prof., (Kyrgyzstan)  
**Bespayev Kh.A.** prof. (Kazakhstan)  
**Bishimbayev V.K.** prof., academician (Kazakhstan)  
**Buktukov N.S.** prof., academician (Kazakhstan)  
**Bulat A.F.** prof., academician (Ukraine)  
**Ganiyev I.N.** prof., academician (Tadjikistan)  
**Gravis R.M.** prof. (USA)  
**Yergaliev G.K.** prof., academician (Kazakhstan)  
**Zhukov N.M.** prof. (Kazakhstan)  
**Kozhakhmetov S.M.** prof., academician (Kazakhstan)  
**Kontorovich A.Ye.** prof., academician (Russia)  
**Kurskeyev A.K.** prof., academician (Kazakhstan)  
**Kurchavov A.M.** prof., (Russia)  
**Medeu A.R.** prof., academician (Kazakhstan)  
**Muhamedzhanov M.A.** prof., corr. member. (Kazakhstan)  
**Nigmatova S.A.** prof. (Kazakhstan)  
**Ozdoyev S.M.** prof., academician (Kazakhstan)  
**Postolatii V.** prof., academician (Moldova)  
**Rakishev B.R.** prof., academician (Kazakhstan)  
**Seitov N.S.** prof., corr. member. (Kazakhstan)  
**Seitmuratova Ye.U.** prof., corr. member. (Kazakhstan)  
**Stepanets V.G.** prof., (Germany)  
**Humphery G.D.** prof. (USA)  
**Steiner M.** prof. (Germany)

**News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technology sciences.**

**ISSN 2518-170X (Online),**

**ISSN 2224-5278 (Print)**

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty).

The certificate of registration of a periodic printed publication in the Committee of information and archives of the Ministry of culture and information of the Republic of Kazakhstan N 10892-Ж, issued 30.04.2010.

Periodicity: 6 times a year.

Circulation: 300 copies.

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,

<http://www.geolog-technical.kz/index.php/en/>

---

© National Academy of Sciences of the Republic of Kazakhstan, 2020

Editorial address: Institute of Geological Sciences named after K.I. Satpayev

69a, Kabanbai batyr str., of. 334, Almaty, 050010, Kazakhstan, tel.: 291-59-38.

Address of printing house: «NurNaz GRACE», 103, Ryskulov str, Almaty.

**NEWS**

OF THE NATIONAL ACADEMY OF SCIENCES OF THE REPUBLIC OF KAZAKHSTAN

**SERIES OF GEOLOGY AND TECHNICAL SCIENCES**

ISSN 2224-5278

Volume 2, Number 440 (2020), 187 – 197

<https://doi.org/10.32014/2020.2518-170X.47>

UDC 625.855.52

MRNTI:

**B. M. Khroustalev<sup>1,4</sup>, T. Liu<sup>1,2,3</sup>, A. V. Busel<sup>1,5</sup>, Zh. Li<sup>1,3</sup>,  
U. A. Veranko<sup>1,4</sup>, V. V. Zankavich<sup>1</sup>, B. Shang<sup>2,3</sup>**

<sup>1</sup>Henan Gaoyuan highway maintenance technology Co., Ltd  
(Henan center for outstanding overseas scientists), Xinxiang, China;

<sup>2</sup>National engineering laboratory for highway maintenance equipment, Xinxiang, China;

<sup>3</sup>Henan provincial key laboratory of highway detection and maintenance, Xinxiang, China;

<sup>4</sup>Science and technology park of Belarusian national technical university "Polytechnic", Minsk, Belarus;

<sup>5</sup>State enterprise "Belarusian road scientific and research institute «BeldorNII", Minsk, Belarus

E-mail: post@park.bntu.by, verenko.vladimir@gmail.com, liutingguo@chngaoyuan.com,  
bulex@tut.by, vitali.zankavich@chngaoyuan.com, lizhongyu@chngaoyuan.com, iver-sb@163.com

## **ESTIMATION AND METHODS OF PREDICTION FOR THE STRUCTURAL AND MECHANICAL PROPERTIES OF RAP-COMPOSITES**

**Abstract.** This article presents the study results of the processes of structure formation and analysis of the methodological evaluation features of strength and deformation properties of RAP-composites. New materials necessitate studying the peculiarities of their behavior in the temperature-time field in order to develop objective technical requirements for their physical and mechanical characteristics that allow them to provide the required values of strength and reliability.

The classical method of applying the temperature-time analogy is valid in the linear domain for the analysis of relaxation curves at low levels of deformation or creep curves at low stresses. This thesis does not allow this theory to be used for the analysis of strength properties and other characteristics associated with the process of destruction of the composite material. Concretes of composite structure containing thermodynamically incompatible binders have nonlinear viscoelasticity and are thermorheologically complex. For composite materials a reduction factor (the amount of displacement curves along the time or deformation speed axis) depends not only on temperature but also material properties, and stress state. This is due to the peculiarities of the structure of composite materials as a system with a complex set of elastic and viscous bonds, and therefore the reduction coefficient depends on the number of elastic bonds involved in the deformation process.

The research is based on the principles of temperature-structural analogy, allowing predicting the properties of composites on organo-hydraulic binders. This makes possible directionally to design a cold mix and to determine the way of reaching a required materials property for construction of different layers of pavement.

The proposed methodological principles of design are based on the determination of the optimal ratio of elastic and viscous bonds, considering the properties of RAP and the amount of cement. The use of this approach allows evaluating the potential maximum durability of composites, practicability of the introduction of various modifying components and the optimum content of the organic binder.

**Key words:** asphalt concrete regeneration, composite based on organo-hydraulic binder, cold RAP-mix, fatigue life, temperature-structural analogy, rheological properties, maximum structural strength

**Introduction.** Asphaltic cement composites of various composition and preparation technology are widely used in road construction practice. These asphalt cement composites are hereinafter referred to as the concretes based on organo-hydraulic binders (concretes on OHB). The concrete that is on OHB is an artificial construction material with a structure combining the properties of thermodynamically incompatible organic (bitumen, tars) and hydraulic (cement, gypsum, ash, and etc.) binders. It is particularly

important when old spent materials are reused in new construction. The reuse of pavement layer materials is an urgent issue in the road-building industry of most countries around the world. Recycling or reuse (regeneration) of materials of existing pavements during their renovation and repair is not a new concept; such projects with varying degrees of success have been implemented since the beginning of the 20th century [1-3].

The regenerated materials without mineral binder (cement) exhibit viscoelastic properties within a wide temperature-time range; plastic deformations and fatigue cracks are the main possible defects in pavements based on the materials stabilized in such a way; and vice versa, when the mineral binder content is increased, the elastic properties and increased shear resistance at high temperatures are exhibited but brittle properties which stimulate low-temperature cracking and reduction of cyclic durability may appear to a greater extent [4-6]. In this regard, increasing attention is being paid to improving the quality of composite materials obtained from the processing of existing road pavements and their reuse in the repair and construction of new pavements [7-9].

In most countries of the world, the required quality indicators of cold regenerated mixtures and concretes are similar and are focused primarily on the regulation of properties via implementation of a set of tests for [10-12]:

- shear resistance;
- crack resistance and fatigue;
- water resistance and frost resistance.

When determining the design parameters required for pavements design and prediction of composite material properties, the provisions of the Williams-Landel-Ferry theory are often used with plotting the main deformation curve and its subsequent shifting depending on the predicted level of load and temperature impact [13-15]. This makes it possible to assess the composites within a wide range of external impacts, as well as to evaluate their fatigue and fatigue life more effectively.

The difficulty of assessing the properties of composite materials on OHB is that they combine the properties of coagulation, condensation and crystallization structures. In such systems, the arrangement of the various bonds is not uniform in the material volume; the strength and deformability of structural aggregates and clusters are also very heterogeneous. With regard to deformation and destruction mechanics, the structure of such materials can be represented in the form of a phenomenological model with a complex set of elastic, viscous and plastic bonds alternating in series and in parallel [16]. This is due to the fact that the processes of influence of hydraulic binder at the levels of microstructure, mesostructure and macro-structure are not sufficiently studied taking into account the properties of the polygranular filler, that is RAP.

**Thesis statement.** Many years of experimental studies of composites on OHB and strength analysis of their unbroken and broken structures have confirmed the possibility of phase contacts when the thickness of organic binder films is within 1-5  $\mu\text{m}$ . However, taking into account the low strength of phase contacts in the presence of such films, they cannot be defined as the main structure-forming factors. In this case, the main structure-forming element is phase-to-phase transition layers of cluster type, the formation of which is influenced both by physical (crystal intergrowth, adsorption, destruction of bitumen associates, ion transfer, formation of double electronic layers) and chemical (formation of bonds of  $\text{Me}^+-\text{OOCR}$  type, hydrogen  $-\text{H}-\text{O}$ , and etc.) processes. The  $\text{Me}^+-\text{OOCR}$  bonds are formed by metal ions, their oxides and hydroxides arising from hydration of the mineral binder due to interaction with oxygen, hydroxyl and carboxyl groups of the organic binder. The hydroxyl groups of hydration products and hydroxyl, nitrogen and sulphur compounds of bitumen are involved in formation of hydrogen bonds [17,18].

Thus, at the interface between the phases of the mineral and organic binder, a certain transition layer with special properties is formed; it is formed by clusters of different sizes, including nanodomains with a different charge transfer between the system components. In these cluster domains, the interaction of atoms differs from the interaction of atoms in isolated domains of cement, bitumen, and water that significantly affects the entire complex of system properties. Therefore, the structure of composites based on cement and bituminous binders is presented by the cement aggregates hydrated to varying degrees and a number of phase-to-phase transition layers.

According to the presented structure formation scheme, the hydraulic binder's impact on the composite structure and properties manifests itself by the mechanism of an active, colmatage and reinforcing filler. Moreover, it refers to the macro- and microstructure. First of all, the cement is a

reinforcing filler forming secondary structures in a bituminous or asphalt concrete matrix. The secondary structures of the mineral binder can interact with each other via phase contact or transition layers having higher strength than the bituminous matrix. As a result, the space reinforcing network with a "hinged" connection in the nodes of varying degrees of mobility is formed. The mineral binder has a colmatage effect because its aggregates, unlike inert fillers, are a rather monolithic system after hydration processes.

The structure formation processes are even more difficult when concretes on OHB are prepared with the use of RAP as fillers. The main feature of intercontact interaction of such filler and organo-hydraulic binder is the fact that RAP is a polygranular material in which the most part of grains is covered with an aged organic binder (as a rule, with a bituminous binder). Consequently, the majority of strong phase contacts with the formation of continuous condensation-crystallization backbone is developed via the filler particles not coated with bitumen, as well as due to partial penetration of crystal whiskers into the bitumen films and during interaction of hydration products with active bitumen components on the surface of RAP-particles. As a result, the formed space condensation and crystallization structure determines the elastic properties of the composite.

As described above, the strength of the condensation and crystallization backbone in the composites on OHB is determined by a ratio of concentrations by volume of bituminous and cement phases. As the volume of the bitumen phase is increased, the strength of the condensation and crystallization structure is decreased. However, the bitumen in the composite material at the macro- and mesostructure level can be located on the RAP surface in the form of structured films and fill the space between the aggregate particles and the products of cement hydration that contributes to reducing the porosity and increasing the hydrophobic properties of the composite.

Based on the full complexity of processes occurring when the structure of composites is formed on the RAP and organo-hydraulic binder, there is an important issue to ensure and predict their mechanical-and-physical properties. This issue should be addressed at the composition design stage. Currently, the majority of methodologies to assess the properties of such composite materials, including the methodology of Standard JTG F41-2008 "Technical Specifications for Highway Asphalt Pavement Recycling" [19], do not allow to predict the efficiency of one or another technical solution of cold regeneration of road asphalt concrete pavements while taking into account the features of interaction during the formation of condensation-and crystallization and coagulation structures of RAP with a complex organo-hydraulic binder within a wide range of their initial properties.

**Novelty.** The main method of predicting the strength and deformation characteristics within a wide range of temperatures and load action time is the principle of temperature-time analogy (TTA), according to which the experimental curves obtained at different temperatures can be combined by parallel shifting along the axis of time  $t$  (or deformation rate) [20,21].

Figure 1 shows the general curve of the relaxation modulus of concrete on OHB prepared using RAP (30% in the filler composition) with addition of 3% of cement and 5% of bitumen emulsion. This curve is plotted by horizontally shifting (with the factor  $a_t$ ) the outgoing relaxation constraints  $E(t)$  along the axis.  $\lg t$

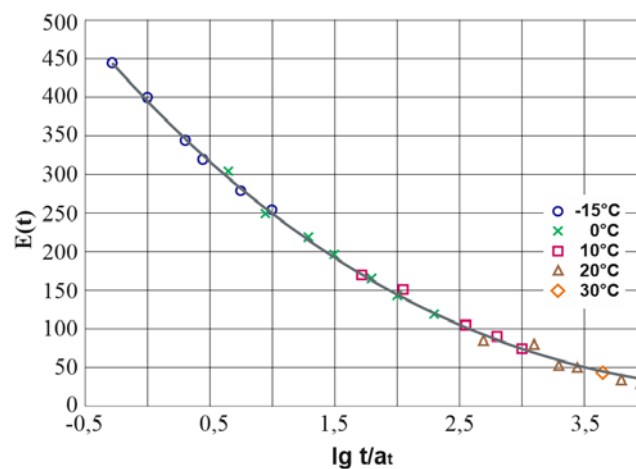


Figure 1 – A general curve of the relaxation modulus



In all cases, the temperature dependence of the shift factor  $\lg a_t$  from  $(T - T_0)$  is well represented by the power function:

$$\lg a_t = A \cdot (T - T_0)^m, \quad (1)$$

where  $T$  – test temperature, °C;  $T_0$  – reduction temperature, °C;  $A$  and  $m$  – constant parameters.

The examples of parameter values of dependence of this type on the material composition are given in table 1.

Table 1 – The value of constant parameters to determine the shift factor  $a_t$

Composition*	A, 10 <sup>2</sup>	m	$\lg a_t$ **
BE – 3%; P – 0%	3.5	1.30	1.72
BE – 5%; P – 0%	3.7	1.34	2.05
BE – 3%; P – 2%	4.1	1.21	1.54
BE – 3%; P – 4%	4.9	1.09	1.28
BE – 5%; P – 6%	5.2	1.02	1.10

\* The RAP content in the filler composition is 30%.  
 \*\* reduction to temperature 10°C (test temperature – 30°C).  
 BE – Bitumen emulsion.  
 P – Portland cement.

As can be seen from table 1, the shift factor is decreased as the weight fraction of the hydraulic binder is increased, indicating that the temperature and time sensitivity of the concretes on the organo-hydraulic binders are decreased if the condensation- crystal lattice is formed in their structure.

At the same time, the classical method of applying the temperature-time analogy is valid in the linear range for analyzing the relaxation curves at low strain levels or the creep curves at low stresses. This provision does not allow us to use it for the analysis of strength properties and other characteristics related to the process of composite material destruction.

The concretes with a composite structure containing the thermodynamically incompatible binders have nonlinear viscoelasticity and are complex in their thermo-rheological properties. A simple visual analysis shows that parallel transfer does not allow the strength-versus-strain rate curves to be aligned (figure 2). Therefore, the reduction factor (the value of shifting the curves along the axis of time or strain rate) depends not only on the temperature but also on the material properties and the degree of strain condition. The situation is even more complicated when RAP obtained from reprocessing of asphalt concrete pavements is used as a filler (part of the filler).

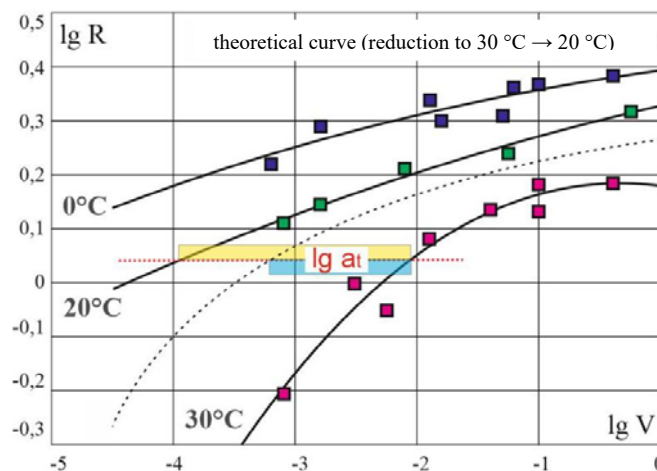


Figure 2 – Bending strength from deformation rate for the concrete based on organo-hydraulic binder

This is due to the features of the composite material structure as a system with a complex set of elastic  $n_r$  and viscous bonds  $n_v$  [16]; that's why the reduction factor  $\lg a_t$  depends mainly on the number of elastic bonds involved in the deformation process. It is valid since the temperature, tension, time changes cause a change in the course of relaxation processes on which the value  $n_r$  directly depends.

If  $n_r = 1$ , then the material properties are practically independent of temperature, stress, time, i.e. the material is "absolutely elastic" and the reduction factor is equal to 1 ( $\lg a_t = 0$ ). If  $n_r$  is decreased and tends to zero, then the material properties become close to viscous ones; the value  $\lg a_t$  can be determined by the Williams-Landel-Ferry equation (WLF) [20, 21]:

$$\lg a_t^{WLF} = -\frac{17,44 \cdot (T - T_q)}{51,6 + (T - T_q)}, \quad (2)$$

where  $T$  – current temperature, K;  $T_q$  – glass transition temperature, K.

Using the additivity concept, we obtain:

$$\lg a_t = (1 - n_r) \cdot \lg a_t^{WLF}. \quad (3)$$

The value  $n_r$  can be determined by the condition [16]:

$$n_r = \frac{E_t}{E_c} = \left( \frac{R_t}{R_c} \right)^{\frac{1}{m}}, \quad (4)$$

where  $E_t$  and  $R_t$  – relaxation modulus and material strength under specific conditions of loading;  $E_c$  and  $R_c$  – maximum values of modulus and strength within the entire range of temperatures and load action time;  $m$  – parameter that depends on the material type. For example, for asphalt cement compositions it ranges from 0.8 to 0.95.

Thus, the value  $a_t$  can be characterized not only by the viscous properties but also by the elastic properties of the composite material. Taking into account that the changes in the composition and structure of concretes on OHB, in the stress degree at the same temperature and time of its action leads primarily to change of the value  $n_r$ , it is possible to predict its rheological properties in case of a change in temperature or time of load action. From the point of view of rheological behavior, the change of  $n_r$  due to the structure variation is similar to its change due to variation of temperature or time of load action, taking into account the initial properties of composite material. This provision allows the concept of temperature-structural analogy (TSA) to be applied in a similar way to the concept of temperature-time analogy (TTA).

**Study methods and results.** Dependence (3) according to the WLF is valid if the glass transition temperature is taken as the reduction temperature. In the case of a random selection of the reduction temperature, it is necessary to adjust the value of WLF factors according to the procedure [21]. The experimental studies and calculations (Fig. 2) have shown that the theoretical curve obtained by the TTA method (dashed line) differs from the experimental curves.

The WLF equation (2) is valid if the glass transition temperature is taken as the reduction temperature. In case of random selection of the reduction temperature, it is necessary to adjust the value of WLF factors according to the procedure [20]. It is possible to use a simplified dependence obtained by shifting the WLF curve along the axes of temperature and reduction factor  $\lg a_t$ . In this case, the factor  $T_{pr}$  of reduction to random temperature is determined from the expression:

$$\lg a_t = \lg a_t^{WLF} - \lg a_t^{T_{pr}}, \quad (5)$$

The value  $\lg a_t^{T_{pr}}$  is calculated by (2) replacing the current temperature ( $T$ ) with the reduction temperature ( $T_{pr}$ ).

Table 2 shows the values of the factor of creep modulus reduction to the temperature of 0°C which is obtained experimentally (by combining the curves) and theoretically. The studies were carried out using the samples from RAP with addition of 3 % of cement and 5 % of bitumen emulsion at a temperature of 0°C and 20°C at two levels of strain. In case of theoretical determination, the value  $n_r$  was obtained by  $\lg a_t$  (2), then the value  $\lg a_t$  was obtained using (2) and (5). The temperature of structural glass transition ( $T_q$ ) was 12°C.

Table 2 – Values of the reduction coefficient for different methods of determination

Time of load action at 20°C, s	Number of elastic bonds according to (4) under strains, MPa		Logarithm of the factor of reduction $\lg a_t$ to temperature of 0°C under strains, MPa	
	0.2	0.4	0.2	0.4
3.0	0.70	0.60	$\frac{-0.7(-0.99)}{-3.3}$	$\frac{-1.1(-1.3)}{-3.3}$
15.0	0.22	0.14	$\frac{-2.6(-2.57)}{-3.3}$	$\frac{-3.0(-2.9)}{-3.3}$
30.0	0.15	0.08	$\frac{-2.95(-2.86)}{-3.3}$	$\frac{-3.2(-3.09)}{-3.3}$

Note. The numerator contains experimental data; theoretical data obtained using (2) and taking into account ( $T_{pr}$ ) and (3) are given in brackets; the denominator contains data obtained using (2).

The table shows that the values  $\lg a_t$  obtained by the proposed procedure are close to experimental data while those data calculated by the WLF equation, have significant deviations and do not take into account the strain level and time. The changes in the concrete composition and structure, in the strain level at the same temperature and time of load action lead primarily to changing the value  $n_r$ . As a result, the material takes on the rheological properties that it would have when the temperature or time of load actions changes, i.e. in terms of rheological behaviour, the change of  $n_r$  due to a structure variation is similar to its change due to a variation of temperature or time of load action for the source material. This provision allows developing the concept of temperature-structural analogy (TSA).

Let's assume that the material at a temperature  $T_1$  and time of load action  $t_1$  has some value of properties  $E_1$  that corresponds to the quantity of elastic bonds  $n_{r1}$ . As the temperature is varied from  $T_1$  to  $T_2$ , the material properties are also varied. As a result, the material will have the same values of properties  $E_1$  at some time of load action  $t_2$ .

The difference between the factors of reduction to temperature  $T_2$  and  $T_1$  taking into account (3) is as follows:

$$\Delta \lg a_t^{T_{pr}} = \frac{-17.44 (T_2 - T_q)}{51.6 + (T_2 - T_q)} (1 - n_{r1}) + \frac{17.44 (T_1 - T_q)}{51.6 + (T_1 - T_q)} (1 - n_{r1}). \quad (6)$$

The same property values  $E_1$  at time of load action  $t_2$  can be obtained by keeping the temperature  $T_1$  but by changing the number of elastic bonds from  $n_{r1}$  to  $n_{r2}$  due to the material structure (e.g. by varying the amount of cement in the composite, binder modification, and etc.). This provision can be considered to be valid because the glass transition temperature is almost independent of the structure [17].

If the value of elastic bonds is varied from  $n_{r1}$  to  $n_{r2}$ , the difference between the reduction factors will be equal to:

$$\Delta \lg a_t^{T_{pr}} = \frac{-17.44 (T_1 - T_q)}{51.6 + (T_1 - T_q)} (1 - n_{r2}) + \frac{17.44 (T_1 - T_q)}{51.6 + (T_1 - T_q)} (1 - n_{r1}). \quad (7)$$

Considering the equality of dependencies (5) and (6) and having made some transformations, we will find:

$$T_2 = \frac{51.6A + T_q(1 - A)}{1 - A}, \quad (8)$$

where

$$A = \frac{(T_1 - T_q)(1 - n_{r2})}{[51.6 + (T_1 - T_q)](1 - n_{r1})}. \quad (9)$$

Formula (8) allows calculating the temperature equivalent ( $T_2 - T_1$ ) to the structural equivalent of the material ( $n_{r2} - n_{r1}$ ).

According to the TSA concept, it is possible to predict the properties of materials having a different composition within a wide range of temperatures and load time. For this purpose it is enough to obtain dependence of material properties of one composition on time of load action at a fixed temperature and strain, then obtain dependence  $n_{r2}$  on the material composition for one time of load action  $t_1$ . The value  $T_2$  is calculated using (8); and the value  $\Delta \lg a_t^{T_{pr}}$  is calculated by formula (7).

If experimentally obtained dependence  $\Delta \lg a_t^{T_{pr}}$  on the temperature with a certain value  $n_{r1}$ , then for using this dependence with other values  $n_{r2}$ , the reduction factor should be multiplied by the ratio  $(1 - n_{r2}) / (1 - n_{r1})$ .

The TSA concept can be used as a fundamental one in the design of concrete mixes on organo-hydraulic binders for certain conditions of their use based on the specified level of reliability (service life) of the road surface dressing (road pavement). Thus, there is a possibility to estimate the design characteristics of concretes on organo-hydraulic binders which values are difficult to find by direct experiment using a method of standard elementary tests, for example, elasticity modulus for various temperatures and time of load action  $E_{T(V)}$  [16] by formula (4).

For example, multi-year researches confirm the validity of the empirical dependence relating the value of the maximum structural strength ( $R_c$ ) to the maximum elasticity modulus ( $E_c$ ) within the entire range of temperature and time of load action:

$$E_c = 3,6 \cdot (16,3 \cdot R_c)^{1,9}. \quad (10)$$

Thus, using the principles of temperature-structural analogy, it is possible to predict the properties of composites based on organo-hydraulic binders as applied to the mechanistic and empirical methods of calculation for road pavements; as well as it is possible to calculate and directly adjust the long-term indicators of properties at the stage of concrete composition design. For example, the required value of elasticity modulus  $E_{V_1}$  at the time of load action  $V_1$  can be directionally adjusted while keeping the temperature conditions and the current load but changing the number of elastic bonds from  $n_{r1}$  to  $n_{r2}$ , i.e. due to the material structure (for example, by varying the amount of cement in the composition of bitumen cement composite binder).

**Conclusion.** For preparing the quality concretes during the regeneration process, RAP should be treated with complex organo-hydraulic binders. The received structure is very complex that is reflected in the behaviour of the received composite in a temperature-time field and by the estimation of its reliability and durability.

The main feature of the inter-contact interaction between the filler and the organo-hydraulic binder is poly-granularity and inhomogeneity of RAP in which the most part of grains are covered with an aged organic binder. Consequently, the majority of strong phase contacts of cement with the formation of continuous condensation-crystallization backbone is developed via the filler particles not coated with bitumen, as well as due to partial penetration of crystal whiskers into the bitumen films and during interaction of hydration products with active bitumen components on the surface of RAP-particles.

The concretes with a composite structure containing the thermodynamically incompatible binders have nonlinear viscoelasticity and are complex in their thermo-rheological properties. The reduction factor (the value of shifting the curves along the axis of time or strain rate) for such materials depends not only on the temperature but also on the material properties and the degree of strain condition.

As a result of studies performed, the concept of temperature-structural analogy is proposed. Along with the temperature and time factor, it takes into account the features of the structure described by the ratio of elastic and viscous bonds. The TSA concept allows obtaining necessary structural features for specific temperature-time factors. Using this concept, it is possible to predict the properties of composites based on OHB suitable for mechanistic and empirical methods of calculation of road pavements. As a result, it is possible to calculate the long-term indicators of properties at the stage of concrete composition design that determines the prerequisites for their directional adjustment.

It is necessary to take into account that an increase in cement content leads to an increase of strength properties and durability at an elastic stage of work; however, the resistance to dynamic impacts and cracks is decreased that reduces durability. In this regard, the proposed method to select the composition of concretes on OHB based on the optimal ratio of elastic and viscous bonds, taking into account the properties of RAP and the amount of cement, allows adjusting effectively the durability and reliability indicators.

**Б. М. Хрусталеv<sup>1,4</sup>, Т. Лю<sup>1,2,3</sup>, А. В. Бусел<sup>1,5</sup>, Ж. Ли<sup>1,3</sup>,  
В. А. Веренько<sup>1,4</sup>, В. В. Занкович<sup>1</sup>, Б. Шан<sup>2,3</sup>**

<sup>1</sup>Автомагистральдарды күтіп ұстау жөніндегі Гаюоань Хэнань технологиялық компаниясы (Біліктілігі жоғары шетелдік мамандар орталығы), Синьсян, Қытай;

<sup>2</sup>Автомагистральдарды күтіп ұстауға арналған ұлттық инженерлік жабдықтар зертханасы, Синьсян, Қытай;

<sup>3</sup>Автомагистральдарды диагностикалау және күтіп ұстау бойынша Хэнань провинциясының негізгі зертханасы, Синьсян, Қытай;

<sup>4</sup>«Политехник» Беларусь ұлттық техникалық университеті Ғылыми-технологиялық паркі, Минск, Беларусь;

<sup>5</sup>«БелдорҒЗИ» «Беларус жол ғылыми-зерттеу институты» мемлекеттік кәсіпорны, Минск, Беларусь

#### **ӨНДЕЛГЕН АСФАЛЬТБЕТОНДЫ ЖОЛ ЖАМЫЛҒЫЛАРЫНАН АЛЫНҒАН ТҮЙІРШІКТЕР НЕГІЗІНДЕГІ КОМПОЗИТТЕРДІҢ ҚҰРЫЛЫМДЫҚ-МЕХАНИКАЛЫҚ ҚАСИЕТТЕРІН БОЛЖАУ ӘДІСТЕМЕСІ ЖӘНЕ БАҒАЛАУ**

**Аннотация.** Бұл мақалада асфальт түйіршіктері негізіндегі композиттердің беріктілік және деформативті қасиеттерін бағалаудың әдіснамалық ерекшеліктерін талдау және құрылым құру үдерістерін зерттеу нәтижелері берілген. Жаңа материалдар беріктілік пен сенімділіктің талап етілетін мәнін қамтамасыз етуге мүмкіндік беретін олардың физикалық-механикалық сипаттамаларына объективті техникалық талаптарды әзірлеу мақсатында температура-уақыт өрісінде олардың әрекет ерекшеліктерін зерттеуді талап етеді.

Температура-уақыт аналогын қолданудың классикалық әдісі деформацияның шағын деңгейлерінде релаксациялық қисықтарды талдауға арналған сызықтық аймақта дұрыс. Мұндай жағдай оны композиттік материалды бұзу процесімен байланысты беріктік қасиеттері мен басқа да сипаттамаларын талдау үшін пайдалануға мүмкіндік бермейді. Құрамында термодинамикалық үйлеспейтін байланыстырғыш бар композициялық құрылым бетондары сызықсыз тұтқырлыққа ие және терморологиялық күрделі болып табылады. Композициялық материалдар үшін келтіру коэффициенті (қисықтардың уақыт осі бойымен жылжу шамасы немесе деформация жылдамдығы) температураға ғана емес, материалдың қасиеттеріне де, сондай-ақ кернеулі күй деңгейіне де байланысты болады. Бұл серпімді және тұтқыр байланыстардың кешенді жиынтығы бар жүйе ретінде композиттік материалдар құрылымының ерекшеліктерімен байланысты, осыған байланысты келтіру коэффициенті деформациялау процесіне тартылған серпімді байланыстардың санына байланысты.

Зерттеудің негізіне органикалық-гидравликалық тұтқыр композиттердің қасиеттерін болжауға мүмкіндік беретін температуралық-құрылымдық ұқсастық принциптері алынған. Бұл жол жамылғысының әр түрлі қабаттарын салуға арналған материалдардың құрамын жобалауға және алу технологиясын анықтауға мүмкіндік береді.

Жобалаудың ұсынылған әдістемелік принциптері асфальттүйіршіктердің қасиеттері мен цемент мөлшерін ескере отырып, серпімді және тұтқыр байланыстардың оңтайлы арақатынасын белгілеуге негізделген. Мұндай тәсілді пайдалану композиттердің барынша ұзақ мерзімділігіне қол жеткізу перспективасын, түрлі түрлендіргіш компоненттерді енгізудің мақсаттылығын және органикалық тұтқыр-тұтқыр шығынының оңтайлы шегін бағалауға мүмкіндік береді.

**Түйін сөздер:** асфальтбетонды регенерациялау, органикалық-гидравликалық байланыстырғыш композит, салқын регенерацияланған асфальтбетонды қоспа, циклдық ұзақ мерзімділік, температуралық-құрылымдық ұқсастық, реологиялық қасиеттер, максималды құрылымдық беріктік.

**Б. М. Хрусталеv<sup>1,4</sup>, Т. Лю<sup>1,2,3</sup>, А. В. Бусел<sup>1,5</sup>, Ж. Ли<sup>1,3</sup>,  
В. А. Веренько<sup>1,4</sup>, В. В. Занкович<sup>1</sup>, Б. Шан<sup>2,3</sup>**

<sup>1</sup>Хэнаньская технологическая компания Гаоюань по содержанию автомагистралей (Центр иностранных специалистов высокой квалификации), Синьзян, Китай;

<sup>2</sup>Национальная инженерная лаборатория оборудования для содержания автомагистралей, Синьсян, Китай;

<sup>3</sup>Ключевая лаборатория провинции Хэнань по диагностике и содержанию автомагистралей, Синьсян, Китай;

<sup>4</sup>Научно-технологический парк Белорусского национального технического университета «Политехник», Минск, Беларусь;

<sup>5</sup>Государственное предприятие «Белорусский дорожный научно-исследовательский институт «БелдорНИИ», Минск, Беларусь

## **ОЦЕНКА И МЕТОДИКА ПРОГНОЗИРОВАНИЯ СТРУКТУРНО-МЕХАНИЧЕСКИХ СВОЙСТВ КОМПОЗИТОВ НА ОСНОВЕ ГРАНУЛЯТОВ ИЗ ПЕРЕРАБОТАННЫХ АСФАЛЬТОБЕТОННЫХ ДОРОЖНЫХ ПОКРЫТИЙ**

**Аннотация.** В настоящей статье представлены результаты исследования процессов структурообразования и анализ методологических особенностей оценки прочностных и деформативных свойств композитов на основе асфальтогранулятов. Новые материалы требуют изучения особенностей их поведения в температурно-временном поле с целью выработки объективных технических требований к их физико-механическим характеристикам, позволяющих обеспечить требуемые значения прочности и надежности.

Классический способ применения температурно-временной аналогии справедлив в линейной области для анализа релаксационных кривых при небольших уровнях деформации или кривых ползучести при небольших напряжениях. Такое положение не позволяет использовать его для анализа прочностных свойств и других характеристик, связанных с процессом разрушения композитного материала. Бетоны компо-

зиционной структуры с содержанием термодинамически несовместимых вяжущих, обладают нелинейной вязкоупругостью и являются терморейологически сложными. Для композиционных материалов коэффициент приведения (величина смещения кривых вдоль оси времени или скорости деформации) зависит не только от температуры, но и свойств материала, а также уровня напряженного состояния. Связано это с особенностями структуры композитных материалов как системы с комплексным набором упругих и вязких связей, в связи с чем коэффициент приведения зависит от числа упругих связей, вовлеченных в процесс деформирования.

В основу исследования положены принципы температурно-структурной аналогии, позволяющие прогнозировать свойства композитов на органо-гидравлических вяжущих. Это позволяет направленно проектировать состав и определять технологию получения материалов для устройства различных слоев дорожных одежд.

Предложенные методологические принципы проектирования основаны на установлении оптимального соотношения упругих и вязких связей с учетом свойств асфальтогранулятов и количества цемента. Использование такого подхода позволяет оценивать перспективность достижения максимальной долговечности композитов, целесообразность введения различных модифицирующих компонентов и оптимальные пределы расхода органического вяжущего.

**Ключевые слова:** регенерация асфальтобетона, композит на органо-гидравлическом вяжущем, холодная регенерированная асфальтобетонная смесь, циклическая долговечность, температурно-структурная аналогия, реологические свойства, максимальная структурная прочность.

#### **Information about authors:**

Khroustalev B.M., Doctor of Engineering Science, Professor, Henan Gaoyuan Highway Maintenance Technology Co., Ltd (Henan Center for Outstanding Overseas Scientists); post@park.bntu.by; <https://orcid.org/0000-0002-4759-6302>

Veranko V.A., Doctor of Engineering Science, Professor, Expert of Henan Gaoyuan Highway Maintenance Technology Co., Ltd (Henan Center for Outstanding Overseas Scientists); verenko.vladimir@gmail.com; <https://orcid.org/0000-0002-5867-5540>

Liu T., Director General of Henan Gaoyuan Highway Maintenance Technology Co., Ltd; liutingguo@chngaoyuan.com; <https://orcid.org/0000-0002-0208-1276>

Busel A.V., Doctor of Engineering Science, Professor, State Enterprise "Belarusian Road Scientific and Research Institute «BeldorNII»"; bulex@tut.by; <https://orcid.org/0000-0003-1168-1780>

Zankavich V.V., Doctor of Science, Expert of Henan Gaoyuan Highway Maintenance Technology Co., Ltd (Henan Center for Outstanding Overseas Scientists); vitali.zankavich@chngaoyuan.com; <https://orcid.org/0000-0002-8115-2342>

Li Zh., Head of Henan Provincial Key Laboratory of Highway Detection and Maintenance; lizhongyu@chngaoyuan.com; <https://orcid.org/0000-0002-1135-3122>

Shang B., Researcher of the National Engineering Laboratory for Highway Maintenance Equipment; iver-sb@163.com; <https://orcid.org/0000-0002-3423-146X>

#### **REFERENCES**

[1] Vaitkus A., Gražulytė J., Juknevičiūtė-Žilinskienė L., Andrejevas V. 2017. Review of Lithuanian Experience in Asphalt Pavements Cold Recycling, in *Proc. of the 10<sup>th</sup> International Conference «Environmental Engineering»*: selected papers. 27–28 April 2017, Vilnius, Lithuania. Vilnius Gediminas Technical University. <https://doi.org/10.3846/enviro.2017.153> (in Eng.).

[2] Veranko V.A., Makarevich A.A. 2008. Experience of using in-situ cold recycling technology when repair of streets of the Minsk city. *Automobile roads and bridges* N 1 (2008): 13-18. (in Russ.)

[3] Jähren C.T., Ellsworth B.J., Cawley B., Bergeson K. 1998. *Review of Cold In-Place Recycled Asphalt Concrete Projects*. Iowa DOT Project HR-392. Ames: Iowa State University. 46 p. (in Eng.).

[4] Teltaev B. 2014. Evaluation of low temperature cracking indicators of hot mix asphalt pavement, *International Journal of Pavement Research and Technology* 7(5): 343-351 (in Eng.).

[5] Teltaev B., Radovskiy B. 2016. Low temperature cracking problem for asphalt pavements in Kazakhstan, *RILEM Bookseries* 13: 139-144 (in Eng.).

- [6] Teltaev B., Radovskiy B. 2018. Predicting thermal cracking of asphalt pavements from bitumen and mix properties, *Road Materials and Pavement Design* 19(8): 1832-1847 (in Eng.).
- [7] Mollenhauer K., Simnofske D., Valentin J., Čížková Z., Suda J., Batista F., McNally C. 2016. Mix designs for cold recycled pavement materials considering local weather and traffic conditions, in *Proc. of 6<sup>th</sup> Eurasphalt & Eurobitume Congress: selected papers*, 1-3 June 2016. Prague, Czech Republic. Czech Technical University in Prague. <https://dx.doi.org/10.14311/EE.2016.357> (in Eng.).
- [8] Ayar P. 2018. Effects of additives on the mechanical performance in recycled mixtures with bitumen emulsion: An overview, *Construction and Building Materials* 178: 551-561. <https://doi.org/10.1016/j.conbuildmat.2018.05.174> (in Eng.).
- [9] Lin J., Hong J., Xiao Y. 2017. Dynamic characteristics of 100% cold recycled asphalt mixture using asphalt emulsion and cement, *Journal of Cleaner Production* 156: 337-344. <https://doi.org/10.1016/j.jclepro.2017.04.065> (in Eng.).
- [10] Tabaković A., McNally C., Fallon E. Specification development for cold in-situ recycling of asphalt, *Construction and Building Materials* 102: 318-328. <https://doi.org/10.1016/j.conbuildmat.2015.10.154> (in Eng.).
- [11] Kim Y., Lee H.D. 2006. Development of mix design procedure for cold in-place recycling with foamed asphalt, *Journal of Materials in Civil Engineering* 18(1): 116-124. [https://doi.org/10.1061/\(ASCE\)0899-1561\(2006\)18:1\(116\)](https://doi.org/10.1061/(ASCE)0899-1561(2006)18:1(116)) (in Eng.).
- [12] Meocci M., Grilli A., La Torre F., Bocci M. 2017. Evaluation of mechanical performance of cement-bitumen-treated materials through laboratory and in-situ testing, *Road Materials and Pavement Design* 18: 376-389. doi:10.1080/14680629.2016.1213506 (in Eng.).
- [13] Valentin J., Suda J., Zak J. 2015. *Report on Durability of cold-recycled mixes: Complex dynamic modulus and master curves of cold recycling mixes*. CEDR Transnational Road Research Programme Call 2012: Recycling: Road construction in a post-fossil fuel society. Czech Technical University in Prague. 19 p. doi: 10.13140/RG.2.1.3439.6327 (in Eng.).
- [14] Lee H., Kim Y. 2007. *Validation of the mix design process for cold in-place rehabilitation using foamed asphalt*. Final Report (IHRB Project TR 474). Public policy center civil and environmental engineering university of Iowa. 234 p. Available from Internet: <http://publications.iowa.gov/id/eprint/5311> (in Eng.).
- [15] Gandi A., Carter A., Singh D. 2018. Effect of binder type on Full Depth Reclamation material behavior, *International Journal of Pavement Research and Technology*. 11 p. <https://doi.org/10.1016/j.ijprt.2018.08.005> (in Eng.).
- [16] Li Z., Liu T., Shi J., Veranko U., Zankavich V. Fatigue resistance of asphalt concrete pavements. Peculiarity and assessments of potentials, *The Baltic Journal of Road and Bridge Engineering* XII (4): 270-275. <http://dx.doi.org/10.3846/bjrbe.2017.34> (in Eng.).
- [17] Veranko V.A. 1993. *Road composite materials. Structure and mechanical properties*. Science and Technology. Minsk. 246 p. (in Russ.).
- [18] Veranko V.A. 1998. Road concretes based on organo-hydraulic binders (Theory and practical using): Abstract of dissertation for the degree of Doctor of Technical Sciences, Belarusian State Polytechnical Academy, Minsk. 40 p. (in Russ.).
- [19] JTG F41-2008 公路沥青路面再生技术规范[Technical Specifications for Highway Asphalt Pavement Recycling]. Chinese Standard. Available from Internet: <http://www.xgtzx.com/upload/files/201711/15095874957748.pdf> (in Eng.).
- [20] Williams M.L., Landel R.F., Ferry J.D. 1955. The Temperature Dependence of Relaxation Mechanisms in Amorphous Polymers and Other Glass-forming Liquids, *Journal of the American Chemical Society* 77 (14): 3701-3707. doi: 10.1021/ja01619a008. (in Eng.).
- [21] Veranko V.A., Makarevich A.A. 2010. Prediction of design characteristics of concretes based on organo-hydraulic binders in wide ranges of temperatures and deformation rates, *Bulletin of Belorussian National Technical University: scientific and technical journal* 3. 20-27. ISSN 2414-0392 (in Russ.).



---

---

**Publication Ethics and Publication Malpractice  
in the journals of the National Academy of Sciences of the Republic of Kazakhstan**

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct ([http://publicationethics.org/files/u2/New\\_Code.pdf](http://publicationethics.org/files/u2/New_Code.pdf)). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

[www:nauka-nanrk.kz](http://www.nauka-nanrk.kz)

**ISSN 2518-170X (Online), ISSN 2224-5278 (Print)**

<http://www.geolog-technical.kz/index.php/en/>

Редакторы *Д. С. Аленов, М. С. Ахметова, Т. А. Апендиев*  
Верстка *Д. А. Абрахимовой*

Подписано в печать 13.04.2020.  
Формат 70x881/8. Бумага офсетная. Печать – ризограф.  
13 п.л. Тираж 300. Заказ 2.